

sarbak



The fortress of honor with its production and of trust with its quality

www.sarbak.com.tr

Sarbak Metal

Our company will continue to exist as an internationally leading company with activities carried out in the field of non-ferrous metal brass production by extending to many sectors from automotive to industry.

We are renewing our experience and accumulation in this day and age when the world continues to grow fast and the needs renew themselves every day.

The satisfaction of you, our valuable customers, is a must for us while serving with our innovative approaches in the brass industry with our experienced technical team and engineering staff who are fully equipped and renew themselves every day.

Even in the smallest project of our company, every precaution has been taken for the health and safety of our employees.

In carrying out all these activities, with the understanding that every source may end someday, it is our primary duty to adopt and disseminate sustainable environmental consciousness.

With an understanding of quality, customer-focused approach and ensuring our employees' health and safety, we are happy to say that we are doing needs to be done in our activity field and we are always ready to take more responsibility in order to provide a livable future for our children.

Andon ARAKELYAN



Since 1976 Sarbak Metal;

Sarbak Metal, which was established in a shop of 5 m2 in Perşembe Pazarı in Istanbul Karaköy and which plays an important role in the development of Turkish industry, has become one of the biggest companies in the sector with its new factory established in 2002 in Çerkezköy Organize Sanayi Bölgesi on 21 thousand m2 area.

In its first years, Sarbak Metal started rod production by applying cold drawing to the ingots, which were obtained by smelting the metal in crucible furnaces and pouring to permanent molds, that were heated in fuel oil heaters and extrusion ed in manually controlled extrusion press with 750 ton leverage and limited functions, in the chain type drawing machine.

Sarbak Metal, which adopts sustainable development and customer satisfaction as principle and keeps up with the developing technology, has started production with induction melting and continuous casting, induction annealing, extrusion in presses with 2.250 and 2.200 tons of pressure, and cold drawing in combined automatic machines In the new plant which started its activity in 2002 in Çerkezköy, it has doubled its production with the latest technology and reached 5000 tons / month capacity. With the new investments it made on the factory in 2014, it increased its production capacity to 8.000 tons / month.

In 1976, Mr. Andon Arakelyan, our esteemed founder and Chairman of the Board of Directors, started off with a dream. SARBAK METAL is actually a complete success story. We can not deny the dedication of our founder who loves his work and produces brass material as if each time he is bringing a new life to the World. At this point of SARBAK METAL, not only his self-sacrificing work but also his entrepreneurial and innovative spirit played an important role. He saw the risks, assessed them, continued on his path by taking risks. Instead of giving up in difficult times, he overcome the risks by showing each colleague how to become one. The desire to produce better with the tendencies of having the best machines and providing the most equipped personnel employment have brought SARBAK METAL to the present.

As Henry Ford says, "If you need a machine and you do not buy it, you have already paid for it."



Sarbak and Innovation

Our goal is to make people's lives easier, better, healthier and more beautiful with our technology. As Sarbak Metal A.Ş., we have established our innovation strategy to meet the needs of our customers with the increasingly qualified brass materials with the developing technology by using our knowledge and experience from past to present.

The driving factors of innovation at Sarbak Metal are both internal and external sources. Ideas and opinions of employees at every level within the company are transformed into product innovation, process innovation and customer focused innovation applications by evaluating them. Sarbak Metal also uses the results of research and development activities carried out with universities for innovation applications, the information acquired from various consulting services and the technology transfers that are acquired through commercial agreements..

Our Innovation Mission

We place innovation culture in Sarbak Metal and have it adopted by all of our staff. We determine the current and future needs of our customers and to produce such products it brings the necessary technology and talents to Sarbak Metal.

Our Innovation Goals

- In order to minimize the problems encountered during our customers' manufactures, customer specific alloys and technologies are being developed.
- To create a new market for Sarbak Metal by introducing lead-free brass alloys, superior properties of the product and its being environment friendly.
- To replace the efficiency of our production technology with the new generation machine park to provide 10% energy in order to reduce production costs and environmental impacts.



Export


Our company, which has started export in 1994, is in the first place of its product class in Turkey's exports and this success is crowned with the stars of exports awards that are presented by İMMİB (Istanbul Mine and Metals Exporters Association) every year. It exports 40% of its production to countries in many different geographies, mainly European Union countries.

Both our company and our country are actively represented by our foreign trade department on international platforms, at meetings, in associations. Our factory welcomed the members of the International Wrought Copper Council (IWCC) and the Organization of European Copper Alloy Ingot Makers (OECAM). It contributes to the development of our industry, the introduction and solution of problems, and most importantly the recognition of Turkey's copper alloys sector by the World by taking responsibilities at various levels of IWCC and OECAM organizations. Our company has been working in Istanbul Chamber of Industry and Istanbul Copper and Brass Industries Association Board of Directors for many years and takes part in all necessary work for solution by monitoring the sectoral problems day by day. For the purpose of improving the exports of our industry, we are working on the URGE project which is formed jointly with İDDMİB in the activities of the Association.

We follow developments in the world one by one, we participate in many international symposiums, conferences and meetings and we are inform our sector about the gain we receive there by posting it on our web site or by sharing it with our colleagues in NGOs that we work.

While living the rightful pride of being one of the few producers in the world in the production of new generation lead-free brass, the secret of increase in the exports of these alloys every year compared to the previous year is that making the right presentation of our products at the fairs and meetings we attended as well as our active role in the development of these alloys and our knowledge.

We are always pleased to assist our colleagues as much as we can in all aspects of our business, both in terms of foreign trade and sectoral issues.

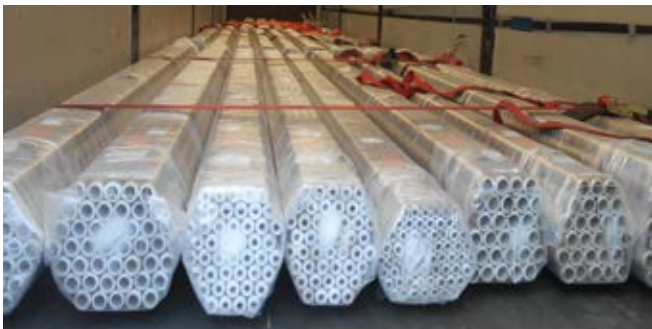

Integrated Management System

Our policy as Sarbak Metal, is to determine the current and future product needs and requirements of our customers and to bring these technologies and talents to Sarbak Metal to produce such products by using the resources we have in the most efficient way through an efficient IMS (Integrated Management System) supported by ERP, with the participation of all our employees and an innovation-oriented value system.

All the QMS (Quality Management System) - EMS (Environmental Management System) - OHSAS (Occupational Health and Safety) - ISMS (Information Security Management System) legislation, to keep up to date with the new developments of the Integrated Management System (IMS) which we have established in order to observe the benefit of all the elements we affect, especially our employees, to establish a good and effective communication channel with the authorities, suppliers, subcontractors, non-governmental organizations, local residents, the whole community and other stakeholders and to carry out the necessary activities to increase the competence in our employees' QMS, IMS, OHSAS and ISMS, we will keep all our wastes under control and reduce harmful wastes as much as possible and eliminate the ones that are not recovered and we will be able to use energy, raw materials and natural resources efficiently and keep the IMS open to public inspection, we want to ensure operational safety in all the factors stemming from our activity, protect our employees against all kinds of oppression, comply with all the ethical rules we interact with, In the scope of ISMS (Information Security Management System), we will ensure the security of the institutions and organizations we serve and ensure the security of the information assets we use for the services we provide, With in the scope of the QMS, we ensure that customer needs and expectations are met at the lowest cost and with in the desired delivery period with the surplus and reliability continuity. In order to achieve these objectives, we are committed to being in harmony with all of our employees and organizations we work with. We respect for everything. We declare and undertake to develop our systems established in line with the objectives we have determined together with the IMS, continuously and in a timely manner, by adding our technology and our ability.

Quality Management System

Quality is our guide in our products and services. Our policy is to ensure that our products comply with all relevant standards with quality, performance and reliability. There is a well-defined quality target to achieve this goal, which is known to all units and the necessary work is fulfilled. Each Sarbak Metal A.Ş. employee tries to do his/her job in a timely, correct manner that does not need to be corrected later. Quality is the duty of everyone in this sense. Our aim is to meet customer needs and expectations with the lowest cost and within the required delivery time and to provide continuity in quality and reliability.

Occupational Health and Safety Management

Our company which produces brass in nonferrous metals sector, continues to exist by accepting the awareness of environmental protection and Occupational Health and Worker Safety issues as the first step of its works in every stage of its activity.

"Sustainable environment", "safe working environment", "keeping people in the forefront" are mottos that determine our road map under the changing needs, evolving technologies, challenging competition conditions.

With all legal requirements in mind, we carry out our production activities, in connection with non-written policies of our facility and our culture but most importantly with the purpose of leaving a livable world for our children, who are the guarantee of our future.



PRODUCTS

Extrusion and Cold Drawing

Extruded Rods

Cold Drawn Rods

Profiles and Bars

Hollow Rods

Cold Drawn Coils

Continuous Casting

Ingots

Billets

Extrusion and Cold Drawing



In our extrusion and cold drawing department, cold drawn rods for efficient machining, extruded rods for hot forging, profiles and bars, hollow bars and cold drawn coils are produced.

Major sectors and areas of use; Construction, automotive, gas, food, health, aviation, electrical, electronics, plumbing, drinking water products, accessories, fasteners. Our products comply with ROHS II and REACH Directives. Our production is carried out within the framework of quality, environment and work safety rules.

We also have compatible production for drinking water applications according to UBA hygienic list and 4MS

Our production is realized in compliance with European Norm (EN) and American Norm (ASTM) as standard

Different norm and alloy demands that come from our customers are examined and produced by the units.

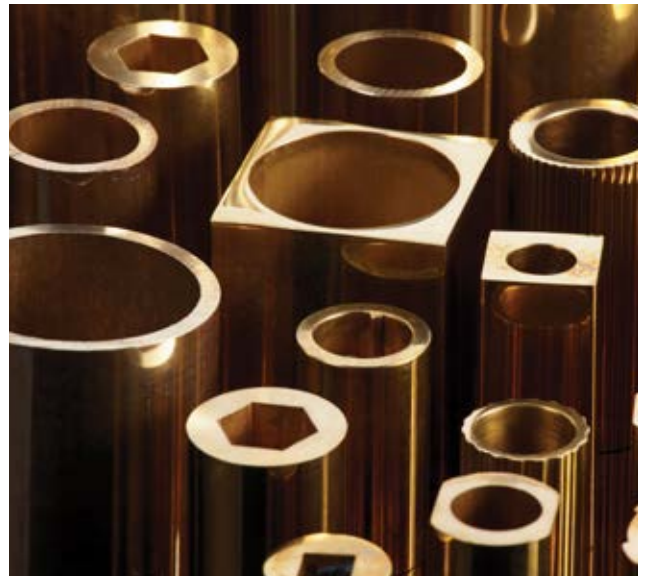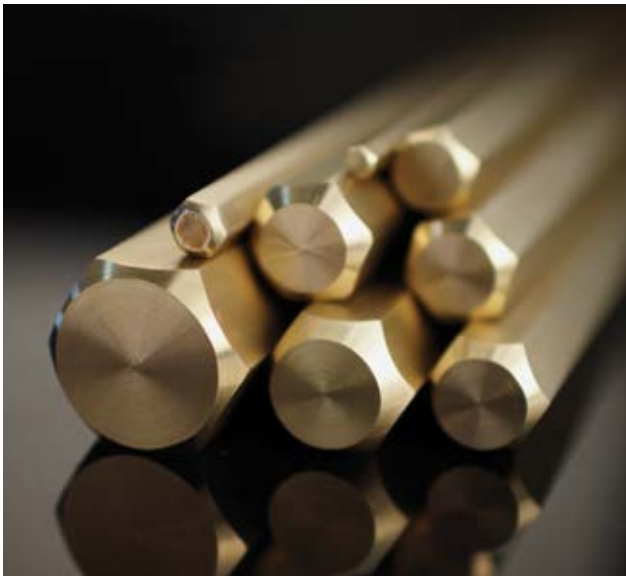

Extruded Rods




Extruded rods are products that manufactured according to EN 12165 European Standard for hot forging processes.

| ALLOYS | | | |
|--------------|------------------|--------|--------|
| Product Code | EN Sembol | EN No | ASTM |
| Ecobrass | CuZn21Si3P | CW724R | C69300 |
| S509-S509DW | CuZn40 | CW509L | C27450 |
| S510-S510DW | CuZn42 | CW510L | C28500 |
| S511-S511DW | CuZn38As | DW511L | C27453 |
| S614-S614DW | CuZn39Pb3 | CW614N | C38500 |
| S617-S617DW | CuZn40Pb2 | CW617N | C38000 |
| S602 | CuZn36Pb2As | CW602N | C35330 |
| S625 | CuZn35Pb1,5AlAs | CW625N | - |
| S626 | CuZn33Pb1,5AlAs | CW626N | - |
| S608 | CuZn38Pb2 | CW608N | - |
| S612-S612DW | CuZn39Pb2 | CW612N | C37700 |
| S709 | CuZn32Pb2AsFeSi | CW709R | - |
| S713 | CuZn37Mn3Al2PbSi | CW713R | C67420 |



| TOLERANCES | | | |
|------------------|---------------------|------------|---------|
| Standard | | EN 12165 | |
| Nominal Diameter | | Tolerances | |
| Over | Up to and including | Class A | Class B |
| 5 | 6 | - | - |
| 6 | 10 | ±0,25 | ±0,14 |
| 10 | 13 | ±0,25 | ±0,14 |
| 13 | 18 | ±0,25 | ±0,14 |
| 18 | 20 | ±0,30 | ±0,17 |
| 20 | 23 | ±0,30 | ±0,17 |
| 23 | 26 | ±0,30 | ±0,17 |
| 26 | 30 | ±0,30 | ±0,17 |
| 30 | 50 | ±0,60 | ±0,20 |
| 50 | 55 | ±0,70 | ±0,37 |
| 55 | 65 | ±0,70 | ±0,37 |
| 65 | 80 | ±0,70 | ±0,37 |
| 80 | 120 | ±2 | - |
| 120 | 140 | ±2,5 | - |

PRODUCTION RANGES

| Designation | | | | Cold Drawn | Extruded | Cold Drawn Polygons | Extruded Polygons | | |
|--------------|--|--------|--------|---------------|----------|---------------------|-------------------------|-----|-----|
| Standards | | | | Diameter (mm) | | | Width Across-flats (mm) | | |
| Product Code | EN Symbol | EN No | ASTM | Min | Max | Max | Min | Max | Max |
| S614 | CuZn39Pb3 | CW614N | C38500 | 6 | 80 | 140 | 6 | 55 | 100 |
| S617 | CuZn40Pb2 | CW617N | C38000 | 6 | 80 | 140 | 6 | 55 | 100 |
| S602 | CuZn36Pb2As | CW602N | C35330 | 10 | 80 | 140 | 10 | 55 | 100 |
| S608 | CuZn38Pb2 | CW608N | - | 6 | 80 | 140 | 6 | 55 | 100 |
| S612 | CuZn39Pb2 | CW612N | C37700 | 8 | 80 | 140 | 8 | 55 | 100 |
| S603 | CuZn36Pb3 | CW603N | C36000 | 10 | 80 | 140 | 10 | 55 | 100 |
| Ecobrass | CuZn21Si3P | CW724R | C69300 | 10 | 80 | 140 | 10 | 55 | 100 |
| S509 |  CuZn40 | CW509L | C27450 | 6 | 80 | 140 | 6 | 55 | 100 |
| S510 |  CuZn42 | CW510L | C28500 | 6 | 80 | 140 | 6 | 55 | 100 |
| S511 |  CuZn38As | CW511L | C27453 | 10 | 80 | 140 | 10 | 55 | 100 |
| S625 | CuZn35Pb1,5AlAs | CW625N | - | 10 | 80 | 140 | 10 | 55 | 100 |
| S626 | CuZn33Pb1,5AlAs | CW626N | - | 10 | 80 | 140 | 10 | 55 | 100 |
| S709 | CuZn32Pb2AsFeSi | CW709R | - | 8 | 80 | 140 | 8 | 55 | 100 |
| S713 | CuZn37Mn3Al2PbSi | CW713R | C67420 | 8 | 80 | 140 | 8 | 55 | 100 |

Over than 55 mm polygons and over than 80 mm round rods are produced without straightness process.



Cold Drawn Rods

Cold drawn rods are produced according to EN 12164 European Standard. They are high precision products suitable for efficient chip removal in free machining process.

| ALLOYS | | | |
|--------------|------------------|--------|--------|
| Product Code | EN Symbol | EN No | ASTM |
| Ecobross | CuZn21Si3P | CW724R | C69300 |
| S509-S509DW | CuZn40 | CW509L | C27450 |
| S510-S510DW | CuZn42 | CW510L | C28500 |
| S511-S511DW | CuZn38As | DW511L | C27453 |
| S603-S603DW | CuZn36Pb3 | CW603N | C36000 |
| S614-S614DW | CuZn39Pb3 | CW614N | C38500 |
| S617-S617DW | CuZn40Pb2 | CW617N | C38000 |
| S602 | CuZn36Pb2As | CW602N | C35330 |
| S625 | CuZn35Pb1,5AlAs | CW625N | - |
| S626 | CuZn33Pb1,5AlAs | CW626N | - |
| S608 | CuZn38Pb2 | CW608N | - |
| S612-S612DW | CuZn39Pb2 | CW612N | C37700 |
| S709 | CuZn32Pb2AsFeSi | CW709R | - |
| S713 | CuZn37Mn3Al2PbSi | CW713R | C67420 |

| PRODUCTION RANGES | | | | | | | | | |
|-------------------|------------------|--------|--------|---------------|----------|---------------------|-------------------------|-----|-----|
| Designation | | | | Cold Drawn | Extruded | Cold Drawn Polygons | Extruded Polygons | | |
| Standards | | | | Diameter (mm) | | | Width Across-flats (mm) | | |
| Product Code | EN Symbol | EN No | ASTM | Min | Max | Max | Min | Max | Max |
| S614 | CuZn39Pb3 | CW614N | C38500 | 6 | 80 | 140 | 6 | 55 | 100 |
| S617 | CuZn40Pb2 | CW617N | C38000 | 6 | 80 | 140 | 6 | 55 | 100 |
| S602 | CuZn36Pb2As | CW602N | C35330 | 10 | 80 | 140 | 10 | 55 | 100 |
| S608 | CuZn38Pb2 | CW608N | - | 6 | 80 | 140 | 6 | 55 | 100 |
| S612 | CuZn39Pb2 | CW612N | C37700 | 8 | 80 | 140 | 8 | 55 | 100 |
| S603 | CuZn36Pb3 | CW603N | C36000 | 10 | 80 | 140 | 10 | 55 | 100 |
| Ecobross | CuZn21Si3P | CW724R | C69300 | 10 | 80 | 140 | 10 | 55 | 100 |
| S509 | CuZn40 | CW509L | C27450 | 6 | 80 | 140 | 6 | 55 | 100 |
| S510 | CuZn42 | CW510L | C28500 | 6 | 80 | 140 | 6 | 55 | 100 |
| S511 | CuZn38As | CW511L | C27453 | 10 | 80 | 140 | 10 | 55 | 100 |
| S625 | CuZn35Pb1,5AlAs | CW625N | - | 10 | 80 | 140 | 10 | 55 | 100 |
| S626 | CuZn33Pb1,5AlAs | CW626N | - | 10 | 80 | 140 | 10 | 55 | 100 |
| S709 | CuZn32Pb2AsFeSi | CW709R | - | 8 | 80 | 140 | 8 | 55 | 100 |
| S713 | CuZn37Mn3Al2PbSi | CW713R | C67420 | 8 | 80 | 140 | 8 | 55 | 100 |

Over than 55 mm polygons and over than 80 mm round rods are produced without straightness process.


TOLERANCES

| Standard | | EN 12164 | | | |
|--|---------------------|-------------|-------------|------------------------|--|
| Nominal Diameter and Width Across- flats | | Round Rod | | Hexagonal, Square Rods | |
| Over | Up to and including | Class A | Class B | Rod | |
| 5 | 6 | 0 -0,05 | 0 -0,03 | 0 -0,08 | |
| 6 | 10 | 0 -0,06 | 0 -0,036 | 0 -0,09 | |
| 10 | 13 | 0 -0,07 | 0 -0,043 | 0 -0,11 | |
| 13 | 18 | 0 -0,07 | 0 -0,043 | 0 -0,11 | |
| 18 | 20 | 0 -0,08 | 0 -0,52 | 0 -0,013 | |
| 20 | 23 | 0 -0,08 | 0 -0,52 | 0 -0,013 | |
| 23 | 26 | 0 -0,08 | 0 -0,52 | 0 -0,013 | |
| 26 | 30 | 0 -0,08 | 0 -0,52 | 0 -0,013 | |
| 30 | 50 | 0 -0,16 | - | 0 -0,016 | |
| 50 | 55 | 0 -0,019 | - | 0 -0,019 | |
| 55 | 65 | 0 -0,19 | - | - | |
| 65 | 80 | 0 -0,19 | - | - | |



INDICATIVE SHAPED ENDS DIMENSIONS

| Nominal Diameter or Width Across-flats | | Type A-Chamfer Length (L) | | Type B-Point Length (L) | |
|--|---------------------|---------------------------|-----|-------------------------|-----|
| Over | Up to and including | Min | Max | Min | Max |
| 5 | 10 | 0,2 | 1,5 | 2 | 7 |
| 10 | 20 | 0,2 | 2 | 3 | 10 |
| 20 | 30 | 0,2 | 3 | 4 | 12 |

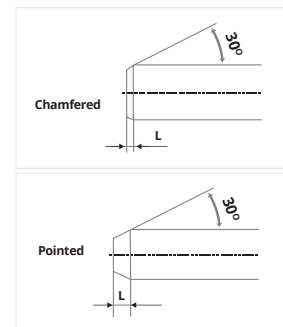

Unless otherwise specified by the buyer, the shape of the ends of products larger than 30 mm is up to the supplier.

Over than 55 mm polygons and over than 65 mm round rods are produced without shaped ends.

*Dimensions are in millimeters (mm).

Profiles and Bars

Profiles and Bars are produced according to customer requirements in special sizes and forms with many years of production experience according to EN 12167 European standard.

Production for profiles and bars is divided into two parts as extruded or cold drawn according to the required dimensional tolerances and mechanical properties.

| ALLOYS | | | |
|--------------|------------------|--------|--------|
| Product Code | EN Symbol | EN No | ASTM |
| Ecobrass | CuZn21Si3P | CW724R | C69300 |
| S509-S509DW | CuZn40 | CW509L | C27450 |
| S510-S510DW | CuZn42 | CW510L | C28500 |
| S511-S511DW | CuZn38As | DW511L | C27453 |
| S603-S603DW | CuZn36Pb3 | CW603N | C36000 |
| S614-S614DW | CuZn39Pb3 | CW614N | C38500 |
| S617-S617DW | CuZn40Pb2 | CW617N | C38000 |
| S602 | CuZn36Pb2As | CW602N | C35330 |
| S625 | CuZn35Pb1,5AlAs | CW625N | - |
| S626 | CuZn33Pb1,5AlAs | CW626N | - |
| S608 | CuZn38Pb2 | CW608N | - |
| S612-S612DW | CuZn39Pb2 | CW612N | C37700 |
| S709 | CuZn32Pb2AsFeSi | CW709R | - |
| S713 | CuZn37Mn3Al2PbSi | CW713R | C67420 |

| EN 12167 - TOLERANCES ON WIDTH AND THICKNESS OF BAR | | | | | | | |
|---|----------------|--------------------|---|-------------------------------|--------------------------------|--------------------------------|--------------------------------|
| Nominal Width | | Tolerance on Width | Tolerance on Thickness for Range of Thickness | | | | |
| Over | Up to and inc. | | Over 5 up to and including 6 | Over 6 up to and including 10 | Over 10 up to and including 18 | Over 18 up to and including 30 | Over 30 up to and including 50 |
| 6 ^{inc.} | 18 | ±0,10 | ±0,07 | ±0,09 | ±0,10 | - | - |
| 18 | 30 | ±0,15 | ±0,07 | ±0,09 | ±0,10 | ±0,15 | - |
| 30 | 50 | ±0,20 | ±0,09 | ±0,10 | ±0,12 | ±0,15 | ±0,20 |
| 50 | 70 | ±0,25 | ±0,11 | ±0,12 | ±0,15 | ±0,20 | ±0,25 |



AVAILABLE RECTANGULAR MEASURES

| Size (mm) | Weight (kg/m) | Size (mm) | Weight (kg/m) | Size (mm) | Weight (kg/m) | Size (mm) | Weight (kg/m) |
|--------------|---------------|---------------|---------------|---------------|---------------|--------------|---------------|
| 8 x 6 | 0,403 | 23 x 8 | 1,546 | 32 x 12 | 3,226 | 45 x 20 | 7,560 |
| 9 x 6,5 | 0,491 | 23 x 10 | 1,932 | 32 x 18 | 4,838 | 45 x 25 | 9,450 |
| 9,28 x 7,6 | 0,592 | 25 x 6 | 1,260 | 33 x 9 | 2,495 | 46 x 16 | 6,182 |
| 10 x 6 | 0,504 | 25 x 8 | 1,680 | 33,5 x 10 | 2,814 | 46 x 26 | 10,046 |
| 10 x 8 | 0,672 | 25 x 10 | 2,100 | 35 x 8 | 2,352 | 50 x 8 | 3,360 |
| 10,8 x 9,8 | 0,889 | 25 x 12 | 2,520 | 35 x 10 | 2,940 | 50 x 10 | 4,200 |
| 12 x 6,5 | 0,655 | 25 x 15 | 3,150 | 35 x 12 | 3,528 | 50 x 12 | 5,040 |
| 12 x 8 | 0,806 | 25 x 20 | 4,200 | 35R1 x 18R1 | 5,292 | 50 x 15 | 6,300 |
| 12 x 10 | 1,008 | 25,4 x 9,53 | 2,033 | 35 x 15 | 4,410 | 50 x 20 | 8,400 |
| 12,7 x 9,53 | 1,017 | 25,4 x 12,7 | 2,710 | 35 x 20 | 5,880 | 50 x 25 | 10,500 |
| 14 x 10 | 1,176 | 25,4 x 15,88 | 3,388 | 35 x 25 | 7,350 | 50 x 30 | 12,600 |
| 14 x 12,5 | 1,470 | 25,4 x 19,05 | 4,065 | 37 x 20 | 6,216 | 50 x 35 | 14,700 |
| 14,6 x 5,8 | 0,711 | 26 x 22 | 4,805 | 38 x 15,86 | 5,063 | 50 x 40 | 16,800 |
| 15 x 8 | 1,008 | 28 x 6 | 1,411 | 38,1 x 19,05 | 6,097 | 50,8 x 19,05 | 8,129 |
| 15 x 10 | 1,260 | 28,6 x 12,68 | 3,046 | 40 x 8 | 2,688 | 50,8 x 22,23 | 9,486 |
| 15 x 12 | 1,512 | 30 x 8 | 2,016 | 40 x 10 | 3,360 | 50,8 x 25,4 | 10,839 |
| 17 x 12 | 1,714 | 30 x 10 | 2,520 | 40 x 12 | 4,032 | 60 x 8 | 4,032 |
| 17,8 x 12,6 | 1,884 | 30 x 12 | 3,024 | 40 x 15 | 5,040 | 60 x 9 | 4,536 |
| 19 x 16 | 2,554 | 30 x 15 | 3,780 | 40 x 20 | 6,720 | 60 x 10 | 5,040 |
| 19,05 x 9,53 | 1,525 | 30 x 20 | 5,040 | 40 x 25 | 8,400 | 60 x 12 | 6,048 |
| 19,05 x 12,7 | 2,032 | 30 x 20,2 | 5,090 | 40 x 30 | 10,080 | 60 x 15 | 7,560 |
| 19,7 x 9,7 | 1,605 | 30 x 25 | 6,300 | 44,45 x 19,05 | 7,113 | 60 x 20 | 10,080 |
| 20 x 8 | 1,344 | 30 x 28 | 7,056 | 45 x 8 | 3,024 | 60 x 25 | 12,600 |
| 20 x 10 | 1,680 | 31,75 x 15,88 | 4,235 | 45 x 10 | 3,780 | 60 x 30 | 15,120 |
| 20 x 12 | 2,016 | 32 x 8 | 2,150 | 45 x 12 | 4,536 | 60 x 40 | 20,160 |
| 20 x 15 | 2,520 | 32 x 8,32 | 2,236 | 45 x 15 | 5,670 | 70 x 20 | 11,760 |




Hollow Rods

Hollow Rods are produced according to EN 12168 European Standard.

It is able to less tool wear, less material consumption and metal loss by decreasing drilling and processing costs to the lowest.

Stress relieving process is an indispensable part of hollow rod production. After the hollow rod production stress relieving process is applied as a standard process.

| ALLOYS | | | |
|--------------|-----------------|--------|--------|
| Product Code | EN Symbol | EN No | ASTM |
| Ecobrass | CuZn21Si3P | CW724R | C69300 |
| S509-S509DW | CuZn40 | CW509L | C27450 |
| S510-S510DW | CuZn42 | CW510L | C28500 |
| S511-S511DW | CuZn38As | DW511L | C27453 |
| S603-S603DW | CuZn36Pb3 | CW603N | C36000 |
| S614-S614DW | CuZn39Pb3 | CW614N | C38500 |
| S617-S617DW | CuZn40Pb2 | CW617N | C38000 |
| S602 | CuZn36Pb2As | CW602N | C35330 |
| S625 | CuZn35Pb1,5AlAs | CW625N | - |


| PRODUCTION RANGES | | | | | | | | | | | | | |
|-------------------|--|--------|--------|------------------------|-----|----------|-------------------------|-----|-------------------|------------------------|-----|---------------------|-----|
| Designation | | | | Cold Drawn | | Extruded | Cold Drawn Polygons | | Extruded Polygons | Round and Polygons | | | |
| Standards | | | | External Diameter (mm) | | | Width Across-flats (mm) | | | Internal Diameter (mm) | | Wall Thickness (mm) | |
| Product Code | EN Symbol | EN No | ASTM | Min | Max | Max | Min | Max | Max | Min | Max | Min | Max |
| S614 | CuZn39Pb3 | CW614N | C38500 | 23 | 80 | 80 | 22 | 74 | 77 | 13 | 59 | 3 | 25 |
| S617 | CuZn40Pb2 | CW617N | C38000 | 23 | 80 | 80 | 22 | 74 | 77 | 13 | 59 | 3 | 25 |
| S602 | CuZn36Pb2As | CW602N | C35330 | 23 | 80 | 80 | 22 | 74 | 77 | 13 | 59 | 4 | 25 |
| S608 | CuZn38Pb2 | CW608N | - | 23 | 80 | 80 | 22 | 74 | 77 | 13 | 59 | 4 | 25 |
| S612 | CuZn39Pb2 | CW612N | C37700 | 23 | 80 | 80 | 22 | 74 | 77 | 13 | 59 | 4 | 25 |
| S603 | CuZn36Pb3 | CW603N | C36000 | 23 | 80 | 80 | 22 | 74 | 77 | 13 | 59 | 4 | 25 |
| Ecobrass | CuZn21Si3P | CW724R | C69300 | 23 | 80 | 80 | 22 | 74 | 77 | 13 | 59 | 4 | 25 |
| S509 |  CuZn40 | CW509L | C27450 | 23 | 80 | 80 | 22 | 74 | 77 | 13 | 59 | 3 | 25 |
| S510 | CuZn42 | CW510L | C28500 | 23 | 80 | 80 | 22 | 74 | 77 | 13 | 59 | 3 | 25 |
| S511 | CuZn38As | CW511L | C27453 | 23 | 80 | 80 | 22 | 74 | 77 | 13 | 59 | 4 | 25 |
| S625 | CuZn35Pb1,5AlAs | CW625N | - | 23 | 80 | 80 | 22 | 74 | 77 | 13 | 59 | 4 | 25 |
| S626 | CuZn33Pb1,5AlAs | CW626N | - | 23 | 80 | 80 | 22 | 74 | 77 | 13 | 59 | 4 | 25 |

Over than 55 mm polygons and over than 80 mm round rods are produced without straightness process.

| STANDARD | | EN 12168 | | | | | |
|---|----------------|--|------------|------------|-------------------------|---------|---------------------------|
| Nominal External Diameter or Width Across-flats | | Tolerances on Diameter or Width Across-flats | | | Tolerance on Hole Round | | Tolerance on Hole Hexagon |
| Over | Up to and inc. | Class A | Class B | Class C | Class A | Class B | - |
| 5 | 6 | - | - | - | - | - | - |
| 6 | 10 | - | - | - | - | - | - |
| 10 | 13 | - | - | - | - | - | - |
| 13 | 18 | - | - | - | ±0,35 | - | +0,70 -0 |
| 18 | 20 | - | - | - | ±0,42 | - | +0,84 -0 |
| 20 | 23 | - | - | - | ±0,42 | ±0,17 | +0,84 -0 |
| 23 | 26 | - | 0 -0,21 | - | ±0,42 | ±0,17 | +0,84 -0 |
| 26 | 30 | - | 0 -0,21 | 0 -0,13 | ±0,42 | ±0,17 | +0,84 -0 |
| 30 | 50 | - | 0 -0,25 | 0 -0,16 | ±0,80 | ±0,20 | +1,6 -0 |
| 50 | 55 | - | 0 -0,46 | 0 -0,30 | ±0,95 | ±0,37 | - |
| 55 | 65 | ±0,60 | 0 -0,46 | 0 -0,30 | ±0,95 | - | - |
| 65 | 80 | ±0,60 | 0 -0,46 | 0 -0,30 | ±0,95 | - | - |

INDICATIVE SHAPED ENDS DIMENSIONS

| Nominal Diameter or Width Across-flats | | Type A-Chamfer Length (L) | | Type B-Point Length (L) | |
|--|---------------------|---------------------------|-----|-------------------------|-----|
| Over | Up to and including | Min | Max | Min | Max |
| 5 | 10 | 0,2 | 1,5 | 2 | 7 |
| 10 | 20 | 0,2 | 2 | 3 | 10 |
| 20 | 30 | 0,2 | 3 | 4 | 12 |

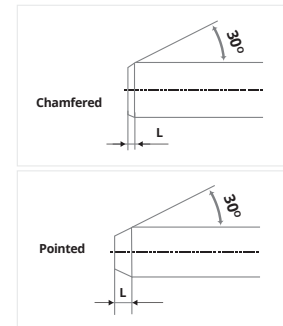


Unless otherwise specified by the buyer, the shape of the ends of products larger than 30 mm is up to the supplier.

Over than 55 mm polygons and over than 65 mm round rods are produced without shaped ends.

*Dimensions are in millimeters (mm).



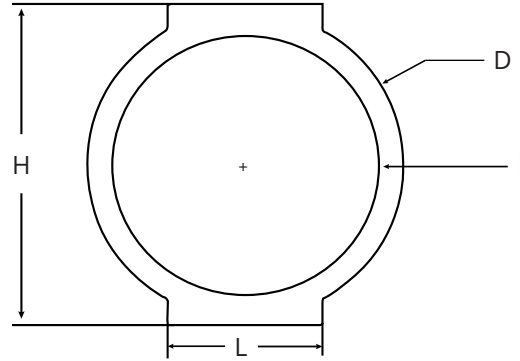

SARBAK METAL MANIFOLD PROFILE DIMENSIONS AND TOLERANCES

| Form Size | 3/4" Normal Manifold | 3/4" Light Manifold | 3/4" Ic Disli Manifold | 35X27 Manifold |
|------------------------|--|--|--|--|
| Alloy | CW614N | CW614N | CW614N | CW614N |
| Top (L1) | 24 ^{+0,05 /} _{-0,20} | 18 ^{+0,05 /} _{-0,20} | 16 ^{+0,05 /} _{-0,20} | 27 ^{+0,20 /} ₋₀ |
| Bottom (L2) | 24 ^{+0,05 /} _{-0,20} | 18 ^{+0,05 /} _{-0,20} | 24 ^{+0,05 /} _{-0,20} | 27 ^{+0,20 /} ₋₀ |
| Height (H) | 35 ^{+0,10 /} _{-0,35} | 32 ^{+0,10 /} _{-0,35} | 35 ^{+0,10 /} _{-0,35} | 35 ^{+0,10 /} _{-0,35} |
| Outer Dia (D) | 31 ±0,20 | 30 ±0,20 | 31 ±0,20 | 32 ±0,20 |
| Inner Dia (I) | 24,4 ±0,20 | 24 ±0,20 | 24 ±0,20 | 23 ±0,20 |
| Weight(Kg / m) | 3,92 | 2,73 | 3,66 | 4,94 |
| Eccentricity (Max) | 10% | 10% | 13% | 10% |

| Form Size | 1" Normal Manifold | 1" B Manifold | 1" Light Manifold | 1" Ic Disli Manifold |
|------------------------|--|--|--|--|
| Alloy | CW614N | CW614N | CW603N | CW614N |
| Top (L1) | 24 ^{+0,05 /} _{-0,20} | 24 ^{+0,05 /} _{-0,20} | 18 ^{+0,10 /} _{-0,20} | 18 ^{+0,05 /} _{-0,20} |
| Bottom (L2) | 24 ^{+0,05 /} _{-0,20} | 24 ^{+0,05 /} _{-0,20} | 18 ^{+0,10 /} _{-0,20} | 21 ^{+0,05 /} _{-0,20} |
| Height (H) | 41 ^{+0,10 /} _{-0,35} | 41 ^{+0,10 /} _{-0,35} | 38 ^{+0,10 /} _{-0,35} | 40,1 ^{+0,10} |
| Outer Dia (D) | 37,5 ±0,20 | 36,5 ±0,20 | 37 ±0,20 | 37,15 ±0,20 |
| Inner Dia (I) | 30,5 ±0,20 | 30,5 ±0,20 | 30,5 ±0,20 | 30 ±0,20 |
| Weight(Kg / m) | 4,40 | 4,13 | 3,31 | 3,95 |
| Eccentricity (Max) | 10% | 10% | 10% | 13% |

| Form Size | 1"KL6 Manifold | 1" Dis Disli Manifold | 1" Disi Manifold | 1" Ic Disli Manifold |
|------------------------|--|--|--|--|
| Alloy | CW614N | CW614N | CW614N | CW614N |
| Top (L1) | 16 ^{+0,05 /} _{-0,20} | 16 ^{+0,05 /} _{-0,20} | 16 ^{+0,05 /} _{-0,20} | 16 ^{+0,05 /} _{-0,20} |
| Bottom (L2) | 24 ^{+0,05 /} _{-0,20} | 24 ^{+0,05 /} _{-0,20} | 24 ^{+0,05 /} _{-0,20} | 24 ^{+0,05 /} _{-0,20} |
| Height (H) | 39 ^{+0,10 /} _{-0,35} | 37 ^{+0,10 /} _{-0,35} | 40,5 ^{+0,10 /} _{-0,35} | 40 ^{+0,10 /} _{-0,35} |
| Outer Dia (D) | 37 ±0,20 | 34 ±0,20 | 37,5 ±0,20 | 36,5 ±0,20 |
| Inner Dia (I) | 30,5 ±0,20 | 27 ±0,20 | 30 ±0,20 | 30 ±0,20 |
| Weight(Kg / m) | 3,59 | 3,72 | 4,20 | 3,81 |
| Eccentricity (Max) | 13% | 13% | 13% | 13% |

SARBAK METAL MANIFOLD PROFILE DIMENSIONS AND TOLERANCES

| Form Size | 1" Elight Manifold | 1 1/4" Normal Manifold | 1 1/4" Light Manifold |
|------------------------|--------------------------------------|---------------------------------------|---------------------------------------|
| Alloy | CW614N | CW614N | CW614N |
| Top (L1) | 25,3 ^{+0/} _{-0,30} | 24 ^{+0,05/} _{-0,20} | 18 ^{+0,05/} _{-0,20} |
| Bottom (L2) | 25,3 ^{+0/} _{-0,30} | 24 ^{+0,05/} _{-0,20} | 18 ^{+0,05/} _{-0,20} |
| Height (H) | 39 ^{+0,20} | 51 ^{+0,10/} _{-0,35} | 48 ^{+0,10/} _{-0,35} |
| Outer Dia (D) | 37 ±0,20 | 47 ±0,20 | 46 ±0,20 |
| Inner Dia (I) | 30,6 ±0,20 | 39 ±0,20 | 39,5 ±0,20 |
| Weight(Kg / m) | 3,94 | 5,77 | 4,15 |
| Eccentricity (Max) | 10% | 10% | 10% |

| Form Size | 1 1/4" Icten Disli Manifold | 1 1/2" Manifold | 1" 20x20 Manifold |
|------------------------|---------------------------------------|---------------------------------------|---------------------------------------|
| Alloy | CW614N | CW614N | CW603N |
| Top (L1) | 18 ^{+0,05/} _{-0,20} | 25 ^{+0,05/} _{-0,20} | 20 ^{+0,05/} _{-0,20} |
| Bottom (L2) | 21 ^{+0,05/} _{-0,20} | 25 ^{+0,05/} _{-0,20} | 20 ^{+0,05/} _{-0,20} |
| Height (H) | 50 ^{+0,10/} _{-0,35} | 57 ^{+0,10/} _{-0,35} | 38 ^{+0,10/} _{-0,35} |
| Outer Dia (D) | 46 ±0,20 | 53,2 ±0,20 | 37 ±0,20 |
| Inner Dia (I) | 39 ±0,20 | 44,8 ^{+0/-0,4} | 30,8 ±0,20 |
| Weight(Kg / m) | 4,82 | 6,65 | 3,30 |
| Eccentricity (Max) | 10% | 10% | 10% |

| Form Size | S19 Manifold | S20 Manifold | S21 Manifold |
|------------------------|---------------------------------------|---|---|
| Alloy | CW603N | CW603N | CW603N |
| Top (L1) | 24 ^{+0,10/} _{-0,20} | 2 ^{+0,10/} _{-0,20} | 24 ^{+0,10/} _{-0,20} |
| Bottom (L2) | 24 ^{+0,10/} _{-0,20} | 24 ^{+0,10/} _{-0,20} | 24 ^{+0,10/} _{-0,20} |
| Height (H) | 3 ^{+0,10/} _{-0,35} | 30,5 ^{+0,10/} _{-0,35} | 46,5 ^{+0,10/} _{-0,35} |
| Outer Dia (D) | 37 ±0,20 | 30 ±0,20 | 46 ±0,20 |
| Inner Dia (I) | 30,8 ±0,20 | 24,4 ±0,20 | 39,5 ±0,20 |
| Weight(Kg / m) | 3,24 | 2,87 | 4,26 |
| Eccentricity (Max) | 10% | 10% | 10% |

Cold Drawn Coils

Cold drawn coils are produced according to EN 12166 European Standard. They are coil shaped high precision products suitable for efficient chip removal in free machining process.

They increase production speed and productivity by reducing the loading times of machines.

| ALLOYS | | | |
|--------------|-----------------|--------|--------|
| Product Code | EN Symbol | EN No | ASTM |
| S511-S511DW | CuZn38As | DW511L | C27453 |
| S603-S603DW | CuZn36Pb3 | CW603N | C36000 |
| S614-S614DW | CuZn39Pb3 | CW614N | C38500 |
| S617-S617DW | CuZn40Pb2 | CW617N | C38000 |
| S602 | CuZn36Pb2As | CW602N | C35330 |
| S625 | CuZn35Pb1,5AlAs | CW625N | - |
| S626 | CuZn33Pb1,5AlAs | CW626N | - |
| S608 | CuZn38Pb2 | CW608N | - |
| S612-S612DW | CuZn39Pb2 | CW612N | C37700 |

PRODUCTION RANGES



| Type | Production Range |
|-----------------|--|
| Round | 5-14 (mm) |
| Hexagon, Square | 5-12 (mm) |
| Rectangle | Thickness : 5-10 (mm) Width : 5-20 (mm) |

EN 12166 - Tolerances on Diameter of Round Coils

| Nominal Diameter | | Tolerances | | | | |
|---------------------|---------------------|------------|------------|------------|------------|-------------|
| Over | Up to and including | Class A | Class B | Class C | Class D | Class E |
| 4,8 ^{Inc.} | 6,0 | ±0,04 | 0 -0,12 | 0 -0,08 | 0 -0,05 | 0 -0,030 |
| 6,0 | 10,0 | ±0,06 | 0 -0,15 | 0 -0,09 | 0 -0,06 | 0 -0,036 |
| 10,0 | 14,0 | ±0 08 | 0 -0,18 | 0 -0,11 | 0 -0,07 | 0 -0,043 |

EN 12166 - Tolerances on Width Across-Flats of Square or Regular Polygonal Coils

| Nominal Width Across-flats | | Tolerances | | |
|----------------------------|---------------------|------------|------------|------------|
| Over | Up to and including | Class A | Class B | Class C |
| 5,0 ^{inc.} | 6,0 | ±0,06 | 0 -0,12 | 0 -0,08 |
| 6,0 | 10,0 | ±0,08 | 0 -0,15 | 0 -0,09 |
| 10,0 | 12,0 | ±0,10 | 0 -0,18 | 0 -0,11 |

EN 12166 - Tolerances on Width and Thickness of Rectangular Wire Coils

| Nominal Width Across-flats | | Tolerance on Width | Tolerances | | |
|----------------------------|----------------|--------------------|----------------------------------|-----------------------------------|------------------------------------|
| Over | Up to and inc. | | over 5,0 up to and including 6,0 | over 6,0 up to and including 10,0 | over 10,0 up to and including 12,0 |
| 5,0 ^{inc.} | 6,0 | ±0,06 | ±0,06 | - | - |
| 6,0 | 10,0 | ±0,08 | ±0,07 | ±0,08 | - |
| 10,0 | 12,0 | ±0,10 | ±0,07 | ±0,09 | ±0,10 |




Continuous Casting

Our continuous casting production is composed of casting of billets and ingots.

Major sectors and areas of use; construction, automotive, gas, food, health, aviation, electrical, electronics, plumbing, drinking water products, accessories, fasteners.

Our products comply with ROHS II and REACH Directives. Our manufacturing is realized within the framework of quality, environment and work safety rules.

We also have 4MS and UBA compatible production for drinking water implementations. As a standard our production is carried out according to European Norm (EN) and American Standard (ASTM). Different norm and alloy demands that come from our customers are examined and produced by the relevant units.

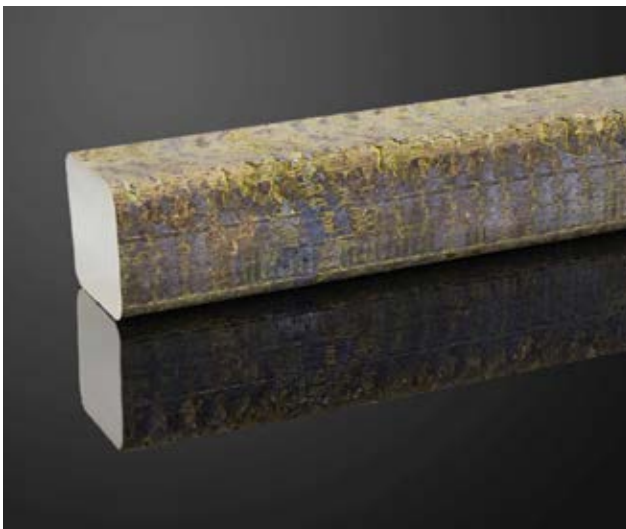

Ingots

In our ingot production process, production is carried out by horizontal continuous casting system. Our company is a member of OECAM (The Organization of European Copper Alloy Ingot Makers).

| ALLOYS | | | |
|---|---------------|--------|--------|
| Product Code | EN Symbol | EN No | ASTM |
| Low Pressure Continuous Casting Ingots | CuZn39Pb1Al-C | CC757S | C85700 |
| Dezincification - Resistant (DZR) Continuous Casting Ingots | CuZn36Pb-C | CC770S | - |
| Dezincification - Resistant (DZR) Continuous Casting Ingots | CuZn35Al-C | - | - |
| Dezincification - Resistant (DZR) Continuous Casting Ingots | CuZn38AsSb-C | CC771S | - |
| Ecocast Unleaded Continuous Casting Ingots | CuZn21Si3P-C | CC768S | C87850 |
| FEDERALLOY IV-B2 | - | - | C89540 |
| Unleaded Continuous Casting Ingots | CuZn42Al-C | CC773S | - |

| STANDARD DIMENSIONS - WEIGHT | |
|------------------------------|----------------------|
| Standard Dimensions (mm) | Standard Weight (kg) |
| 64x64x380 | Average 12 |



Billets

The homogeneous, uniformly shaped billets produced in 7 horizontal continuous casting lines with a capacity of 300 tons / day can be produced in desired sizes up to 140 mm from to 240 mm diameter.

| ALLOYS | | | |
|--------------|------------------|--------|--------|
| Product Code | EN Symbol | EN No | ASTM |
| Ecobrass | CuZn21Si3P | CW724R | C69300 |
| S509-S509DW | CuZn40 | CW509L | C27450 |
| S510-S510DW | CuZn42 | CW510L | C28500 |
| S511-S511DW | CuZn38As | DW511L | C27453 |
| S603-S603DW | CuZn36Pb3 | CW603N | C36000 |
| S614-S614DW | CuZn39Pb3 | CW614N | C38500 |
| S617-S617DW | CuZn40Pb2 | CW617N | C38000 |
| S602 | CuZn36Pb2As | CW602N | C35330 |
| S625 | CuZn35Pb1,5AlAs | CW625N | - |
| S626 | CuZn33Pb1,5AlAs | CW626N | - |
| S608 | CuZn38Pb2 | CW608N | - |
| S612-S612DW | CuZn39Pb2 | CW612N | C37700 |
| S709 | CuZn32Pb2AsFeSi | CW709R | - |
| S713 | CuZn37Mn3Al2PbSi | CW713R | C67420 |





ALLOYS

| ROD | HOLLOW RODS | COILS | INGOTS |
|---------|------------------|-------|--|
| S612 | S625 | S602 | LOW PRESSURE CONTINUOUS CASTING INGOTS |
| S614 | S608 | S511 | DEZINCIFICATION - RESISTANT (DZR) CONTINUOUS CASTING INGOTS |
| S617 | S603 | S510 | UNLEADED CONTINUOUS CASTING INGOTS |
| ECOBASS | S626 | S509 | ECOBASS - ECOCAST CONTINUOUS CASTING (PATENTED) |
| | | | FEDERALLOY IV - B2 - UNLEADED CONTINUOUS CASTING INGOTS (PATENTED) |

S612 - S612DW

RODS / HOLLOW RODS

CW612N - CuZn39Pb2

| Product Code | EN Symbol | EN No | ASTM | | Cu | Zn | Pb | Sn | Fe | Ni | Al | Si | Others Total |
|--------------|--------------|-----------|--------|---------|------|------|-----|-----|-----|-----|------|------|--------------|
| S612 | CuZn39Pb2 | CW612N | C37700 | Min (%) | 59,0 | Rem. | 1,6 | - | - | - | - | - | - |
| | | | | Max (%) | 60,0 | Rem. | 2,5 | 0,3 | 0,3 | 0,3 | 0,05 | - | 0,2 |
| (*) S612DW | CuZn39Pb2-DW | CW612N-DW | C37700 | Min (%) | 59,0 | Rem. | 1,6 | - | - | - | - | - | - |
| | | | | Max (%) | 60,0 | Rem. | 2,2 | 0,3 | 0,3 | 0,1 | 0,05 | 0,03 | 0,2 |

(*) Each of the other elements < 0,02 %

Features And Applications

It is an alloy with excellent hot forging features due to high copper content, and very good machinability with lead content. It has good ductility Also this alloy compliance with RoHS II and REACH directives. CW612N-DW alloy be used suitable for 4MS vs UBA list for drinking water applications.

4MS and UBA Hygienic list group for CW612N-DW alloy: B, C, D

Area of Usage

Automotive, electrical components, screws, clamps .

TECHNICAL SPECIFICATIONS

| | | | |
|-----------------------------|--------------------------|-----------------------|------------|
| Structure | $\alpha+\beta$ | Hot Forming | 650-800 °C |
| Machinability | % 90 | Soft Annealing | 450-600 °C |
| Density | 8,44 g/cm ³ | Soft Annealing Time | 1-3 hours |
| Electrical Conductivity | 13,9 MS/m, 24 %IACS | Stress Relieving | 200-300 °C |
| Thermal Conductivity | 109 W/(m·K) | Stress Relieving Time | 1-3 hours |
| Elasticity Module | 102 GPa | | |
| Coeff. of Thermal Expansion | 21,1 10 ⁻⁶ /K | | |
| Melting Point | 880-895 °C | | |


Range of Products

S612 and S612-DW alloys can be produced in our extrusion and cold drawing unit as rods, hollows and profiles suitable for both forging and machining. Please contact us for other technical informations.

INDICATIVE SHAPED ENDS DIMENSIONS

| Nominal Diameter or Width | | Type A - Chamfer Length (L) | | Type B - Point Length (L) | |
|---------------------------|---------------------|-----------------------------|----------|---------------------------|----------|
| Across-flats (mm) | | Min (mm) | Max (mm) | Min (mm) | Max (mm) |
| Over | Up to and including | | | | |
| 5 | 10 | 0,2 | 1,5 | 2 | 7 |
| 10 | 20 | 0,2 | 2 | 3 | 10 |
| 20 | 30 | 0,2 | 3 | 4 | 12 |

Unless otherwise specified by the buyer, the shape of the ends of products larger than 30 mm is up to the supplier.

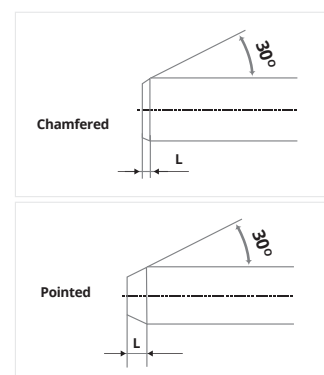

| Nominal Diameter or Width Across-flats (mm) | | Preferred (available) Lengths (mm) | Tolerance on Length (mm) |
|--|---------------------|---------------------------------------|-----------------------------|
| Over | Up to and including | | |
| 8 Inc. | 30 | 3.000 - 4.000 | ±50 |
| 30 | 80 | 3.000 - 4.000 | ±100 |

Stress Relieving The polygonal rods and hollow rods are subjected to stress relieving treatment

Packaging 500 or 1000 kg bundle – 3/5 metal straps different bundle packagings, up to 10 mm dimension products are packed with wooden case

EN 12164 - Rods for Free Machining

| Material Condition | Nominal Diameter (mm) | | Width Across-flats (mm) | | Tensile Strength Rm N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation | | | Hardness (HBW) | |
|--------------------|-----------------------|----------------|-------------------------|----------------|--|--|-----|------------------------|-----------------------|-------|----------------|-----|
| | Over | Up to and inc. | Over | Up to and inc. | | Min | Max | A _{100mm} (%) | A _{11,3} (%) | A (%) | Min | Max |
| M | All | | All | | As manufactured | | | | | | | |
| R360 | 8 | 80 | 8 | 55 | 360 | - | 300 | - | 15 | 20 | - | - |
| H070 | 8 | 80 | 8 | 55 | - | - | - | - | - | - | 70 | 100 |
| R410 | 8 | 40 | 8 | 35 | 410 | 230 | - | 8 | 10 | 12 | - | - |
| H100 | 8 | 40 | 8 | 35 | - | - | - | - | - | - | 100 | 145 |
| R500 | 8 | 14 | 8 | 10 | 500 | 350 | - | 3 | 5 | 8 | - | - |
| H120 | 8 | 14 | 8 | 10 | - | - | - | - | - | - | 120 | - |

EN 12168 - Hollow Rods for Free Machining

| Material Condition | Wall Thickness (mm) | | Tensile Strength Rm N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation A (%) Min | Hardness (HBW) | | Hardness (HV) | |
|--------------------|---------------------|----------------|--|--|-----|-------------------------|----------------|-----|---------------|-----|
| | Over | Up to and inc. | | Min | Max | | Min | Max | Min | Max |
| M | All | | As manufactured | | | | | | | |
| R360 | 4 | 20 | 360 | - | 300 | 20 | - | - | - | - |
| H070 | 4 | 20 | - | - | - | - | 70 | 100 | 80 | 110 |
| R410 | 4 | 10 | 410 | 250 | - | 12 | - | - | - | - |
| H100 | 4 | 10 | - | - | - | - | 100 | 145 | 110 | 155 |
| R500 | 4 | 7 | 500 | 350 | - | 8 | - | - | - | - |
| H120 | 4 | 7 | - | - | - | - | 120 | - | 130 | - |

EN 12165 - Wrought and Unwrought Forging Stocks

| Material Condition | Nominal Diameter (mm) | | Hardness (HBW) | |
|--------------------|-----------------------|---------------------|-----------------|-----|
| | Over | Up to and including | Min | Max |
| M | All | | As manufactured | |
| H070 | 8 | 80 | 70 | 100 |

| STANDARD | | EN 12164 | | | EN 12165 | | EN 12168 | | | | | |
|-----------------|--------------|------------|-------------|-------------------|-----------|---------|---|------------|------------|----------------------|---------|---------------------|
| Dimension Range | | Round Rod | | Hexagonal, Square | Round Rod | | Round and Hexagonal Hollow Rod, Outer Dim. Tol. | | | Hole Tolerance Round | | Hole Tol. Hexagonal |
| Over | Up to & inc. | Class A | Class B | Rod | Class A | Class B | Class A | Class B | Class C | Class A | Class B | - |
| 7 | 10 | 0 -0,06 | 0 -0,036 | 0 -0,09 | ±0,25 | ±0,14 | - | - | - | - | - | - |
| 10 | 13 | 0 -0,07 | 0 -0,043 | 0 -0,11 | ±0,25 | ±0,14 | - | - | - | - | - | - |
| 13 | 18 | 0 -0,07 | 0 -0,043 | 0 -0,11 | ±0,25 | ±0,14 | - | - | - | ±0,35 | - | +0,70 -0 |
| 18 | 20 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | - | - | ±0,42 | - | +0,84 -0 |
| 20 | 23 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | - | - | ±0,42 | ±0,17 | +0,84 -0 |
| 23 | 26 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | 0 -0,21 | - | ±0,42 | ±0,17 | +0,84 -0 |
| 26 | 30 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | 0 -0,21 | 0 -0,13 | ±0,42 | ±0,17 | +0,84 -0 |
| 30 | 50 | 0 -0,16 | - | 0 -0,16 | ±0,60 | ±0,20 | - | 0 -0,25 | 0 -0,16 | ±0,80 | ±0,20 | +1,6 -0 |
| 50 | 55 | 0 -0,19 | - | 0 -0,19 | ±0,70 | ±0,37 | - | 0 -0,46 | 0 -0,30 | ±0,95 | ±0,37 | - |
| 55 | 65 | 0 -0,19 | - | - | ±0,70 | ±0,37 | ±0,60 | 0 -0,46 | 0 -0,30 | ±0,95 | - | - |
| 65 | 80 | 0 -0,19 | - | - | ±0,70 | ±0,37 | ±0,60 | 0 -0,46 | 0 -0,30 | ±0,95 | - | - |
| 80 | 120 | - | - | - | ±2 | - | - | - | - | - | - | - |
| 120 | 140 | - | - | - | ±2,5 | - | - | - | - | - | - | - |

For Hollow Rods

Minimum wall thickness is 4 mm. Eccentricity : %10 (max.)

Outer Cold Drawn - Internal Extruded

Outer Class B - Hole Class A tolerance

Inner-Outer Cold Drawn

Outer Class C - Hole Class B tolerance

Inner-Outer Extruded

Outer Class A - Hole Class A tolerance



S614 - S614DW

RODS / HOLLOW RODS

CW614N - CuZn39Pb3

| Product Code | EN Symbol | EN No | ASTM | | Cu | Zn | Pb | Sn | Fe | Ni | Al | Si | Others Total |
|--------------|--------------|-----------|--------|---------|------|------|-----|-----|-----|-----|------|------|--------------|
| S614 | CuZn39Pb3 | CW614N | C38500 | Min (%) | 57,0 | Rem. | 2,5 | - | - | - | - | - | - |
| | | | | Max (%) | 59,0 | Rem. | 3,5 | 0,3 | 0,3 | 0,3 | 0,05 | - | 0,2 |
| (*) S614DW | CuZn39Pb3-DW | CW614N-DW | C38500 | Min (%) | 57,0 | Rem. | 2,5 | - | - | - | - | - | - |
| | | | | Max (%) | 59,0 | Rem. | 3,5 | 0,3 | 0,3 | 0,2 | 0,05 | 0,03 | 0,2 |

(*) Each of the other elements < 0,02 %

Features And Applications

CW614N called MS58 in the market, is the most widely used standard free machining material with a 100% machinability index. It has got limited hot forming and poor cold forming capability. Also this alloy compliance with RoHS II and REACH directives. CW614N-DW alloy be used suitable for 4MS vs UBA list for drinking water applications.

4MS and UBA Hygienic list group for CW614N-DW alloy: C and D

Area of Usage

General parts produced by machining.

TECHNICAL SPECIFICATIONS

| | | | |
|-----------------------------|--------------------------|-----------------------|------------|
| Structure | $\alpha+\beta$ | Hot Forming | 650-800 °C |
| Machinability | % 100 | Soft Annealing | 450-600 °C |
| Density | 8,46 g/cm ³ | Soft Annealing Time | 1-3 hours |
| Electrical Conductivity | 14,6 MS/m, 25 %IACS | Stress Relieving | 200-300 °C |
| Thermal Conductivity | 113 W/(m·K) | Stress Relieving Time | 1-3 hours |
| Elasticity Module | 96 GPa | | |
| Coeff. of Thermal Expansion | 21,4 10 ⁻⁶ /K | | |
| Melting Point | 880-895 °C | | |



Range of Products

S614 and S614-DW alloys can be produced in our extrusion and cold drawing unit as rods, hollows and profiles suitable for both forging and machining. Please contact us for other technical informations.

INDICATIVE SHAPED ENDS DIMENSIONS

| Nominal Diameter or Width | | Type A - Chamfer Length (L) | | Type B - Point Length (L) | |
|---------------------------|---------------------|-----------------------------|----------|---------------------------|----------|
| Across-flats (mm) | | Min (mm) | Max (mm) | Min (mm) | Max (mm) |
| Over | Up to and including | | | | |
| 5 | 10 | 0,2 | 1,5 | 2 | 7 |
| 10 | 20 | 0,2 | 2 | 3 | 10 |
| 20 | 30 | 0,2 | 3 | 4 | 12 |

Unless otherwise specified by the buyer, the shape of the ends of products larger than 30 mm is up to the supplier.

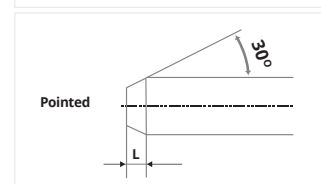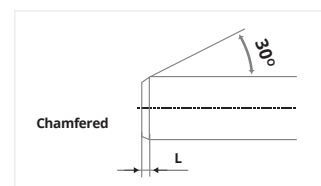

| Nominal Diameter or Width Across-flats (mm) | | Preferred (available) Lengths (mm) | Tolerance on Length (mm) |
|--|---------------------|---------------------------------------|-----------------------------|
| Over | Up to and including | | |
| 5 | 30 | 3.000 - 4.000 | ±50 |
| 30 | 80 | 3.000 - 4.000 | ±100 |

Stress Relieving The polygonal rods and hollow rods are subjected to stress relieving treatment

Packaging 500 or 1000 kg bundle – 3/5 metal straps different bundle packagings, up to 10 mm dimension products are packed with wooden case

EN 12164 - Rods for Free Machining

| Material Condition | Nominal Diameter (mm) | | Width Across-flats (mm) | | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation | | | Hardness (HBW) | |
|-----------------------|-----------------------------|-------------------|-------------------------------|-------------------|---|--|-----|----------------------------------|---------------------------------|-----------------|-------------------|-----|
| | Over | Up to and inc. | Over | Up to and inc. | | Min | Max | A _{100mm} (%) Min | A _{11,3} (%) Min | A (%) Min | Min | Max |
| M | All | | All | | As manufactured | | | | | | | |
| R360 | 6 | 80 | 5 | 55 | 360 | - | 350 | - | 15 | 20 | - | - |
| H090 | 6 | 80 | 5 | 55 | - | - | - | - | - | - | 90 | 125 |
| R430 | 5 | 60 | 5 | 40 | 430 | 220 | - | 6 | 8 | 10 | - | - |
| H110 | 5 | 60 | 5 | 40 | - | - | - | - | - | - | 110 | 160 |
| R500 | 5 | 14 | 5 | 10 | 500 | 350 | - | - | 3 | 5 | - | - |
| H135 | 5 | 14 | 5 | 10 | - | - | - | - | - | - | 135 | - |

EN 12168 - Hollow Rods for Free Machining

| Material Condition | Wall Thickness (mm) | | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation A (%) Min | Hardness (HBW) | | Hardness (HV) | |
|-----------------------|------------------------|-------------------|---|--|-----|-------------------------------|-------------------|-----|------------------|-----|
| | Over | Up to and inc. | | Min | Max | | Min | Max | Min | Max |
| M | All | | As manufactured | | | | | | | |
| R360 | 3 | 40 | 360 | - | 320 | 20 | - | - | - | - |
| H090 | 3 | 40 | - | - | - | - | 90 | 125 | 100 | 135 |
| R430 | 3 | 15 | 430 | 220 | - | 10 | - | - | - | - |
| H110 | 3 | 15 | - | - | - | - | 110 | 160 | 120 | 170 |
| R500 | 3 | 7 | 500 | 350 | - | 8 | - | - | - | - |
| H135 | 3 | 7 | - | - | - | - | 135 | - | 145 | - |

EN 12165 - Wrought and Unwrought Forging Stocks

| Material Condition | Nominal Diameter (mm) | | Hardness (HBW) | |
|-----------------------|--------------------------|---------------------|-------------------|-----|
| | Over | Up to and including | Min | Max |
| M | All | | As manufactured | |
| H080 | 8 | 80 | 80 | 125 |

| STANDARD | | EN 12164 | | | EN 12165 | | EN 12168 | | | | | |
|-----------------|--------------|------------|-------------|-------------------|-----------|---------|---|------------|------------|----------------------|---------|---------------------|
| Dimension Range | | Round Rod | | Hexagonal, Square | Round Rod | | Round and Hexagonal Hollow Rod, Outer Dim. Tol. | | | Hole Tolerance Round | | Hole Tol. Hexagonal |
| | Up to & inc. | Class A | Class B | Rod | Class A | Class B | Class A | Class B | Class C | Class A | Class B | - |
| 5 | 6 | 0 -0,05 | 0 -0,03 | 0 -0,08 | - | - | - | - | - | - | - | - |
| 6 | 10 | 0 -0,06 | 0 -0,036 | 0 -0,09 | ±0,25 | ±0,14 | - | - | - | - | - | - |
| 10 | 13 | 0 -0,07 | 0 -0,043 | 0 -0,11 | ±0,25 | ±0,14 | - | - | - | - | - | - |
| 13 | 18 | 0 -0,07 | 0 -0,043 | 0 -0,11 | ±0,25 | ±0,14 | - | - | - | ±0,35 | - | +0,70 -0 |
| 18 | 20 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | - | - | ±0,42 | - | +0,84 -0 |
| 20 | 23 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | - | - | ±0,42 | ±0,17 | +0,84 -0 |
| 23 | 26 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | 0 -0,21 | - | ±0,42 | ±0,17 | +0,84 -0 |
| 26 | 30 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | 0 -0,21 | 0 -0,13 | ±0,42 | ±0,17 | +0,84 -0 |
| 30 | 50 | 0 -0,16 | - | 0 -0,16 | ±0,60 | ±0,20 | - | 0 -0,25 | 0 -0,16 | ±0,80 | ±0,20 | +1,6 -0 |
| 50 | 55 | 0 -0,19 | - | 0 -0,19 | ±0,70 | ±0,37 | - | 0 -0,46 | 0 -0,30 | ±0,95 | ±0,37 | - |
| 55 | 65 | 0 -0,19 | - | - | ±0,70 | ±0,37 | ±0,60 | 0 -0,46 | 0 -0,30 | ±0,95 | - | - |
| 65 | 80 | 0 -0,19 | - | - | ±0,70 | ±0,37 | ±0,60 | 0 -0,46 | 0 -0,30 | ±0,95 | - | - |
| 80 | 120 | - | - | - | ±2 | - | - | - | - | - | - | - |
| 120 | 140 | - | - | - | ±2,5 | - | - | - | - | - | - | - |

For Hollow Rods

Minimum wall thickness is 3 mm. Eccentricity : %10 (max.)

Outer Cold Drawn - Internal Extruded


Outer Class B - Hole Class A tolerance

Inner-Outer Cold Drawn

Outer Class C - Hole Class B tolerance

Inner-Outer Extruded

Outer Class A - Hole Class A tolerance

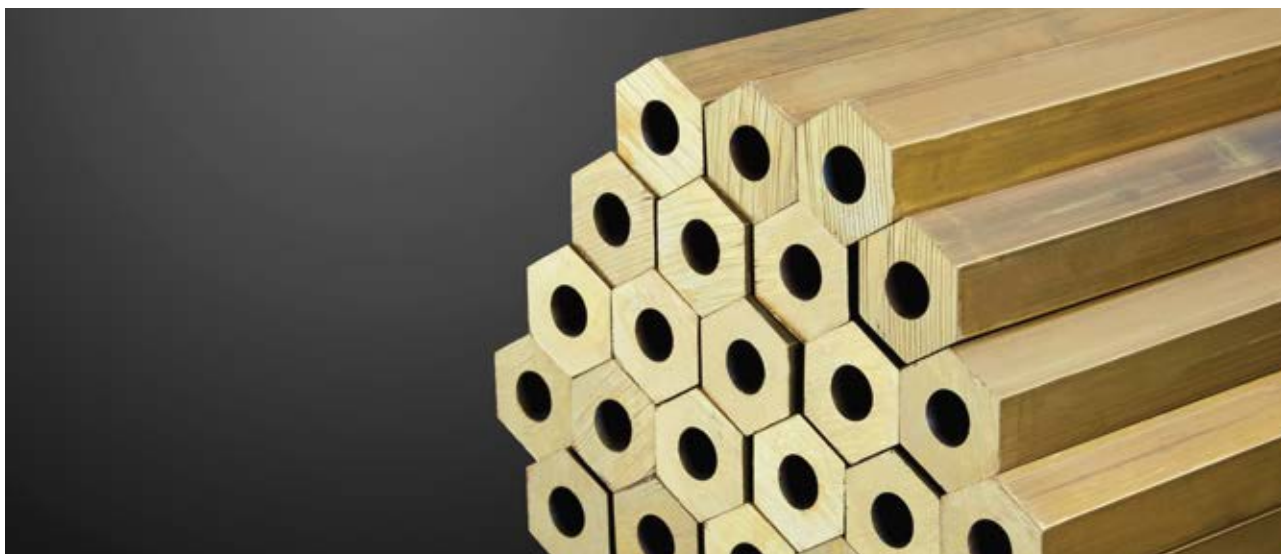

S617 - S617DW

RODS / HOLLOW RODS

CW617N - CuZn40Pb2

| Product Code | EN Symbol | EN No | ASTM | | Cu | Zn | Pb | Sn | Fe | Ni | Al | Si | Others Total |
|--------------|--------------|-----------|--------|---------|------|------|-----|-----|-----|-----|------|------|--------------|
| S617 | CuZn40Pb2 | CW617N | C38000 | Min (%) | 57,0 | Rem. | 1,6 | - | - | - | - | - | - |
| | | | | Max (%) | 59,0 | Rem. | 2,5 | 0,3 | 0,3 | 0,3 | 0,05 | - | 0,2 |
| (*) S617DW | CuZn40Pb2-DW | CW617N-DW | C38000 | Min (%) | 57,0 | Rem. | 1,6 | - | - | - | - | - | - |
| | | | | Max (%) | 59,0 | Rem. | 2,2 | 0,3 | 0,3 | 0,1 | 0,05 | 0,03 | 0,2 |

(*) Each of the other elements < 0,02 %

Features And Applications

CW617N is mainly used standard hot forging material. It has a good machinability capability due to lead content. Also this alloy compliance with RoHS II and REACH directives. CW617N-DW alloy be used suitable for 4MS vs UBA list for drinking water applications.

4MS and UBA Hygienic list group for CW617N-DW alloy: B, C, D

Area of Usage

Hot forging parts.

TECHNICAL SPECIFICATIONS

| | | | |
|-----------------------------|--------------------------|-----------------------|------------|
| Structure | $\alpha+\beta$ | Hot Forming | 650-800 °C |
| Machinability | % 95 | Soft Annealing | 450-600 °C |
| Density | 8,43g/cm ³ | Soft Annealing Time | 1-3 hours |
| Electrical Conductivity | 14,9 MS/m, 25 %IACS | Stress Relieving | 200-300 °C |
| Thermal Conductivity | 113 W/(m·K) | Stress Relieving Time | 1-3 hours |
| Elasticity Module | 96 GPa | | |
| Coeff. of Thermal Expansion | 21,1 10 ⁻⁶ /K | | |
| Melting Point | 880-895 °C | | |


Range of Products

S617 and S617-DW alloys can be produced in our extrusion and cold drawing unit as rods, hollows and profiles suitable for both forging and machining. Please contact us for other technical informations.

INDICATIVE SHAPED ENDS DIMENSIONS

| Nominal Diameter or Width | | Type A - Chamfer Length (L) | | Type B - Point Length (L) | |
|---------------------------|---------------------|-----------------------------|----------|---------------------------|----------|
| Across-flats (mm) | | Min (mm) | Max (mm) | Min (mm) | Max (mm) |
| Over | Up to and including | | | | |
| 5 | 10 | 0,2 | 1,5 | 2 | 7 |
| 10 | 20 | 0,2 | 2 | 3 | 10 |
| 20 | 30 | 0,2 | 3 | 4 | 12 |

Unless otherwise specified by the buyer, the shape of the ends of products larger than 30 mm is up to the supplier.

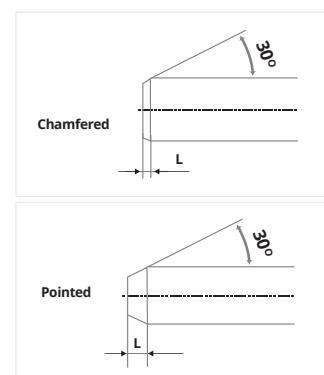

| Nominal Diameter or Width Across-flats (mm) | | Preferred (available) Lengths (mm) | Tolerance on Length (mm) |
|--|---------------------|---------------------------------------|-----------------------------|
| Over | Up to and including | | |
| 5 | 30 | 3.000 - 4.000 | ±50 |
| 30 | 80 | 3.000 - 4.000 | ±100 |

Stress Relieving The polygonal rods and hollow rods are subjected to stress relieving treatment

Packaging 500 or 1000 kg bundle – 3/5 metal straps different bundle packagings, up to 10 mm dimension products are packed with wooden case

EN 12164 - Rods for Free Machining

| Material Condition | Nominal Diameter (mm) | | Width Across-flats (mm) | | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation | | | Hardness (HBW) | |
|-----------------------|-----------------------------|-------------------|-------------------------------|-------------------|---|--|-----|----------------------------------|---------------------------------|-----------------|-------------------|-----|
| | Over | Up to and inc. | Over | Up to and inc. | | Min | Max | A _{100mm} (%) Min | A _{11,3} (%) Min | A (%) Min | Min | Max |
| M | All | | All | | As manufactured | | | | | | | |
| R360 | 6 | 80 | 5 | 55 | 360 | - | 350 | - | 15 | 20 | - | - |
| H090 | 6 | 80 | 5 | 55 | - | - | - | - | - | - | 90 | 125 |
| R430 | 5 | 60 | 5 | 40 | 430 | 220 | - | 6 | 8 | 10 | - | - |
| H110 | 5 | 60 | 5 | 40 | - | - | - | - | - | - | 110 | 160 |
| R500 | 5 | 14 | 5 | 10 | 500 | 350 | - | - | 3 | 5 | - | - |
| H135 | 5 | 14 | 5 | 10 | - | - | - | - | - | - | 135 | - |

EN 12168 - Hollow Rods for Free Machining

| Material Condition | Wall Thickness (mm) | | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation A (%) Min | Hardness (HBW) | | Hardness (HV) | |
|-----------------------|------------------------|-------------------|---|--|-----|-------------------------------|-------------------|-----|------------------|-----|
| | Over | Up to and inc. | | Min | Max | | Min | Max | Min | Max |
| M | All | | As manufactured | | | | | | | |
| R360 | 3 | 40 | 360 | - | 320 | 20 | - | - | - | - |
| H090 | 3 | 40 | - | - | - | - | 90 | 125 | 100 | 135 |
| R430 | 3 | 15 | 430 | 220 | - | 10 | - | - | - | - |
| H110 | 3 | 15 | - | - | - | - | 110 | 160 | 120 | 170 |
| R500 | 3 | 7 | 500 | 350 | - | 8 | - | - | - | - |
| H135 | 3 | 7 | - | - | - | - | 135 | - | 145 | - |

EN 12165 - Wrought and Unwrought Forging Stocks

| Material Condition | Nominal Diameter (mm) | | Hardness (HBW) | |
|-----------------------|--------------------------|---------------------|-------------------|-----|
| | Over | Up to and including | Min | Max |
| M | All | | As manufactured | |
| H080 | 8 | 80 | 80 | 125 |

| STANDARD | | EN 12164 | | | EN 12165 | | EN 12168 | | | | | |
|-----------------|--------------|------------|-------------|-------------------|-----------|---------|---|------------|------------|----------------------|---------|---------------------|
| Dimension Range | | Round Rod | | Hexagonal, Square | Round Rod | | Round and Hexagonal Hollow Rod, Outer Dim. Tol. | | | Hole Tolerance Round | | Hole Tol. Hexagonal |
| Over | Up to & inc. | Class A | Class B | Rod | Class A | Class B | Class A | Class B | Class C | Class A | Class B | - |
| 5 | 6 | 0 -0,05 | 0 -0,03 | 0 -0,08 | - | - | - | - | - | - | - | - |
| 6 | 10 | 0 -0,06 | 0 -0,036 | 0 -0,09 | ±0,25 | ±0,14 | - | - | - | - | - | - |
| 10 | 13 | 0 -0,07 | 0 -0,043 | 0 -0,11 | ±0,25 | ±0,14 | - | - | - | - | - | - |
| 13 | 18 | 0 -0,07 | 0 -0,043 | 0 -0,11 | ±0,25 | ±0,14 | - | - | - | ±0,35 | - | +0,70 -0 |
| 18 | 20 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | - | - | ±0,42 | - | +0,84 -0 |
| 20 | 23 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | - | - | ±0,42 | ±0,17 | +0,84 -0 |
| 23 | 26 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | 0 -0,21 | - | ±0,42 | ±0,17 | +0,84 -0 |
| 26 | 30 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | 0 -0,21 | 0 -0,13 | ±0,42 | ±0,17 | +0,84 -0 |
| 30 | 50 | 0 -0,16 | - | 0 -0,16 | ±0,60 | ±0,20 | - | 0 -0,25 | 0 -0,16 | ±0,80 | ±0,20 | +1,6 -0 |
| 50 | 55 | 0 -0,19 | - | 0 -0,19 | ±0,70 | ±0,37 | - | 0 -0,46 | 0 -0,30 | ±0,95 | ±0,37 | - |
| 55 | 65 | 0 -0,19 | - | - | ±0,70 | ±0,37 | ±0,60 | 0 -0,46 | 0 -0,30 | ±0,95 | - | - |
| 65 | 80 | 0 -0,19 | - | - | ±0,70 | ±0,37 | ±0,60 | 0 -0,46 | 0 -0,30 | ±0,95 | - | - |
| 80 | 120 | - | - | - | ±2 | - | - | - | - | - | - | - |
| 120 | 140 | - | - | - | ±2,5 | - | - | - | - | - | - | - |

For Hollow Rods

Minimum wall thickness is 3 mm. Eccentricity : %10 (max.)

Outer Cold Drawn - Internal Extruded

Outer Class B - Hole Class A tolerance

Inner-Outer Cold Drawn

Outer Class C - Hole Class B tolerance

Inner-Outer Extruded

Outer Class A - Hole Class A tolerance



ECOBASS

(PATENTED)

RODS / HOLLOW RODS

CW724R - CuZn21Si3P

| Product Code | EN Symbol | EN No | ASTM | | Cu | Zn | Pb | Sn | Fe | Ni | Al | Mn | P | Si | Others Total |
|--------------|------------|--------|--------|---------|------|------|------|-----|-----|-----|------|------|------|-----|--------------|
| ECOBRESS | CuZn21Si3P | CW724R | C69300 | Min (%) | 75,0 | Rem. | - | - | - | - | - | - | 0,02 | 2,7 | - |
| | | | | Max (%) | 77,0 | Rem. | 0,09 | 0,3 | 0,3 | 0,2 | 0,05 | 0,05 | 0,10 | 3,5 | 0,2 |

(*) Each of the other elements < 0,02 %

Features And Applications

This lead free alloy is patented. Chips and parts should not be mixed with other alloys. It has many features such as good machinability, high durability, recyclability, perfect corrosion resistance, good forgeability. Ecobrass can be produced as rods, hollows, profiles suitable for both forging and machining. Ecobrass meets ISO 6509 requirements regarding the dezincification resistance. Also this alloy compliance with UBA Hygienic list, 4MS, ELV, RoHS II and REACH directives.

4MS and UBA Hygienic list group for CW724R alloy: B, C, D

Area of Usage

Automotive industry, naval industry, plumbing and drinking water applications. Also this alloy suitable for drinking water application in USA and Canada Markets.

TECHNICAL SPECIFICATIONS

| | | | |
|-----------------------------|------------------------|-------------------------------|------------|
| Structure | kappa+gama | Hot Forming | 530-650 °C |
| Machinability | % 80 | Soft Annealing | 1-3 hours |
| Density | 8,25 g/cm ³ | Soft Annealing Time | 200-300 °C |
| Electrical Conductivity | 4,5 MS/m, 7,8 %IACS | Stress Relieving Time | 1-3 hours |
| Thermal Conductivity | 35 W/(m·K) | Max. Depth of Dezincification | <100 μm |
| Elasticity Module | ca.100 GPa | | |
| Coeff. of Thermal Expansion | 860-925 °C | | |
| Melting Point | 680-750 °C | | |


Range of Products

CW724R can be produced in our extrusion and cold drawing unit as rods, hollows and profiles suitable for both forging and machining. Please contact us for other technical informations.

INDICATIVE SHAPED ENDS DIMENSIONS

| Nominal Diameter or Width | | Type A - Chamfer Length (L) | | Type B - Point Length (L) | |
|---------------------------|---------------------|-----------------------------|----------|---------------------------|----------|
| Across-flats (mm) | | Min (mm) | Max (mm) | Min (mm) | Max (mm) |
| Over | Up to and including | | | | |
| - | 10 | 0,2 | 1,5 | 2 | 7 |
| 10 | 20 | 0,2 | 2 | 3 | 10 |
| 20 | 30 | 0,2 | 3 | 4 | 12 |

Unless otherwise specified by the buyer, the shape of the ends of products larger than 30 mm is up to the supplier.

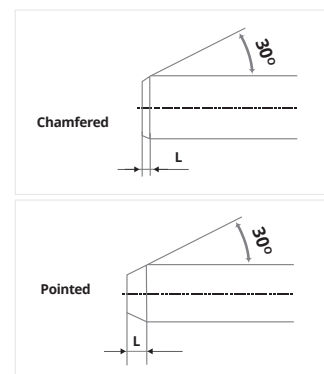

| Nominal Diameter or Width Across-flats (mm) | | Preferred (available) Lengths (mm) | Tolerance on Length (mm) |
|--|---------------------|---------------------------------------|-----------------------------|
| Over | Up to and including | | |
| 10 ^{Inc.} | 30 | 3.000 - 4.000 | ±50 |
| 30 | 80 | 3.000 - 4.000 | ±100 |

Stress Relieving

The polygonal rods and hollow rods are subjected to stress relieving treatment

Packaging

500 or 1000 kg bundle - 3/5 metal straps different bundle packagings, up to 10 mm dimension products are packed with wooden case

EN 12164 - Rods for Free Machining

| Material Condition | Nominal Diameter (mm) | | Width Across-flats (mm) | | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation | | | Hardness (HBW) | | |
|--------------------|-----------------------|----------------|-------------------------|----------------|--|--|-----|------------------------|-----------------------|-------|----------------|-----|--|
| | Over | Up to and inc. | Over | Up to and inc. | | Min | Max | A _{100mm} (%) | A _{11,3} (%) | A (%) | Min | Max | |
| M | All | | All | | As manufactured | | | | | | | | |
| R500 | 10 | 80 | 35 | 55 | 500 | - | 450 | - | - | 15 | - | - | |
| H130 | 10 | 80 | 35 | 55 | - | - | - | - | - | - | 130 | 180 | |
| R600 | 10 | 40 | 15 | 40 | 600 | 300 | - | - | - | 12 | - | - | |
| H150 | 10 | 40 | 15 | 40 | - | - | - | - | - | - | 150 | 220 | |
| R670 | 10 | 20 | 10 | 15 | 670 | 400 | - | 8 | 9 | 10 | - | - | |
| H170 | 10 | 20 | 10 | 15 | - | - | - | - | - | - | 170 | - | |

EN 12168 - Hollow Rods for Free Machining

| Material Condition | Wall Thickness (mm) | | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation A (%) Min | Hardness (HBW) | | Hardness (HV) | |
|--------------------|---------------------|----------------|--|--|-----|-------------------------|----------------|-----|---------------|-----|
| | Over | Up to and inc. | | Min | Max | | Min | Max | Min | Max |
| M | All | | As manufactured | | | | | | | |
| R500 | 4 | 20 | 500 | - | 450 | 15 | - | - | - | - |
| H130 | 4 | 20 | - | - | - | - | 130 | 180 | 140 | 190 |
| R600 | 4 | 20 | 600 | 350 | - | 12 | - | - | - | - |
| H150 | 4 | 20 | - | - | - | - | 150 | 220 | 160 | 230 |
| R650 | 4 | 7 | 650 | 400 | - | 10 | - | - | - | - |
| H170 | 4 | 7 | - | - | - | - | 170 | - | 180 | - |

EN 12165 - Wrought and Unwrought Forging Stocks

| Material Condition | Nominal Diameter (mm) | | Hardness (HBW) | |
|--------------------|-----------------------|---------------------|-----------------|-----|
| | Over | Up to and including | Min | Max |
| M | All | | As manufactured | |
| H130 | 8 | 80 | 130 | 220 |

| STANDARD | | EN 12164 | | | EN 12165 | | EN 12168 | | | | |
|-----------------|--------------|------------|-------------|-------------------|-----------|---------|---|------------|----------------------|---------|---------------------|
| Dimension Range | | Round Rod | | Hexagonal, Square | Round Rod | | Round and Hexagonal Hollow Rod, Outer Dim. Tol. | | Hole Tolerance Round | | Hole Tol. Hexagonal |
| Over | Up to & inc. | Class A | Class B | Rod | Class A | Class B | Class A | Class B | Class A | Class B | - |
| - | 10 | 0 -0,06 | 0 -0,036 | 0 -0,09 | ±0,25 | ±0,14 | - | - | - | - | - |
| 10 | 13 | 0 -0,07 | 0 -0,043 | 0 -0,11 | ±0,25 | ±0,14 | - | - | - | - | - |
| 13 | 18 | 0 -0,07 | 0 -0,043 | 0 -0,11 | ±0,25 | ±0,14 | - | - | ±0,35 | - | +0,70 -0 |
| 18 | 20 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | - | ±0,42 | - | +0,84 -0 |
| 20 | 23 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | - | ±0,42 | ±0,17 | +0,84 -0 |
| 23 | 26 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | 0 -0,21 | ±0,42 | ±0,17 | +0,84 -0 |
| 26 | 30 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | 0 -0,21 | ±0,42 | ±0,17 | +0,84 -0 |
| 30 | 50 | 0 -0,16 | - | 0 -0,16 | ±0,60 | ±0,20 | - | 0 -0,25 | ±0,80 | ±0,20 | +1,6 -0 |
| 50 | 55 | 0 -0,19 | - | 0 -0,19 | ±0,70 | ±0,37 | - | 0 -0,46 | ±0,95 | ±0,37 | - |
| 55 | 65 | 0 -0,19 | - | - | ±0,70 | ±0,37 | ±0,60 | 0 -0,46 | ±0,95 | - | - |
| 65 | 80 | 0 -0,19 | - | - | ±0,70 | ±0,37 | ±0,60 | 0 -0,46 | ±0,95 | - | - |
| 80 | 120 | - | - | - | ±2 | - | - | - | - | - | - |
| 120 | 140 | - | - | - | ±2,5 | - | - | - | - | - | - |

For Hollow Rods

Minimum wall thickness is 4 mm. Eccentricity : %10 (max.)

Outer Cold Drawn - Internal Extruded

Outer Class B - Hole Class A tolerance

Inner-Outer Extruded

Outer Class A - Hole Class A tolerance



S625

RODS / HOLLOW RODS

CW625N - CuZn35Pb1,5AlAs

| Product Code | EN Symbol | EN No | ASTM | | Cu | Zn | Pb | Sn | Fe | As | Ni | Al | Mn | Others Total |
|--------------|-----------------|--------|------|---------|------|------|-----|-----|-----|------|-----|-----|-----|--------------|
| S625 | CuZn35Pb1,5AlAs | CW625N | - | Min (%) | 62,0 | Rem. | 1,2 | - | - | 0,02 | - | 0,5 | - | - |
| | | | | Max (%) | 64,0 | Rem. | 1,6 | 0,3 | 0,3 | 0,15 | 0,2 | 0,7 | 0,1 | 0,2 |

(*) Each of the other elements < 0,02 %

Features And Applications

CW625N is an alloy as a substitute for the alloy CW602N. CW625N meets ISO 6509 requirements regarding the dezincification resistance. Approximately 2 hours annealing at around 500 °C is recommended for EN ISO 6509 standard compliance after hot forging process. Depending on the process conditions, temperature and time can also change. Also this alloy compliance with UBA Hygienic list, 4MS, RoHS II and REACH directives.

4MS and UBA Hygienic list group for CW625N alloy: B, C, D

Area of Usage

Fitting parts used in aggressive (corrosive) water.

TECHNICAL SPECIFICATIONS

| | | | |
|-----------------------------|--------------------------|-------------------------------|------------|
| Structure | α | Hot Forming | 700-800 °C |
| Machinability | % 80 | Soft Annealing | 500-550 °C |
| Density | 8,4 g/cm ³ | Soft Annealing Time | 2 hours |
| Electrical Conductivity | 19 %IACS | Stress Relieving | 200-250 °C |
| Thermal Conductivity | 93 W/(m·K) | Stress Relieving Time | 2 hours |
| Elasticity Module | 100 kN/mm ² | Max. Depth of Dezincification | <200 μm |
| Coeff. of Thermal Expansion | 21,3 10 ⁻⁶ /K | | |
| Melting Point | 875-900 °C | | |



Range of Products

S625 alloy can be produced in our extrusion and cold drawing unit as rods, hollows and profiles suitable for both forging and machining. Please contact us for other technical informations.

INDICATIVE SHAPED ENDS DIMENSIONS

| Nominal Diameter or Width | | Type A – Chamfer Length (L) | | Type B – Point Length (L) | |
|---------------------------|---------------------|-----------------------------|----------|---------------------------|----------|
| Across-flats (mm) | | Min (mm) | Max (mm) | Min (mm) | Max (mm) |
| Over | Up to and including | | | | |
| - | 10 | 0,2 | 1,5 | 2 | 7 |
| 10 | 20 | 0,2 | 2 | 3 | 10 |
| 20 | 30 | 0,2 | 3 | 4 | 12 |

Unless otherwise specified by the buyer, the shape of the ends of products larger than 30 mm is up to the supplier.

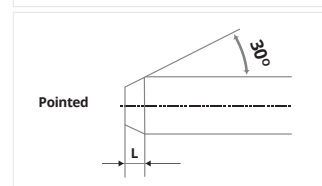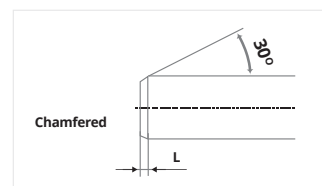

| Nominal Diameter or Width Across-flats (mm) | | Preferred (available) Lengths (mm) | Tolerance on Length (mm) |
|--|---------------------|---------------------------------------|-----------------------------|
| Over | Up to and including | | |
| 10 ^{inc.} | 30 | 3.000 - 4.000 | ±50 |
| 30 | 80 | 3.000 - 4.000 | ±100 |

Stress Relieving The polygonal rods and hollow rods are subjected to stress relieving treatment

Packaging 500 or 1000 kg bundle – 3/5 metal straps different bundle packagings, up to 10 mm dimension products are packed with wooden case

EN 12164 - Rods for Free Machining

| Material Condition | Nominal Diameter (mm) | | Width Across-flats (mm) | | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation | | | Hardness (HBW) | |
|--------------------|-----------------------|----------------|-------------------------|----------------|--|--|-----|------------------------|-----------------------|-------|----------------|-----|
| | Over | Up to and inc. | Over | Up to and inc. | | Min | Max | A _{100mm} (%) | A _{11,3} (%) | A (%) | Min | Max |
| M | All | | All | | As manufactured | | | | | | | |
| R280 | 10 | 80 | 10 | 55 | 280 | - | 200 | - | 25 | 30 | - | - |
| H070 | 10 | 80 | 10 | 55 | - | - | - | - | - | - | 70 | 110 |
| R320 | 10 | 60 | 10 | 50 | 320 | 200 | - | - | 15 | 20 | - | - |
| H090 | 10 | 60 | 10 | 50 | - | - | - | - | - | - | 90 | 135 |
| R400 | 10 | 15 | 10 | 13 | 400 | 250 | - | - | 5 | 8 | - | - |
| H105 | 10 | 15 | 10 | 13 | - | - | - | - | - | - | 105 | - |

EN 12168 - Hollow Rods for Free Machining

| Material Condition | Wall Thickness (mm) | | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation A (%) Min | Hardness (HBW) | | Hardness (HV) | |
|--------------------|---------------------|----------------|--|--|-----|-------------------------|----------------|-----|---------------|-----|
| | Over | Up to and inc. | | Min | Max | | Min | Max | Min | Max |
| M | All | | As manufactured | | | | | | | |
| R280 | 4 | All | 280 | - | 200 | 30 | - | - | - | - |
| H070 | 4 | All | - | - | - | - | 70 | 110 | 80 | 120 |
| R320 | 4 | 20 | 320 | 200 | - | 20 | - | - | - | - |
| H090 | 4 | 20 | - | - | - | - | 90 | 135 | 100 | 145 |
| R400 | 4 | 8 | 400 | 250 | - | 8 | - | - | - | - |
| H105 | 4 | 8 | - | - | - | - | 105 | - | 115 | - |

EN 12165 - Wrought and Unwrought Forging Stocks

| Material Condition | Nominal Diameter (mm) | | Hardness (HBW) | |
|--------------------|-----------------------|---------------------|-----------------|-----|
| | Over | Up to and including | Min | Max |
| M | All | | As manufactured | |
| H070 | 8 | 80 | 70 | 110 |

| STANDARD | | EN 12164 | | | EN 12165 | | EN 12168 | | | | | |
|-----------------|--------------|------------|-------------|-------------------|-----------|---------|---|------------|------------|----------------------|---------|---------------------|
| Dimension Range | | Round Rod | | Hexagonal, Square | Round Rod | | Round and Hexagonal Hollow Rod, Outer Dim. Tol. | | | Hole Tolerance Round | | Hole Tol. Hexagonal |
| Over | Up to & inc. | Class A | Class B | Rod | Class A | Class B | Class A | Class B | Class C | Class A | Class B | - |
| - | 10 | 0 -0,06 | 0 -0,036 | 0 -0,09 | ±0,25 | ±0,14 | - | - | - | - | - | - |
| 10 | 13 | 0 -0,07 | 0 -0,043 | 0 -0,11 | ±0,25 | ±0,14 | - | - | - | - | - | - |
| 13 | 18 | 0 -0,07 | 0 -0,043 | 0 -0,11 | ±0,25 | ±0,14 | - | - | - | ±0,35 | - | +0,70 -0 |
| 18 | 20 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | - | - | ±0,42 | - | +0,84 -0 |
| 20 | 23 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | - | - | ±0,42 | ±0,17 | +0,84 -0 |
| 23 | 26 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | 0 -0,21 | - | ±0,42 | ±0,17 | +0,84 -0 |
| 26 | 30 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | 0 -0,21 | 0 -0,13 | ±0,42 | ±0,17 | +0,84 -0 |
| 30 | 50 | 0 -0,16 | - | 0 -0,16 | ±0,60 | ±0,20 | - | 0 -0,25 | 0 -0,16 | ±0,80 | ±0,20 | +1,6 -0 |
| 50 | 55 | 0 -0,19 | - | 0 -0,19 | ±0,70 | ±0,37 | - | 0 -0,46 | 0 -0,30 | ±0,95 | ±0,37 | - |
| 55 | 65 | 0 -0,19 | - | - | ±0,70 | ±0,37 | ±0,60 | 0 -0,46 | 0 -0,30 | ±0,95 | - | - |
| 65 | 80 | 0 -0,19 | - | - | ±0,70 | ±0,37 | ±0,60 | 0 -0,46 | 0 -0,30 | ±0,95 | - | - |
| 80 | 120 | - | - | - | ±2 | - | - | - | - | - | - | - |
| 120 | 140 | - | - | - | ±2,5 | - | - | - | - | - | - | - |

For Hollow Rods

Minimum wall thickness is 4 mm. Eccentricity : %10 (max.)

Outer Cold Drawn - Internal Extruded

Outer Class B - Hole Class A tolerance

Inner-Outer Cold Drawn

Outer Class C - Hole Class B tolerance

Inner-Outer Extruded

Outer Class A - Hole Class A tolerance



S608

RODS / HOLLOW RODS

CW608N - CuZn38Pb2

| Product Code | EN Symbol | EN No | ASTM | | Cu | Zn | Pb | Sn | Fe | Ni | Al | Others Total |
|--------------|-----------|-------|------|---------|------|------|-----|-----|-----|-----|------|--------------|
| S608 | CuZn38Pb2 | - | - | Min (%) | 60,0 | Rem. | 1,6 | - | - | - | - | - |
| | | | | Max (%) | 61,0 | Rem. | 2,5 | 0,2 | 0,2 | 0,3 | 0,05 | 0,2 |

Features And Applications

In addition to good machinability is an alloy that exhibits good cold working properties. Also this alloy compliance with RoHS II and REACH directives.

CW603N alloy is not suitable for 4MS vs UBA list for drinking water applications.

Area of Usage

Parts manufactured by cold forming.

TECHNICAL SPECIFICATIONS

| | | | |
|-----------------------------|--------------------------|-----------------------|------------|
| Structure | $\alpha+\beta$ | Hot Forming | 650-750 °C |
| Machinability | % 90 | Soft Annealing | 450-650 °C |
| Density | 8,44 g/cm ³ | Soft Annealing Time | 1-3 hours |
| Electrical Conductivity | 14 MS/m, 24 %IACS | Stress Relieving | 200-300 °C |
| Thermal Conductivity | 109 W/(m·K) | Stress Relieving Time | 1-3 hours |
| Elasticity Module | 102 GPa | | |
| Coeff. of Thermal Expansion | 20,4 10 ⁻⁶ /K | | |
| Melting Point | 895-900 °C | | |



Range of Products

S608 alloy can be produced in our extrusion and cold drawing unit as rods, hollows and profiles suitable for both forging and machining. Please contact us for other technical informations.

INDICATIVE SHAPED ENDS DIMENSIONS

| Nominal Diameter or Width | | Type A - Chamfer Length (L) | | Type B - Point Length (L) | |
|---------------------------|---------------------|-----------------------------|----------|---------------------------|----------|
| Across-flats (mm) | | Min (mm) | Max (mm) | Min (mm) | Max (mm) |
| Over | Up to and including | | | | |
| 6 inc. | 10 | 0,2 | 1,5 | 2 | 7 |
| 10 | 20 | 0,2 | 2 | 3 | 10 |
| 20 | 30 | 0,2 | 3 | 4 | 12 |

Unless otherwise specified by the buyer, the shape of the ends of products larger than 30 mm is up to the supplier.

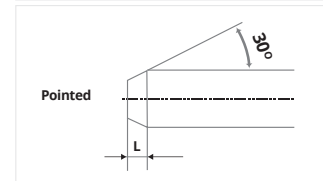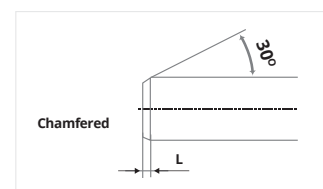

| Nominal Diameter or Width Across-flats (mm) | | Preferred (available) Lengths (mm) | Tolerance on Length (mm) |
|--|---------------------|---------------------------------------|-----------------------------|
| Over | Up to and including | | |
| 6 ^{Inc.} | 30 | 3.000 - 4.000 | ±50 |
| 30 | 80 | 3.000 - 4.000 | ±100 |

Stress Relieving The polygonal rods and hollow rods are subjected to stress relieving treatment

Packaging 500 or 1000 kg bundle – 3/5 metal straps different bundle packagings, up to 10 mm dimension products are packed with wooden case

EN 12164 - Rods for Free Machining

| Material Condition | Nominal Diameter (mm) | | Width Across-flats (mm) | | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation | | | Hardness (HBW) | |
|-----------------------|-----------------------------|-------------------|-------------------------------|-------------------|---|--|-----|----------------------------------|---------------------------------|-----------------|-------------------|-----|
| | Over | Up to and inc. | Over | Up to and inc. | | Min | Max | A _{100mm} (%) Min | A _{11,3} (%) Min | A (%) Min | Min | Max |
| M | All | | All | | As manufactured | | | | | | | |
| R360 | 6 | 80 | 6 | 55 | 360 | - | 300 | - | 15 | 20 | - | - |
| H070 | 6 | 80 | 6 | 55 | - | - | - | - | - | - | 70 | 100 |
| R410 | 6 | 40 | 6 | 35 | 410 | 230 | - | 8 | 10 | 12 | - | - |
| H100 | 6 | 40 | 6 | 35 | - | - | - | - | - | - | 100 | 145 |
| R500 | 6 | 14 | 6 | 10 | 500 | 350 | - | 3 | 5 | 8 | - | - |
| H120 | 6 | 14 | 6 | 10 | - | - | - | - | - | - | 120 | - |

EN 12168 - Hollow Rods for Free Machining

| Material Condition | Wall Thickness (mm) | | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation A (%) Min | Hardness (HBW) | | Hardness (HV) | |
|-----------------------|------------------------|-------------------|---|--|-----|-------------------------------|-------------------|-----|------------------|-----|
| | Over | Up to and inc. | | Min | Max | | Min | Max | Min | Max |
| M | All | | As manufactured | | | | | | | |
| R360 | 4 | 20 | 360 | - | 300 | 20 | - | - | - | - |
| H070 | 4 | 20 | - | - | - | - | 70 | 100 | 80 | 110 |
| R410 | 4 | 10 | 410 | 250 | - | 12 | - | - | - | - |
| H100 | 4 | 10 | - | - | - | - | 100 | 145 | 110 | 155 |
| R500 | 4 | 7 | 500 | 350 | - | 8 | - | - | - | - |
| H120 | 4 | 7 | - | - | - | - | 120 | - | 130 | - |

EN 12165 - Wrought and Unwrought Forging Stocks

| Material Condition | Nominal Diameter (mm) | | Hardness (HBW) | |
|-----------------------|--------------------------|---------------------|-------------------|-----|
| | Over | Up to and including | Min | Max |
| M | All | | As manufactured | |
| H070 | 8 | 80 | 70 | 100 |

| STANDARD | | EN 12164 | | | EN 12165 | | EN 12168 | | | | | |
|-----------------|--------------|------------|-------------|-------------------|-----------|---------|---|------------|------------|----------------------|---------|---------------------|
| Dimension Range | | Round Rod | | Hexagonal, Square | Round Rod | | Round and Hexagonal Hollow Rod, Outer Dim. Tol. | | | Hole Tolerance Round | | Hole Tol. Hexagonal |
| Over | Up to & inc. | Class A | Class B | Rod | Class A | Class B | Class A | Class B | Class C | Class A | Class B | - |
| - | 6 | 0 -0,05 | 0 -0,03 | 0 -0,08 | - | - | - | - | - | - | - | - |
| 6 | 10 | 0 -0,06 | 0 -0,36 | 0 -0,09 | ±0,25 | ±0,14 | - | - | - | - | - | - |
| 10 | 13 | 0 -0,07 | 0 -0,043 | 0 -0,11 | ±0,25 | ±0,14 | - | - | - | - | - | - |
| 13 | 18 | 0 -0,07 | 0 -0,043 | 0 -0,11 | ±0,25 | ±0,14 | - | - | - | ±0,35 | - | +0,70 -0 |
| 18 | 20 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | - | - | ±0,42 | - | +0,84 -0 |
| 20 | 23 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | - | - | ±0,42 | ±0,17 | +0,84 -0 |
| 23 | 26 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | 0 -0,21 | - | ±0,42 | ±0,17 | +0,84 -0 |
| 26 | 30 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | 0 -0,21 | 0 -0,13 | ±0,42 | ±0,17 | +0,84 -0 |
| 30 | 50 | 0 -0,16 | - | 0 -0,16 | ±0,60 | ±0,20 | - | 0 -0,25 | 0 -0,16 | ±0,80 | ±0,20 | +1,6 -0 |
| 50 | 55 | 0 -0,19 | - | 0 -0,19 | ±0,70 | ±0,37 | - | 0 -0,46 | 0 -0,30 | ±0,95 | ±0,37 | - |
| 55 | 65 | 0 -0,19 | - | - | ±0,70 | ±0,37 | ±0,60 | 0 -0,46 | 0 -0,30 | ±0,95 | - | - |
| 65 | 80 | 0 -0,19 | - | - | ±0,70 | ±0,37 | ±0,60 | 0 -0,46 | 0 -0,30 | ±0,95 | - | - |
| 80 | 120 | - | - | - | ±2 | - | - | - | - | - | - | - |
| 120 | 140 | - | - | - | ±2,5 | - | - | - | - | - | - | - |

For Hollow Rods

Minimum wall thickness is 4 mm. Eccentricity : %10 (max.)

Outer Cold Drawn - Internal Extruded

Outer Class B - Hole Class A tolerance

Inner-Outer Cold Drawn

Outer Class C - Hole Class B tolerance

Inner-Outer Extruded

Outer Class A - Hole Class A tolerance



S603 - S603DW

RODS / HOLLOW RODS

CW603N - CuZn36Pb3

| Product Code | EN Symbol | EN No | ASTM | | Cu | Zn | Pb | Sn | Fe | Ni | Al | Si | Others Total |
|--------------|--------------|-----------|--------|---------|------|------|-----|-----|-----|-----|------|------|--------------|
| S603 | CuZn36Pb3 | CW603N | C36000 | Min (%) | 60,0 | Rem. | 2,5 | - | - | - | - | - | - |
| | | | | Max (%) | 62,0 | Rem. | 3,5 | 0,2 | 0,3 | 0,3 | 0,05 | - | 0,2 |
| (*) S603DW | CuZn36Pb3-DW | CW603N-DW | C36000 | Min (%) | 60,0 | Rem. | 2,5 | - | - | - | - | - | - |
| | | | | Max (%) | 62,0 | Rem. | 3,5 | 0,2 | 0,3 | 0,2 | 0,05 | 0,02 | 0,2 |

(*) Each of the other elements < 0,02 %

Features And Applications

CW603N is standard free machining alloy in USA market and named C36000. Also this alloy compliance with RoHS II and REACH directives. CW603N-DW alloy be used suitable for 4MS vs UBA list for drinking water applications.

4MS and UBA Hygienic list group for CW603N-DW alloy: C and D

Area of Usage

High speed machining parts, screws and nuts.

TECHNICAL SPECIFICATIONS

| | | | |
|-----------------------------|--------------------------|-------------------------------|------------|
| Structure | $\alpha+\beta$ | Hot Forming | 700-800 °C |
| Machinability | % 90 | Soft Annealing | 450-600 °C |
| Density | 8,5 g/cm ³ | Soft Annealing Time | 1-3 hours |
| Electrical Conductivity | 13 MS/m, 22 %IACS | Stress Relieving | 200-300 °C |
| Thermal Conductivity | 100 W/(m·K) | Max. Depth of Dezincification | 1-3 hours |
| Elasticity Module | 102 GPa | | |
| Coeff. of Thermal Expansion | 20,6 10 ⁻⁶ /K | | |
| Melting Point | 885-900 °C | | |


Range of Products

S603 and S603-DW alloys can be produced in our extrusion and cold drawing unit as rods, hollows and profiles suitable for both forging and machining. Please contact us for other technical informations.

INDICATIVE SHAPED ENDS DIMENSIONS

| Nominal Diameter or Width | | Type A – Chamfer Length (L) | | Type B – Point Length (L) | |
|---------------------------|---------------------|-----------------------------|----------|---------------------------|----------|
| Across-flats (mm) | | Min (mm) | Max (mm) | Min (mm) | Max (mm) |
| Over | Up to and including | | | | |
| - | 10 | 0,2 | 1,5 | 2 | 7 |
| 10 | 20 | 0,2 | 2 | 3 | 10 |
| 20 | 30 | 0,2 | 3 | 4 | 12 |

Unless otherwise specified by the buyer, the shape of the ends of products larger than 30 mm is up to the supplier.

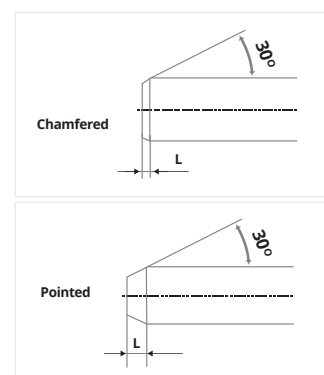

| Nominal Diameter or Width Across-flats (mm) | | Preferred (available) Lengths (mm) | Tolerance on Length (mm) |
|--|---------------------|---------------------------------------|-----------------------------|
| Over | Up to and including | | |
| 10 ^{inc.} | 30 | 3.000 - 4.000 | ±50 |
| 30 | 80 | 3.000 - 4.000 | ±100 |

Stress Relieving The polygonal rods and hollow rods are subjected to stress relieving treatment

Packaging 500 or 1000 kg bundle – 3/5 metal straps different bundle packagings, up to 10 mm dimension products are packed with wooden case

EN 12164 - Rods for Free Machining

| Material Condition | Nominal Diameter (mm) | | Width Across-flats (mm) | | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation | | | Hardness (HBW) | |
|-----------------------|-----------------------------|-------------------|-------------------------------|-------------------|---|--|-----|----------------------------------|---------------------------------|-----------------|-------------------|-----|
| | Over | Up to and inc. | Over | Up to and inc. | | Min | Max | A _{100mm} (%) Min | A _{11,3} (%) Min | A (%) Min | Min | Max |
| M | All | | All | | As manufactured | | | | | | | |
| R340 | 10 | 80 | 10 | 55 | 340 | - | 280 | - | - | 20 | - | - |
| H070 | 10 | 80 | 10 | 55 | - | - | - | - | - | - | 70 | 120 |
| R400 | 10 | 25 | 10 | 20 | 400 | 200 | - | 4 | 8 | 12 | - | - |
| H100 | 10 | 25 | 10 | 20 | - | - | - | - | - | - | 100 | 140 |
| R480 | 10 | 14 | 10 | 10 | 480 | 350 | - | 3 | 5 | 8 | - | - |
| H125 | 10 | 14 | 10 | 10 | - | - | - | - | - | - | 125 | - |

EN 12168 - Hollow Rods for Free Machining

| Material Condition | Wall Thickness (mm) | | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation A (%) Min | Hardness (HBW) | | Hardness (HV) | |
|-----------------------|------------------------|-------------------|---|--|-----|-------------------------------|-------------------|-----|------------------|-----|
| | Over | Up to and inc. | | Min | Max | | Min | Max | Min | Max |
| M | All | | As manufactured | | | | | | | |
| R340 | 4 | 20 | 340 | - | 280 | 20 | - | - | - | - |
| H070 | 4 | 20 | - | - | - | - | 70 | 120 | 80 | 130 |
| R400 | 4 | 10 | 400 | 200 | - | 12 | - | - | - | - |
| H100 | 4 | 10 | - | - | - | - | 100 | 140 | 110 | 150 |
| R480 | 4 | 7 | 480 | 350 | - | 8 | - | - | - | - |
| H125 | 4 | 7 | - | - | - | - | 125 | - | 135 | - |

| STANDARD | | EN 12164 | | | EN 12165 | | EN 12168 | | | | | |
|-----------------|--------------|------------|-------------|-------------------|-----------|---------|---|------------|------------|----------------------|---------|---------------------|
| Dimension Range | | Round Rod | | Hexagonal, Square | Round Rod | | Round and Hexagonal Hollow Rod, Outer Dim. Tol. | | | Hole Tolerance Round | | Hole Tol. Hexagonal |
| Over | Up to & inc. | Class A | Class B | Rod | Class A | Class B | Class A | Class B | Class C | Class A | Class B | - |
| - | 10 | 0 -0,06 | 0 -0,036 | 0 -0,09 | - | - | - | - | - | - | - | - |
| 10 | 13 | 0 -0,07 | 0 -0,043 | 0 -0,11 | - | - | - | - | - | - | - | - |
| 13 | 18 | 0 -0,07 | 0 -0,043 | 0 -0,11 | - | - | - | - | - | ±0,35 | - | +0,70 -0 |
| 18 | 20 | 0 -0,08 | 0 -0,052 | 0 -0,13 | - | - | - | - | - | ±0,42 | - | +0,84 -0 |
| 20 | 23 | 0 -0,08 | 0 -0,052 | 0 -0,13 | - | - | - | - | - | ±0,42 | ±0,17 | +0,84 -0 |
| 23 | 26 | 0 -0,08 | 0 -0,052 | 0 -0,13 | - | - | - | 0 -0,21 | - | ±0,42 | ±0,17 | +0,84 -0 |
| 26 | 30 | 0 -0,08 | 0 -0,052 | 0 -0,13 | - | - | - | 0 -0,21 | 0 -0,13 | ±0,42 | ±0,17 | +0,84 -0 |
| 30 | 50 | 0 -0,16 | - | 0 -0,16 | - | - | - | 0 -0,25 | 0 -0,16 | ±0,80 | ±0,20 | +1,6 -0 |
| 50 | 55 | 0 -0,19 | - | 0 -0,19 | - | - | - | 0 -0,46 | 0 -0,30 | ±0,95 | ±0,37 | - |
| 55 | 65 | 0 -0,19 | - | - | - | - | ±0,60 | 0 -0,46 | 0 -0,30 | ±0,95 | - | - |
| 65 | 80 | 0 -0,19 | - | - | - | - | ±0,60 | 0 -0,46 | 0 -0,30 | ±0,95 | - | - |
| 80 | 120 | - | - | - | - | - | - | - | - | - | - | - |
| 120 | 140 | - | - | - | - | - | - | - | - | - | - | - |

For Hollow Rods

Minimum wall thickness is 4 mm. Eccentricity : %10 (max.)

Outer Cold Drawn - Internal Extruded


Outer Class B - Hole Class A tolerance

Inner-Outer Cold Drawn

Outer Class C - Hole Class B tolerance

Inner-Outer Extruded

Outer Class A - Hole Class A tolerance

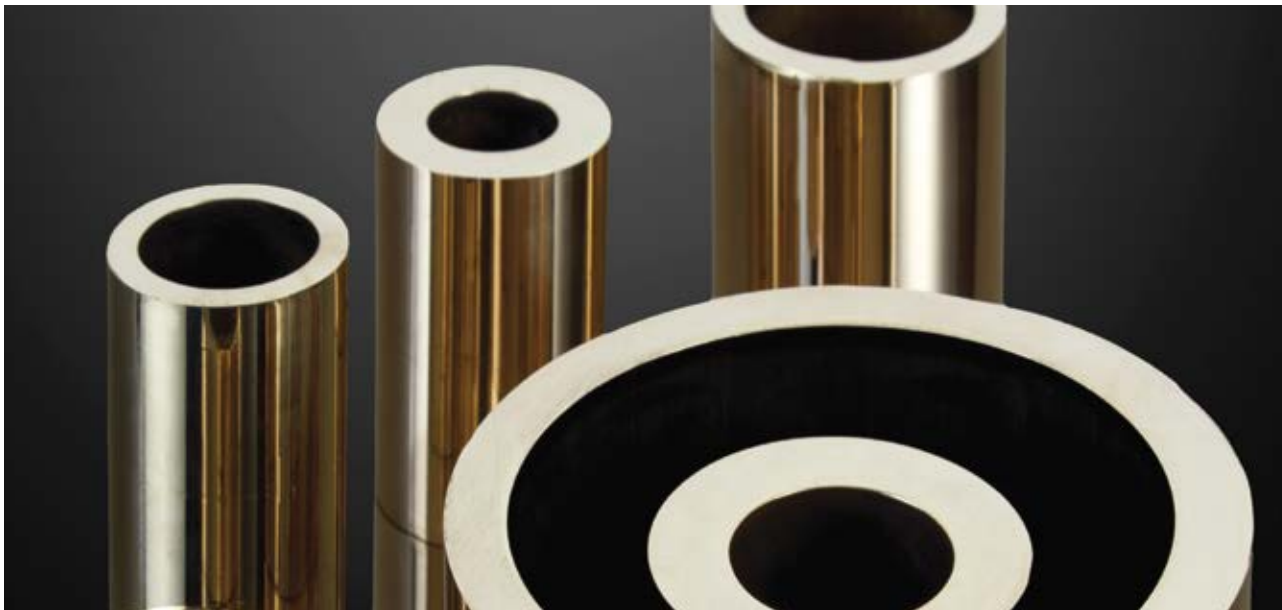

S626

RODS / HOLLOW RODS

CW626N - CuZn33Pb1,5AlAs

| Product Code | EN Symbol | EN No | ASTM | | Cu | Zn | Pb | Sn | Fe | As | Ni | Al | Mn | Others Total |
|--------------|-----------------|--------|------|---------|------|------|-----|-----|-----|------|-----|-----|-----|--------------|
| S626 | CuZn33Pb1,5AlAs | CW626N | - | Min (%) | 64,0 | Rem. | 1,2 | - | - | 0,02 | - | 0,8 | - | - |
| | | | | Max (%) | 66,0 | Rem. | 1,7 | 0,3 | 0,3 | 0,15 | 0,2 | 1 | 0,1 | 0,2 |

(*) Each of the other elements < 0,02 %

Features And Applications

CW626N is an alloy as a substitute for the alloy CW602N. CW626N meets ISO 6509 requirements regarding the dezincification resistance. Approximately 2 hours annealing at around 500 °C is recommended for EN ISO 6509 standard compliance after hot forging process. Depending on the process conditions, temperature and time can also change. Also this alloy compliance with UBA Hygienic list, 4MS, RoHS II and REACH directives.

4MS and UBA Hygienic list group for CW626N alloy: B, C, D

Area of Usage

Fitting parts used in aggressive (corrosive) water.

TECHNICAL SPECIFICATIONS

| | | | |
|-----------------------------|--------------------------|-------------------------------|------------|
| Structure | α | Hot Forming | 700-800 °C |
| Machinability | % 70 | Soft Annealing | 500-550 °C |
| Density | 8,4 g/cm ³ | Soft Annealing Time | 2 hours |
| Electrical Conductivity | 20 %IACS | Stress Relieving | 200-250 °C |
| Thermal Conductivity | 95 W/(m·K) | Stress Relieving Time | 2 hours |
| Elasticity Module | 96 kN/mm ² | Max. Depth of Dezincification | <200 μm |
| Coeff. of Thermal Expansion | 21,5 10 ⁻⁶ /K | | |
| Melting Point | 875-900 °C | | |


Range of Products

S626 alloy can be produced in our extrusion and cold drawing unit as rods, hollows and profiles suitable for both forging and machining. Please contact us for other technical informations.

INDICATIVE SHAPED ENDS DIMENSIONS

| Nominal Diameter or Width | | Type A – Chamfer Length (L) | | Type B – Point Length (L) | |
|---------------------------|---------------------|-----------------------------|----------|---------------------------|----------|
| Across-flats (mm) | | Min (mm) | Max (mm) | Min (mm) | Max (mm) |
| Over | Up to and including | | | | |
| - | 10 | 0,2 | 1,5 | 2 | 7 |
| 10 | 20 | 0,2 | 2 | 3 | 10 |
| 20 | 30 | 0,2 | 3 | 4 | 12 |

Unless otherwise specified by the buyer, the shape of the ends of products larger than 30 mm is up to the supplier.

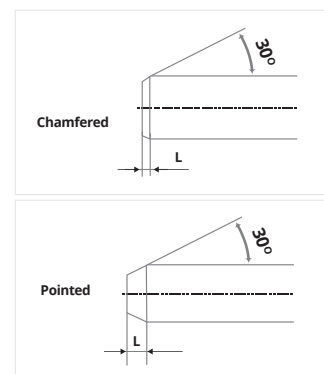

| Nominal Diameter or Width Across-flats (mm) | | Preferred (available) Lengths (mm) | Tolerance on Length (mm) |
|--|---------------------|---------------------------------------|-----------------------------|
| Over | Up to and including | | |
| 10 ^{inc.} | 30 | 3.000 - 4.000 | ±50 |
| 30 | 80 | 3.000 - 4.000 | ±100 |

Stress Relieving The polygonal rods and hollow rods are subjected to stress relieving treatment

Packaging 500 or 1000 kg bundle – 3/5 metal straps different bundle packagings, up to 10 mm dimension products are packed with wooden case

EN 12164 - Rods for Free Machining

| Material Condition | Nominal Diameter (mm) | | Width Across-flats (mm) | | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation | | | Hardness (HBW) | |
|-----------------------|-----------------------------|-------------------|-------------------------------|-------------------|---|--|-----|----------------------------------|---------------------------------|-----------------|-------------------|-----|
| | Over | Up to and inc. | Over | Up to and inc. | | Min | Max | A _{100mm} (%) Min | A _{11,3} (%) Min | A (%) Min | Min | Max |
| M | All | | All | | As manufactured | | | | | | | |
| R280 | 10 | 80 | 10 | 55 | 280 | - | 200 | - | 25 | 30 | - | - |
| H070 | 10 | 80 | 10 | 55 | - | - | - | - | - | - | 70 | 110 |
| R320 | 10 | 60 | 10 | 50 | 320 | 200 | - | - | 15 | 20 | - | - |
| H090 | 10 | 60 | 10 | 50 | - | - | - | - | - | - | 90 | 135 |
| R400 | 10 | 15 | 10 | 13 | 400 | 250 | - | - | 5 | 8 | - | - |
| H105 | 10 | 15 | 10 | 13 | - | - | - | - | - | - | 105 | - |

EN 12168 - Hollow Rods for Free Machining

| Material Condition | Wall Thickness (mm) | | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation A (%) Min | Hardness (HBW) | | Hardness (HV) | |
|-----------------------|------------------------|-------------------|---|--|-----|-------------------------------|-------------------|-----|------------------|-----|
| | Over | Up to and inc. | | Min | Max | | Min | Max | Min | Max |
| M | All | | As manufactured | | | | | | | |
| R280 | 4 | All | 280 | - | 200 | 30 | - | - | - | - |
| H070 | 4 | All | - | - | - | - | 70 | 110 | 80 | 120 |
| R320 | 4 | 20 | 320 | 200 | - | 20 | - | - | - | - |
| H090 | 4 | 20 | - | - | - | - | 90 | 135 | 100 | 145 |
| R400 | 4 | 8 | 400 | 250 | - | 8 | - | - | - | - |
| H105 | 4 | 8 | - | - | - | - | 105 | - | 115 | - |

EN 12165 - Wrought and Unwrought Forging Stocks

| Material Condition | Nominal Diameter (mm) | | Hardness (HBW) | |
|-----------------------|--------------------------|---------------------|-------------------|-----|
| | Over | Up to and including | Min | Max |
| M | All | | As manufactured | |
| H070 | 8 | 80 | 70 | 110 |

| Dimension Range | | Round Rod | | Hexagonal, Square | Round Rod | | Round and Hexagonal Hollow Rod, Outer Dim. Tol. | | | Hole Tolerance Round | | Hole Tol. Hexagonal |
|-----------------|--------------|------------|-------------|-------------------|-----------|---------|---|------------|------------|----------------------|---------|---------------------|
| Over | Up to & inc. | Class A | Class B | Rod | Class A | Class B | Class A | Class B | Class C | Class A | Class B | - |
| - | 10 | 0 -0,06 | 0 -0,036 | 0 -0,09 | ±0,25 | ±0,14 | - | - | - | - | - | - |
| 10 | 13 | 0 -0,07 | 0 -0,043 | 0 -0,11 | ±0,25 | ±0,14 | - | - | - | - | - | - |
| 13 | 18 | 0 -0,07 | 0 -0,043 | 0 -0,11 | ±0,25 | ±0,14 | - | - | - | ±0,35 | - | +0,70 -0 |
| 18 | 20 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | - | - | ±0,42 | - | +0,84 -0 |
| 20 | 23 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | - | - | ±0,42 | ±0,17 | +0,84 -0 |
| 23 | 26 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | 0 -0,21 | - | ±0,42 | ±0,17 | +0,84 -0 |
| 26 | 30 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | 0 -0,21 | 0 -0,13 | ±0,42 | ±0,17 | +0,84 -0 |
| 30 | 50 | 0 -0,16 | - | 0 -0,16 | ±0,60 | ±0,20 | - | 0 -0,25 | 0 -0,16 | ±0,80 | ±0,20 | +1,6 -0 |
| 50 | 55 | 0 -0,19 | - | 0 -0,19 | ±0,70 | ±0,37 | - | 0 -0,46 | 0 -0,30 | ±0,95 | ±0,37 | - |
| 55 | 65 | 0 -0,19 | - | - | ±0,70 | ±0,37 | ±0,60 | 0 -0,46 | 0 -0,30 | ±0,95 | - | - |
| 65 | 80 | 0 -0,19 | - | - | ±0,70 | ±0,37 | ±0,60 | 0 -0,46 | 0 -0,30 | ±0,95 | - | - |
| 80 | 120 | - | - | - | ±2 | - | - | - | - | - | - | - |
| 120 | 140 | - | - | - | ±2,5 | - | - | - | - | - | - | - |

For Hollow Rods

Minimum wall thickness is 4 mm. Eccentricity : %10 (max.)

Outer Cold Drawn - Internal Extruded

Outer Class B - Hole Class A tolerance

Inner-Outer Cold Drawn

Outer Class C - Hole Class B tolerance

Inner-Outer Extruded

Outer Class A - Hole Class A tolerance



S602

RODS / HOLLOW RODS

CW602N - CuZn36Pb2As

| Product Code | EN Symbol | EN No | ASTM | | Cu | Zn | Pb | Sn | Fe | As | Ni | Al | Mn | Others Total |
|--------------|-------------|--------|--------|---------|------|------|-----|-----|-----|------|-----|------|-----|--------------|
| S602 | CuZn36Pb2As | CW602N | C35330 | Min (%) | 61,0 | Rem. | 1,7 | - | - | 0,02 | - | - | - | - |
| | | | | Max (%) | 63,0 | Rem. | 2,2 | 0,1 | 0,1 | 0,15 | 0,3 | 0,05 | 0,1 | 0,2 |

Features And Applications

CW602N alloy is standard dezincification resistant brass . CW602N meets ISO 6509 requirements regarding the dezincification resistance. Approximately 2 hours annealing at around 500° C is recommended for EN ISO 6509 standard compliance after hot forging process. Depending on the process conditions, temperature and time can also change. Also this alloy compliance with RoHS II and REACH directives.

CW602N alloy is not suitable for 4MS.

Area of Usage

Fitting parts used in aggressive (corrosive) water.

TECHNICAL SPECIFICATIONS

| | | | |
|-----------------------------|--------------------------|-------------------------------|------------|
| Structure | α | Hot Forming | 720-830 °C |
| Machinability | % 80 | Soft Annealing | 450-550 °C |
| Density | 8,46 g/cm ³ | Soft Annealing Time | 1-3 hours |
| Electrical Conductivity | 14,7 MS/m, 25 %IACS | Stress Relieving | 250-350 °C |
| Thermal Conductivity | 114 W/(m·K) | Stress Relieving Time | 1-3 hours |
| Elasticity Module | 105 GPa | Max. Depth of Dezincification | <100 μm |
| Coeff. of Thermal Expansion | 20,3 10 ⁻⁶ /K | | |
| Melting Point | 885-910 °C | | |


Range of Products

S602 alloy can be produced in our extrusion and cold drawing unit as rods, hollows and profiles suitable for both forging and machining. Please contact us for other technical informations.

INDICATIVE SHAPED ENDS DIMENSIONS

| Nominal Diameter or Width | | Type A - Chamfer Length (L) | | Type B - Point Length (L) | |
|---------------------------|---------------------|-----------------------------|----------|---------------------------|----------|
| Across-flats (mm) | | Min (mm) | Max (mm) | Min (mm) | Max (mm) |
| Over | Up to and including | | | | |
| - | 10 | 0,2 | 1,5 | 2 | 7 |
| 10 | 20 | 0,2 | 2 | 3 | 10 |
| 20 | 30 | 0,2 | 3 | 4 | 12 |

Unless otherwise specified by the buyer, the shape of the ends of products larger than 30 mm is up to the supplier.

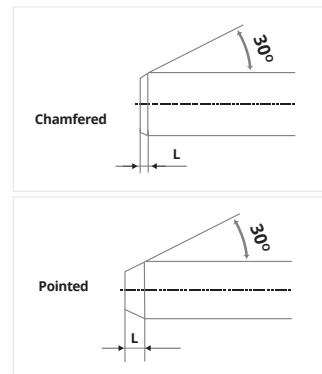

| Nominal Diameter or Width Across-flats (mm) | | Preferred (available) Lengths (mm) | Tolerance on Length (mm) |
|--|---------------------|---------------------------------------|-----------------------------|
| Over | Up to and including | | |
| 10 ^{inc.} | 30 | 3.000 - 4.000 | ±50 |
| 30 | 80 | 3.000 - 4.000 | ±100 |

Stress Relieving The polygonal rods and hollow rods are subjected to stress relieving treatment

Packaging 500 or 1000 kg bundle - 3/5 metal straps different bundle packagings, up to 10 mm dimension products are packed with wooden case

EN 12164 - Rods for Free Machining

| Material Condition | Nominal Diameter (mm) | | Width Across-flats (mm) | | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation | | | Hardness (HBW) | |
|-----------------------|-----------------------------|-------------------|-------------------------------|-------------------|---|--|-----|----------------------------------|---------------------------------|-----------------|-------------------|-----|
| | Over | Up to and inc. | Over | Up to and inc. | | Min | Max | A _{100mm} (%) Min | A _{11,3} (%) Min | A (%) Min | Min | Max |
| M | All | | All | | As manufactured | | | | | | | |
| R280 | 10 | 80 | 10 | 55 | 280 | - | 200 | - | 25 | 30 | - | - |
| H070 | 10 | 80 | 10 | 55 | - | - | - | - | - | - | 70 | 110 |
| R320 | 10 | 60 | 10 | 50 | 320 | 200 | - | - | 15 | 20 | - | - |
| H090 | 10 | 60 | 10 | 50 | - | - | - | - | - | - | 90 | 135 |
| R400 | 10 | 15 | 10 | 13 | 400 | 250 | - | - | 5 | 8 | - | - |
| H105 | 10 | 15 | 10 | 13 | - | - | - | - | - | - | 105 | - |

EN 12168 - Hollow Rods for Free Machining

| Material Condition | Wall Thickness (mm) | | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation A (%) Min | Hardness (HBW) | | Hardness (HV) | |
|-----------------------|------------------------|-------------------|---|--|-----|-------------------------------|-------------------|-----|------------------|-----|
| | Over | Up to and inc. | | Min | Max | | Min | Max | Min | Max |
| M | All | | As manufactured | | | | | | | |
| R280 | 4 | All | 280 | - | 200 | 30 | - | - | - | - |
| H070 | 4 | All | - | - | - | - | 70 | 110 | 80 | 120 |
| R320 | 4 | 20 | 320 | 200 | - | 20 | - | - | - | - |
| H090 | 4 | 20 | - | - | - | - | 90 | 135 | 100 | 145 |
| R400 | 4 | 8 | 400 | 250 | - | 8 | - | - | - | - |
| H105 | 4 | 8 | - | - | - | - | 105 | - | 115 | - |

EN 12165 - Wrought and Unwrought Forging Stocks

| Material Condition | Nominal Diameter (mm) | | Hardness (HBW) | |
|-----------------------|--------------------------|---------------------|-------------------|-----|
| | Over | Up to and including | Min | Max |
| M | All | | As manufactured | |
| H070 | 8 | 80 | 70 | 110 |

| STANDARD | | EN 12164 | | | EN 12165 | | EN 12168 | | | | | |
|-----------------|--------------|------------|-------------|-------------------|-----------|---------|---|------------|------------|----------------------|---------|---------------------|
| Dimension Range | | Round Rod | | Hexagonal, Square | Round Rod | | Round and Hexagonal Hollow Rod, Outer Dim. Tol. | | | Hole Tolerance Round | | Hole Tol. Hexagonal |
| Over | Up to & inc. | Class A | Class B | Rod | Class A | Class B | Class A | Class B | Class C | Class A | Class B | - |
| - | 10 | 0 -0,06 | 0 -0,036 | 0 -0,09 | ±0,25 | ±0,14 | - | - | - | - | - | - |
| 10 | 13 | 0 -0,07 | 0 -0,043 | 0 -0,11 | ±0,25 | ±0,14 | - | - | - | - | - | - |
| 13 | 18 | 0 -0,07 | 0 -0,043 | 0 -0,11 | ±0,25 | ±0,14 | - | - | - | ±0,35 | - | +0,70 -0 |
| 18 | 20 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | - | - | ±0,42 | - | +0,84 -0 |
| 20 | 23 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | - | - | ±0,42 | ±0,17 | +0,84 -0 |
| 23 | 26 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | 0 -0,21 | - | ±0,42 | ±0,17 | +0,84 -0 |
| 26 | 30 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | 0 -0,21 | 0 -0,13 | ±0,42 | ±0,17 | +0,84 -0 |
| 30 | 50 | 0 -0,16 | - | 0 -0,16 | ±0,60 | ±0,20 | - | 0 -0,25 | 0 -0,16 | ±0,80 | ±0,20 | +1,6 -0 |
| 50 | 55 | 0 -0,19 | - | 0 -0,19 | ±0,70 | ±0,37 | - | 0 -0,46 | 0 -0,30 | ±0,95 | ±0,37 | - |
| 55 | 65 | 0 -0,19 | - | - | ±0,70 | ±0,37 | ±0,60 | 0 -0,46 | 0 -0,30 | ±0,95 | - | - |
| 65 | 80 | 0 -0,19 | - | - | ±0,70 | ±0,37 | ±0,60 | 0 -0,46 | 0 -0,30 | ±0,95 | - | - |
| 80 | 120 | - | - | - | ±2 | - | - | - | - | - | - | - |
| 120 | 140 | - | - | - | ±2,5 | - | - | - | - | - | - | - |

For Hollow Rods

Minimum wall thickness is 4 mm. Eccentricity : %10 (max.)

Outer Cold Drawn - Internal Extruded

Outer Class B - Hole Class A tolerance

Inner-Outer Cold Drawn

Outer Class C - Hole Class B tolerance

Inner-Outer Extruded

Outer Class A - Hole Class A tolerance



S511 - S511DW

RODS / HOLLOW RODS

CW511L - CuZn38As

| Product Code | EN Symbol | EN No | ASTM | | Cu | Zn | Pb | Sn | Fe | Ni | Al | As | Others Total |
|--------------|-------------|-----------|--------|---------|------|------|-----|-----|-----|-----|------|------|--------------|
| S511 | CuZn38As | CW511L | C27453 | Min (%) | 61,5 | Rem. | - | - | - | - | - | 0,02 | - |
| | | | | Max (%) | 63,5 | Rem. | 0,2 | 0,1 | 0,1 | 0,3 | 0,05 | 0,15 | 0,2 |
| (*) S511DW | CuZn38As-DW | CW511L-DW | C27453 | Min (%) | 61,5 | Rem. | - | - | - | - | - | 0,02 | - |
| | | | | Max (%) | 63,5 | Rem. | 0,2 | 0,1 | 0,1 | 0,3 | 0,05 | 0,15 | 0,2 |

(*) Each of the other elements < 0,02 %

Features And Applications

CW511L alloy is standard dezincification resistant brass with low lead content. Chips and parts can be mixed with CW602N alloy. CW511L meets ISO 6509 requirements regarding the dezincification resistance. Approximately 2 hours annealing at around 500 °C is recommended for EN ISO 6509 standard compliance after hot forging process. Depending on the process conditions, temperature and time can also change. Also these alloy compliance with RoHS II and REACH directives. CW511L-DW alloy be used suitable for 4MS vs UBA list for drinking water applications.

4MS and UBA Hygienic list group for CW511L-DW alloy: B, C, D

Area of Usage

This alloy suitable for drinking water application in USA and Canada Markets because of the lead content below 0.2%. Thanks to a good dezincification resistance properties, it is suitable for the manufacture of parts used in aggressive (corrosive) water.

TECHNICAL SPECIFICATIONS

| | | | |
|-----------------------------|--------------------------|-------------------------------|------------|
| Structure | α | Melting Point | 850-900 °C |
| Machinability | % 40 | Hot Forming | 600-800 °C |
| Density | 8,41 g/cm ³ | Soft Annealing | 450-550 °C |
| Electrical Conductivity | 14,7 MS/m, 25,4 %IACS | Soft Annealing Time | 1-3 hours |
| Thermal Conductivity | 114 W/(m·K) | Stress Relieving | 200-250 °C |
| Elasticity Module | 100 kN/mm ² | Stress Relieving Time | 1-3 hours |
| Coeff. of Thermal Expansion | 21,7 10 ⁻⁶ /K | Max. Depth of Dezincification | <100 μm |


Range of Products

S511L and S511L-DW alloys can be produced in our extrusion and cold drawing unit as rods, hollows and profiles suitable for both forging and machining. Please contact us for other technical informations.

INDICATIVE SHAPED ENDS DIMENSIONS

| Nominal Diameter or Width | | Type A - Chamfer Length (L) | | Type B - Point Length (L) | |
|---------------------------|---------------------|-----------------------------|----------|---------------------------|----------|
| Across-flats (mm) | | Min (mm) | Max (mm) | Min (mm) | Max (mm) |
| Over | Up to and including | | | | |
| - | 10 | 0,2 | 1,5 | 2 | 7 |
| 10 | 20 | 0,2 | 2 | 3 | 10 |
| 20 | 30 | 0,2 | 3 | 4 | 12 |

Unless otherwise specified by the buyer, the shape of the ends of products larger than 30 mm is up to the supplier.

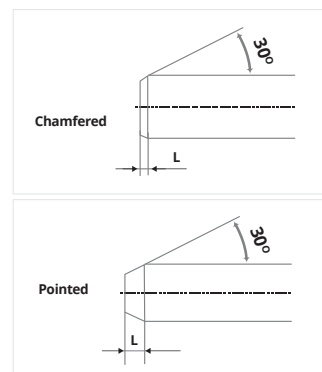

| Nominal Diameter or Width Across-flats (mm) | | Preferred (available) Lengths (mm) | Tolerance on Length (mm) |
|--|---------------------|---------------------------------------|-----------------------------|
| Over | Up to and including | | |
| 10 ^{inc.} | 30 | 3.000 - 4.000 | ±50 |
| 30 | 80 | 3.000 - 4.000 | ±100 |

Stress Relieving

The polygonal rods and hollow rods are subjected to stress relieving treatment

Packaging

500 or 1000 kg bundle – 3/5 metal straps different bundle packagings, up to 10 mm dimension products are packed with wooden case

EN 12164 - Rods for Free Machining

| Material Condition | Nominal Diameter (mm) | | Width Across-flats (mm) | | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation | | | Hardness (HBW) | |
|--------------------|-----------------------|----------------|-------------------------|----------------|--|---|-----|------------------------|-----------------------|-------|----------------|-----|
| | Over | Up to and inc. | Over | Up to and inc. | | Min | Max | A _{100mm} (%) | A _{11,3} (%) | A (%) | Min | Max |
| M | All | | All | | As manufactured | | | | | | | |
| R280 | 10 | 80 | 10 | 55 | 280 | - | 200 | - | 25 | 30 | - | - |
| H070 | 10 | 80 | 10 | 55 | - | - | - | - | - | - | 70 | 110 |
| R320 | 10 | 60 | 10 | 50 | 320 | 200 | - | - | 15 | 20 | - | - |
| H090 | 10 | 60 | 10 | 50 | - | - | - | - | - | - | 90 | 135 |
| R400 | 10 | 15 | 10 | 13 | 400 | 250 | - | - | 5 | 8 | - | - |
| H105 | 10 | 15 | 10 | 13 | - | - | - | - | - | - | 105 | - |

EN 12168 - Hollow Rods for Free Machining

| Material Condition | Wall Thickness (mm) | | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation A (%) Min | Hardness (HBW) | | Hardness (HV) | |
|--------------------|---------------------|----------------|--|---|-----|----------------------------|----------------|-----|---------------|-----|
| | Over | Up to and inc. | | Min | Max | | Min | Max | Min | Max |
| M | All | | As manufactured | | | | | | | |
| R280 | 4 | All | 280 | - | 200 | 30 | - | - | - | - |
| H070 | 4 | All | - | - | - | - | 70 | 110 | 80 | 120 |
| R320 | 4 | 20 | 320 | 200 | - | 20 | - | - | - | - |
| H090 | 4 | 20 | - | - | - | - | 90 | 135 | 100 | 145 |
| R400 | 4 | 8 | 400 | 250 | - | 8 | - | - | - | - |
| H105 | 4 | 8 | - | - | - | - | 105 | - | 115 | - |

EN 12165 - Wrought and Unwrought Forging Stocks

| Material Condition | Nominal Diameter (mm) | | Hardness (HBW) | |
|--------------------|-----------------------|---------------------|-----------------|-----|
| | Over | Up to and including | Min | Max |
| M | All | | As manufactured | |
| H070 | 8 | 80 | 70 | 110 |

| STANDARD | | EN 12164 | | | EN 12165 | | EN 12168 | | | | | |
|-----------------|--------------|------------|-------------|-------------------|-----------|---------|---|------------|------------|----------------------|---------|---------------------|
| Dimension Range | | Round Rod | | Hexagonal, Square | Round Rod | | Round and Hexagonal Hollow Rod, Outer Dim. Tol. | | | Hole Tolerance Round | | Hole Tol. Hexagonal |
| Over | Up to & inc. | Class A | Class B | Rod | Class A | Class B | Class A | Class B | Class C | Class A | Class B | - |
| - | 10 | 0 -0,06 | 0 -0,036 | 0 -0,09 | ±0,25 | ±0,14 | - | - | - | - | - | - |
| 10 | 13 | 0 -0,07 | 0 -0,043 | 0 -0,11 | ±0,25 | ±0,14 | - | - | - | - | - | - |
| 13 | 18 | 0 -0,07 | 0 -0,043 | 0 -0,11 | ±0,25 | ±0,14 | - | - | - | ±0,35 | - | +0,70 -0 |
| 18 | 20 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | - | - | ±0,42 | - | +0,84 -0 |
| 20 | 23 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | - | - | ±0,42 | ±0,17 | +0,84 -0 |
| 23 | 26 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | 0 -0,21 | 0 -0,13 | ±0,42 | ±0,17 | +0,84 -0 |
| 26 | 30 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | 0 -0,21 | 0 -0,16 | ±0,42 | ±0,17 | +0,84 -0 |
| 30 | 50 | 0 -0,16 | - | 0 -0,16 | ±0,60 | ±0,20 | - | 0 -0,25 | 0 -0,30 | ±0,80 | ±0,20 | +1,6 -0 |
| 50 | 55 | 0 -0,19 | - | 0 -0,19 | ±0,70 | ±0,37 | - | 0 -0,46 | 0 -0,30 | ±0,95 | ±0,37 | - |
| 55 | 65 | 0 -0,19 | - | - | ±0,70 | ±0,37 | ±0,60 | 0 -0,46 | 0 -0,30 | ±0,95 | - | - |
| 65 | 80 | 0 -0,19 | - | - | ±0,70 | ±0,37 | ±0,60 | 0 -0,46 | - | ±0,95 | - | - |
| 80 | 120 | - | - | - | ±2 | - | - | - | - | - | - | - |
| 120 | 140 | - | - | - | ±2,5 | - | - | - | - | - | - | - |

For Hollow Rods

Minimum wall thickness is 4 mm. Eccentricity : %10 (max.)

Outer Cold Drawn - Internal Extruded


Outer Class B - Hole Class A tolerance

Inner-Outer Cold Drawn

Outer Class C - Hole Class B tolerance

Inner-Outer Extruded

Outer Class A - Hole Class A tolerance

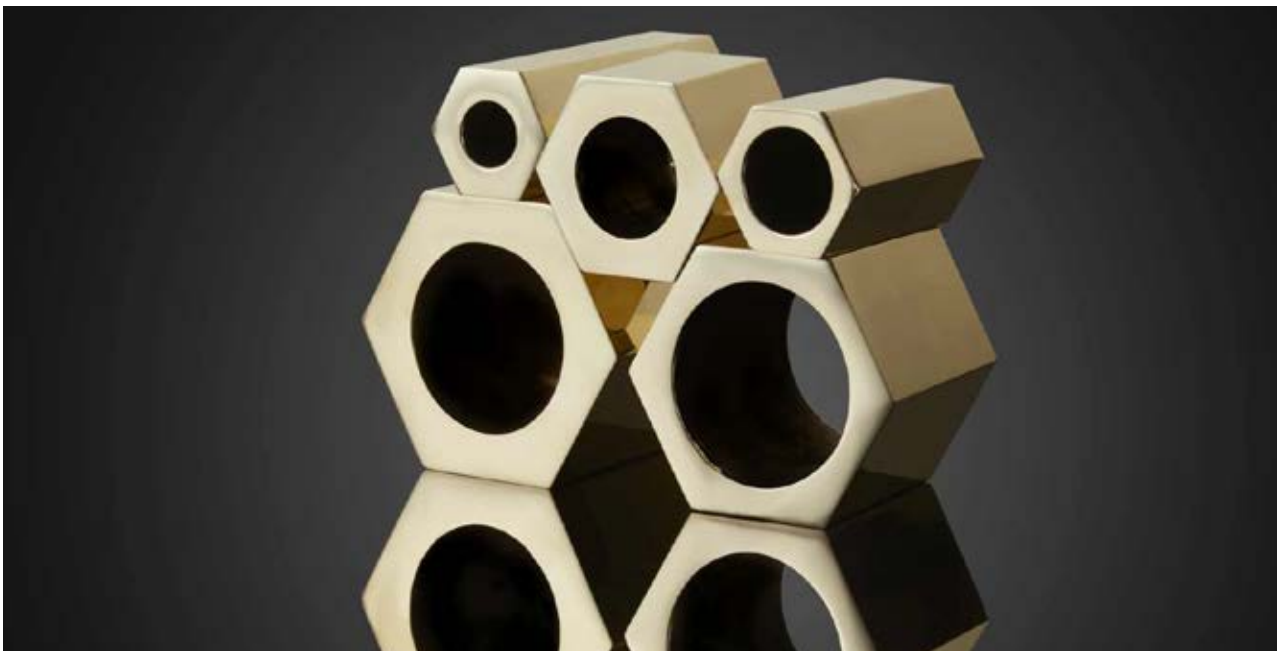

S510 - S510DW

RODS / HOLLOW RODS

CW510L - CuZn42

| Product Code | EN Symbol | EN No | ASTM | | Cu | Zn | Pb | Sn | Fe | Ni | Al | Si | Others Total |
|--------------|-----------|-----------|--------|---------|------|------|-----|-----|-----|-----|------|------|--------------|
| S510 | CuZn42 | CW510L | C28500 | Min (%) | 57,0 | Rem. | - | - | - | - | - | - | - |
| | | | | Max (%) | 59,0 | Rem. | 0,2 | 0,3 | 0,3 | 0,3 | 0,05 | - | 0,2 |
| (*) S510DW | CuZn42-DW | CW510L-DW | C28500 | Min (%) | 57,0 | Rem. | - | - | - | - | - | - | - |
| | | | | Max (%) | 59,0 | Rem. | 0,2 | 0,3 | 0,3 | 0,2 | 0,05 | 0,02 | 0,2 |

(*) Each of the other elements < 0,02 %

Features And Applications

Chips and parts can be mixed with MS58 group alloys. Also this alloy compliance with RoHS II and REACH directives. CW510L-DW alloy be used suitable for 4MS vs UBA list for drinking water applications.

4MS and UBA Hygienic list group for CW510L-DW alloy: B, C, D

Area of Usage

Construction, automotive, gas, food, health, aviation, electrical, electronics, plumbing, drinking water products, accessories and fittings. Also this alloy suitable for drinking water application in USA and Canada Markets because of the lead content below 0.2%.

TECHNICAL SPECIFICATIONS


| | | | |
|-----------------------------|--------------------------|-----------------------|------------|
| Structure | $\alpha+\beta$ | Hot Forming | 650-750 °C |
| Machinability | % 70 | Soft Annealing | 450-550 °C |
| Density | 8,37 g/cm ³ | Soft Annealing Time | 1-3 hours |
| Electrical Conductivity | 18 MS/m, 31 %IACS | Stress Relieving | 250-350 °C |
| Thermal Conductivity | 139 W/(m·K) | Stress Relieving Time | 1-3 hours |
| Elasticity Module | 85 kN/mm ² | | |
| Coeff. of Thermal Expansion | 21,7 10 ⁻⁶ /K | | |
| Melting Point | 870-900 °C | | |

Range of Products

S510L and S510L-DW alloys can be produced in our extrusion and cold drawing unit as rods, hollows and profiles suitable for both forging and machining. Please contact us for other technical informations.

| INDICATIVE SHAPED ENDS DIMENSIONS | | | | | |
|-----------------------------------|---------------------|-----------------------------|----------|---------------------------|----------|
| Nominal Diameter or Width | | Type A - Chamfer Length (L) | | Type B - Point Length (L) | |
| Across-flats (mm) | | Min (mm) | Max (mm) | Min (mm) | Max (mm) |
| Over | Up to and including | | | | |
| 5 | 10 | 0,2 | 1,5 | 2 | 7 |
| 10 | 20 | 0,2 | 2 | 3 | 10 |
| 20 | 30 | 0,2 | 3 | 4 | 12 |

Unless otherwise specified by the buyer, the shape of the ends of products larger than 30 mm is up to the supplier.

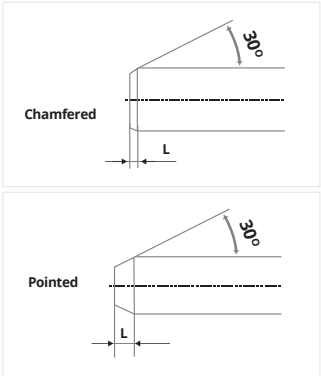

| Nominal Diameter or Width Across-flats (mm) | | Preferred (available) Lengths (mm) | Tolerance on Length (mm) |
|--|---------------------|---------------------------------------|-----------------------------|
| Over | Up to and including | | |
| 6 Inc. | 30 | 3.000 - 4.000 | ±50 |
| 30 | 80 | 3.000 - 4.000 | ±100 |

Stress Relieving The polygonal rods and hollow rods are subjected to stress relieving treatment

Packaging 500 or 1000 kg bundle - 3/5 metal straps different bundle packagings, up to 10 mm dimension products are packed with wooden case

EN 12164 - Rods for Free Machining

| Material Condition | Nominal Diameter (mm) | | Width Across-flats (mm) | | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation | | | Hardness (HBW) | | |
|-----------------------|-----------------------------|-------------------|-------------------------------|-------------------|---|--|-----|----------------------------------|---------------------------------|-----------------|-------------------|-----|--|
| | Over | Up to and inc. | Over | Up to and inc. | | Min | Max | A _{100mm} (%) Min | A _{11,3} (%) Min | A (%) Min | Min | Max | |
| M | All | | All | | As manufactured | | | | | | | | |
| R360 | 6 | 80 | 6 | 55 | 360 | - | 320 | - | 15 | 20 | - | - | |
| H090 | 6 | 80 | 6 | 55 | - | - | - | - | - | - | 90 | 125 | |
| R430 | 6 | 40 | 6 | 35 | 430 | 220 | - | 6 | 8 | 10 | - | - | |
| H110 | 6 | 40 | 6 | 35 | - | - | - | - | - | - | 110 | 160 | |
| R500 | 6 | 14 | 6 | 10 | 500 | 350 | - | - | 3 | 5 | - | - | |
| H135 | 6 | 14 | 6 | 10 | - | - | - | - | - | - | 135 | - | |

EN 12168 - Hollow Rods for Free Machining

| Material Condition | Wall Thickness (mm) | | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation A (%) Min | Hardness (HBW) | | Hardness (HV) | |
|-----------------------|------------------------|-------------------|---|--|-----|-------------------------------|-------------------|-----|------------------|-----|
| | Over | Up to and inc. | | Min | Max | | Min | Max | Min | Max |
| M | All | | As manufactured | | | | | | | |
| R360 | 3 | 40 | 360 | - | 320 | 20 | - | - | - | - |
| H090 | 3 | 40 | - | - | - | - | 90 | 125 | 100 | 135 |
| R430 | 3 | 15 | 430 | 220 | - | 10 | - | - | - | - |
| H110 | 3 | 15 | - | - | - | - | 110 | 160 | 120 | 170 |
| R500 | 3 | 7 | 500 | 350 | - | 8 | - | - | - | - |
| H135 | 3 | 7 | - | - | - | - | 135 | - | 145 | - |

EN 12165 - Wrought and Unwrought Forging Stocks

| Material Condition | Nominal Diameter (mm) | | Hardness (HBW) | |
|-----------------------|--------------------------|---------------------|-------------------|-----|
| | Over | Up to and including | Min | Max |
| M | All | | As manufactured | |
| H090 | 8 | 80 | 90 | 125 |

| STANDARD | | EN 12164 | | | EN 12165 | | EN 12168 | | | | | |
|-----------------|--------------|------------|-------------|-------------------|-----------|---------|---|------------|------------|----------------------|---------|---------------------|
| Dimension Range | | Round Rod | | Hexagonal, Square | Round Rod | | Round and Hexagonal Hollow Rod, Outer Dim. Tol. | | | Hole Tolerance Round | | Hole Tol. Hexagonal |
| Over | Up to & inc. | Class A | Class B | Rod | Class A | Class B | Class A | Class B | Class C | Class A | Class B | - |
| 5 | 6 | 0 -0,05 | 0 -0,03 | 0 -0,08 | - | - | - | - | - | - | - | - |
| 6 | 10 | 0 -0,06 | 0 -0,036 | 0 -0,09 | ±0,25 | ±0,14 | - | - | - | - | - | - |
| 10 | 13 | 0 -0,07 | 0 -0,43 | 0 -0,11 | ±0,25 | ±0,14 | - | - | - | - | - | - |
| 13 | 18 | 0 -0,07 | 0 -0,43 | 0 -0,11 | ±0,25 | ±0,14 | - | - | - | ±0,35 | - | +0,70 -0 |
| | 20 | 0 -0,08 | 0 -0,52 | 0 -0,13 | ±0,30 | ±0,17 | - | - | - | ±0,42 | - | +0,84 -0 |
| 20 | 23 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | - | - | ±0,42 | ±0,17 | +0,84 -0 |
| 23 | 26 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | 0 -0,21 | - | ±0,42 | ±0,17 | +0,84 -0 |
| 26 | 30 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | 0 -0,21 | 0 -0,13 | ±0,42 | ±0,17 | +0,84 -0 |
| 30 | 50 | 0 -0,16 | - | 0 -0,16 | ±0,60 | ±0,20 | - | 0 -0,25 | 0 -0,16 | ±0,80 | ±0,20 | +1,6 -0 |
| 50 | 55 | 0 -0,19 | - | 0 -0,19 | ±0,70 | ±0,37 | - | 0 -0,46 | 0 -0,30 | ±0,95 | ±0,37 | - |
| 55 | 65 | 0 -0,19 | - | - | ±0,70 | ±0,37 | ±0,60 | 0 -0,46 | 0 -0,30 | ±0,95 | - | - |
| 65 | 80 | 0 -0,19 | - | - | ±0,70 | ±0,37 | ±0,60 | 0 -0,46 | 0 -0,30 | ±0,95 | - | - |
| 80 | 120 | - | - | - | ±2 | - | - | - | - | - | - | - |
| 120 | 140 | - | - | - | ±2,5 | - | - | - | - | - | - | - |

For Hollow Rods

Minimum wall thickness is 3 mm. Eccentricity : %10 (max.)

Outer Cold Drawn - Internal Extruded

Outer Class B - Hole Class A tolerance

Inner-Outer Cold Drawn

Outer Class C - Hole Class B tolerance

Inner-Outer Extruded

Outer Class A - Hole Class A tolerance



S509 - S509DW

RODS / HOLLOW RODS

CW509L - CuZn40

| Product Code | EN Symbol | EN No | ASTM | | Cu | Zn | Pb | Sn | Fe | Ni | Al | Si | Others Total |
|--------------|-----------|-----------|--------|---------|------|------|-----|-----|-----|-----|------|------|--------------|
| S509 | CuZn40 | CW509L | C27450 | Min (%) | 59,0 | Rem. | - | - | - | - | - | - | - |
| | | | | Max (%) | 61,5 | Rem. | 0,2 | 0,2 | 0,2 | 0,3 | 0,05 | - | 0,2 |
| (*) S509DW | CuZn40-DW | CW509L-DW | C27450 | Min (%) | 59,5 | Rem. | - | - | - | - | - | - | - |
| | | | | Max (%) | 61,5 | Rem. | 0,2 | 0,2 | 0,2 | 0,2 | 0,05 | 0,02 | 0,2 |

(*) Each of the other elements < 0,02 %

Features And Applications

Chips and parts can be mixed with MS58 group alloys. Also this alloy compliance with RoHS II and REACH directives. CW509L-DW alloy be used suitable for 4MS vs UBA list for drinking water applications.

4MS and UBA Hygienic list group for CW509L-DW alloy: B, C, D

Area of Usage

Construction, automotive, gas, food, health, aviation, electrical, electronics, plumbing, drinking water products, accessories and fittings. Also this alloy suitable for drinking water application in USA and Canada Markets because of the lead content below 0.2%.

TECHNICAL SPECIFICATIONS

| | | | |
|-----------------------------|--------------------------|-----------------------|------------|
| Structure | $\alpha+\beta$ | Hot Forming | 650-750 °C |
| Machinability | % 50 | Soft Annealing | 450-550 °C |
| Density | 8,4 g/cm ³ | Soft Annealing Time | 1-3 hours |
| Electrical Conductivity | 28 %IACS | Stress Relieving | 200-250 °C |
| Thermal Conductivity | 122 W/(m·K) | Stress Relieving Time | 1-3 hours |
| Elasticity Module | 105 GPa | | |
| Coeff. of Thermal Expansion | 20,8 10 ⁻⁶ /K | | |
| Melting Point | 880-910 °C | | |


Range of Products

S509L and S509L-DW alloys can be produced in our extrusion and cold drawing unit as rods, hollows and profiles suitable for both forging and machining. Please contact us for other technical informations.

INDICATIVE SHAPED ENDS DIMENSIONS

| Nominal Diameter or Width | | Type A - Chamfer Length (L) | | Type B - Point Length (L) | |
|---------------------------|---------------------|-----------------------------|----------|---------------------------|----------|
| Across-flats (mm) | | Min (mm) | Max (mm) | Min (mm) | Max (mm) |
| Over | Up to and including | | | | |
| - | 10 | 0,2 | 1,5 | 2 | 7 |
| 10 | 20 | 0,2 | 2 | 3 | 10 |
| 20 | 30 | 0,2 | 3 | 4 | 12 |

Unless otherwise specified by the buyer, the shape of the ends of products larger than 30 mm is up to the supplier.

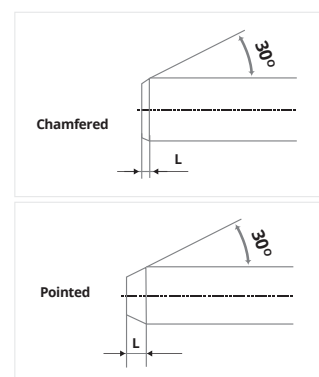

| Nominal Diameter or Width Across-flats (mm) | | Preferred (available) Lengths (mm) | Tolerance on Length (mm) |
|--|---------------------|---------------------------------------|-----------------------------|
| Over | Up to and including | | |
| 10 ^{inc.} | 30 | 3.000 - 4.000 | ±50 |
| 30 | 80 | 3.000 - 4.000 | ±100 |

Stress Relieving The polygonal rods and hollow rods are subjected to stress relieving treatment

Packaging 500 or 1000 kg bundle - 3/5 metal straps different bundle packagings, up to 10 mm dimension products are packed with wooden case

EN 12164 - Rods for Free Machining

| Material Condition | Nominal Diameter (mm) | | Width Across-flats (mm) | | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation | | | Hardness (HBW) | |
|--------------------|-----------------------|----------------|-------------------------|----------------|--|--|-----|------------------------|-----------------------|-------|----------------|-----|
| | Over | Up to and inc. | Over | Up to and inc. | | Min | Max | A _{100mm} (%) | A _{11,3} (%) | A (%) | Min | Max |
| M | All | | All | | As manufactured | | | | | | | |
| R360 | 10 | 80 | 10 | 55 | 360 | - | 300 | - | 15 | 20 | - | - |
| H070 | 10 | 80 | 10 | 55 | - | - | - | - | - | - | 70 | 100 |
| R410 | 10 | 40 | 10 | 35 | 410 | 230 | - | 8 | 10 | 12 | - | - |
| H100 | 10 | 40 | 10 | 35 | - | - | - | - | - | - | 100 | 145 |
| R500 | 10 | 14 | 10 | 10 | 500 | 350 | - | 3 | 5 | 8 | - | - |
| H120 | 10 | 14 | 10 | 10 | - | - | - | - | - | - | 120 | - |

EN 12168 - Hollow Rods for Free Machining

| Material Condition | Wall Thickness (mm) | | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation A (%) Min | Hardness (HBW) | | Hardness (HV) | |
|--------------------|---------------------|----------------|--|--|-----|-------------------------|----------------|-----|---------------|-----|
| | Over | Up to and inc. | | Min | Max | | Min | Max | Min | Max |
| M | All | | As manufactured | | | | | | | |
| R360 | 4 | 20 | 360 | - | 300 | 20 | - | - | - | - |
| H070 | 4 | 20 | - | - | - | - | 70 | 100 | 80 | 110 |
| R410 | 4 | 10 | 410 | 250 | - | 12 | - | - | - | - |
| H100 | 4 | 10 | - | - | - | - | 100 | 145 | 110 | 155 |
| R500 | 4 | 7 | 500 | 350 | - | 8 | - | - | - | - |
| H120 | 4 | 7 | - | - | - | - | 120 | - | 130 | - |

EN 12165 - Wrought and Unwrought Forging Stocks

| Material Condition | Nominal Diameter (mm) | | Hardness (HBW) | |
|--------------------|-----------------------|---------------------|-----------------|-----|
| | Over | Up to and including | Min | Max |
| M | All | | As manufactured | |
| H070 | 8 | 80 | 70 | 100 |

| STANDARD | | EN 12164 | | | EN 12165 | | EN 12168 | | | | | |
|-----------------|--------------|------------|-------------|-------------------|-----------|---------|---|------------|------------|----------------------|---------|---------------------|
| Dimension Range | | Round Rod | | Hexagonal, Square | Round Rod | | Round and Hexagonal Hollow Rod, Outer Dim. Tol. | | | Hole Tolerance Round | | Hole Tol. Hexagonal |
| Over | Up to & inc. | Class A | Class B | Rod | Class A | Class B | Class A | Class B | Class C | Class A | Class B | - |
| - | 10 | 0 -0,06 | 0 -0,036 | 0 -0,09 | ±0,25 | ±0,14 | - | - | - | - | - | - |
| 10 | 13 | 0 -0,07 | 0 -0,043 | 0 -0,11 | ±0,25 | ±0,14 | - | - | - | - | - | - |
| 13 | 18 | 0 -0,07 | 0 -0,043 | 0 -0,11 | ±0,25 | ±0,14 | - | - | - | ±0,35 | - | +0,70 -0 |
| 18 | 20 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | - | - | ±0,42 | - | +0,84 -0 |
| 20 | 23 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | - | - | ±0,42 | ±0,17 | +0,84 -0 |
| 23 | 26 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | 0 -0,21 | - | ±0,42 | ±0,17 | +0,84 -0 |
| 26 | 30 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | 0 -0,21 | 0 -0,13 | ±0,42 | ±0,17 | +0,84 -0 |
| 30 | 50 | 0 -0,16 | - | 0 -0,16 | ±0,60 | ±0,20 | - | 0 -0,25 | 0 -0,16 | ±0,80 | ±0,20 | +1,6 -0 |
| 50 | 55 | 0 -0,19 | - | 0 -0,019 | ±0,70 | ±0,37 | - | 0 -0,46 | 0 -0,30 | ±0,95 | ±0,37 | - |
| 55 | 65 | 0 -0,19 | - | - | ±0,70 | ±0,37 | ±0,60 | 0 -0,46 | 0 -0,30 | ±0,95 | - | - |
| 65 | 80 | 0 -0,19 | - | - | ±0,70 | ±0,37 | ±0,60 | 0 -0,46 | 0 -0,30 | ±0,95 | - | - |
| 80 | 120 | - | - | - | ±2 | - | - | - | - | - | - | - |
| 120 | 140 | - | - | - | ±2,5 | - | - | - | - | - | - | - |

For Hollow Rods

Minimum wall thickness is 3-4 mm. Eccentricity : %10 (max.)

Outer Cold Drawn - Internal Extruded

Outer Class B - Hole Class A tolerance

Inner-Outer Cold Drawn

Outer Class C - Hole Class B tolerance

Inner-Outer Extruded

Outer Class A - Hole Class A tolerance



S709

RODS / HOLLOW RODS

CW709R - CuZn32Pb2AsFeSi

| Product Code | EN Symbol | EN No | ASTM | | Cu | Zn | Pb | Sn | Fe | Ni | Al | Si | As | Others Total |
|--------------|-----------------|--------|------|---------|------|------|-----|-----|-----|-----|------|------|------|--------------|
| S709 | CuZn32Pb2AsFeSi | CW709R | - | Min (%) | 64,0 | Rem. | 1,5 | - | 0,1 | - | - | 0,45 | 0,03 | - |
| | | | | Max (%) | 66,5 | Rem. | 2,2 | 0,3 | 0,2 | 0,3 | 0,05 | 0,8 | 0,08 | 0,2 |

Features And Applications

Due to its good resistance to dezincification, it is preferred in the manufacture of parts which come in contact with water. Also this alloy compliance with RoHS II and REACH directives.

Area of Usage

Fitting parts used in aggressive (corrosive) water.

TECHNICAL SPECIFICATIONS

| | | | |
|-----------------------------|------------------------|-------------------------------|------------|
| Structure | $\alpha+\beta$ | Hot Forming | 700-830 °C |
| Machinability | % 85 | Soft Annealing | 500-600 °C |
| Density | 8,48 g/cm ³ | Soft Annealing Time | 1-3 hours |
| Electrical Conductivity | 13,4 %IACS | Stress Relieving | 300-400 °C |
| Thermal Conductivity | 65 W/(m·K) | Stress Relieving Time | 1-3 hours |
| Elasticity Module | 109 GPa | Max. Depth of Dezincification | <100 μm |
| Coeff. of Thermal Expansion | 21 10 ⁻⁶ /K | | |
| Melting Point | 910-940 °C | | |



Range of Products

S709 alloy can be produced in our extrusion and cold drawing unit as rods, hollows and profiles suitable for both forging and machining. Please contact us for other technical informations.

INDICATIVE SHAPED ENDS DIMENSIONS

| Nominal Diameter or Width | | Type A - Chamfer Length (L) | | Type B - Point Length (L) | |
|---------------------------|---------------------|-----------------------------|----------|---------------------------|----------|
| Across-flats (mm) | | Min (mm) | Max (mm) | Min (mm) | Max (mm) |
| Over | Up to and including | | | | |
| 8 Inc. | 10 | 0,2 | 1,5 | 2 | 7 |
| 10 | 20 | 0,2 | 2 | 3 | 10 |
| 20 | 30 | 0,2 | 3 | 4 | 12 |

Unless otherwise specified by the buyer, the shape of the ends of products larger than 30 mm is up to the supplier.

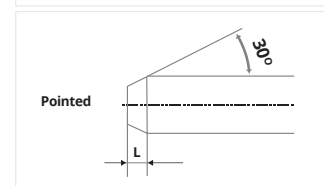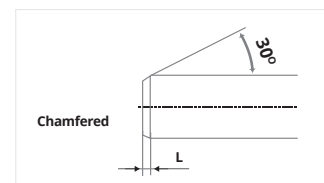

| Nominal Diameter or Width Across-flats (mm) | | Preferred (available) Lengths (mm) | Tolerance on Length (mm) |
|--|---------------------|---------------------------------------|-----------------------------|
| Over | Up to and including | | |
| 8 ^{Inc.} | 30 | 3.000 - 4.000 | ±50 |
| 30 | 80 | 3.000 - 4.000 | ±100 |

Stress Relieving The polygonal rods and hollow rods are subjected to stress relieving treatment

Packaging 500 or 1000 kg bundle - 3/5 metal straps different bundle packagings, up to 10 mm dimension products are packed with wooden case

EN 12164 - Rods for Free Machining

| Material Condition | Nominal Diameter (mm) | | Width Across-flats (mm) | | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation | | | Hardness (HBW) | |
|--------------------|-----------------------|----------------|-------------------------|----------------|--|---|-----|------------------------|-----------------------|-------|----------------|-----|
| | Over | Up to and inc. | Over | Up to and inc. | | Min | Max | A _{100mm} (%) | A _{11,3} (%) | A (%) | Min | Max |
| M | All | | All | | As manufactured | | | | | | | |
| R380 | 8 | 40 | 8 | 40 | 380 | 220 | - | - | 15 | 20 | 110 | 160 |
| R430 | 8 | 40 | 8 | 40 | 430 | 280 | - | - | 12 | 15 | 120 | 170 |

EN 12168 - Hollow Rods for Free Machining

| Material Condition | Wall Thickness (mm) | | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation A (%) Min | Hardness (HBW) | | Hardness (HV) | |
|--------------------|---------------------|----------------|--|---|-----|----------------------------|----------------|-----|---------------|-----|
| | Over | Up to and inc. | | Min | Max | | Min | Max | Min | Max |
| M | All | | As manufactured | | | | | | | |
| R380 | 4 | 15 | 380 | 220 | - | 20 | - | - | - | - |
| H110 | 4 | 15 | - | - | - | - | 110 | 150 | 120 | 160 |
| R430 | 4 | 10 | 430 | 260 | - | 15 | - | - | - | - |
| H120 | 4 | 10 | - | - | - | - | 120 | 170 | 130 | 180 |

EN 12165 - Wrought and Unwrought Forging Stocks

| Material Condition | Nominal Diameter (mm) | | Hardness (HBW) | |
|--------------------|-----------------------|---------------------|-----------------|-----|
| | Over | Up to and including | Min | Max |
| M | All | | As manufactured | |
| H090 | 8 | 80 | 90 | 170 |

| STANDARD | | EN 12164 | | | EN 12165 | | EN 12168 | | | |
|-----------------|--------------|------------|-------------|-------------------|-----------|---------|---|------------|----------------------|---------------------|
| Dimension Range | | Round Rod | | Hexagonal, Square | Round Rod | | Round and Hexagonal Hollow Rod, Outer Dim. Tol. | | Hole Tolerance Round | Hole Tol. Hexagonal |
| Over | Up to & inc. | Class A | Class B | Rod | Class A | Class B | Class A | Class B | Class A | - |
| 8 | 10 | 0 -0,06 | 0 -0,036 | 0 -0,09 | ±0,25 | ±0,14 | - | - | - | - |
| 10 | 13 | 0 -0,07 | 0 -0,043 | 0 -0,11 | ±0,25 | ±0,14 | - | - | - | - |
| 13 | 18 | 0 -0,07 | 0 -0,043 | 0 -0,11 | ±0,25 | ±0,14 | - | - | ±0,35 | +0,70 -0 |
| 18 | 20 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | - | ±0,42 | +0,84 -0 |
| 20 | 23 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | - | ±0,42 | +0,84 -0 |
| 23 | 26 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | 0 -0,21 | ±0,42 | +0,84 -0 |
| 26 | 30 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | 0 -0,21 | ±0,42 | +0,84 -0 |
| 30 | 50 | 0 -0,16 | - | 0 -0,16 | ±0,60 | ±0,20 | - | 0 -0,25 | ±0,80 | +1,6 -0 |
| 50 | 55 | 0 -0,19 | - | 0 -0,19 | ±0,70 | ±0,37 | - | 0 -0,46 | ±0,95 | - |
| 55 | 65 | 0 -0,19 | - | - | ±0,70 | ±0,37 | ±0,60 | 0 -0,46 | ±0,95 | - |
| 65 | 80 | 0 -0,19 | - | - | ±0,70 | ±0,37 | ±0,60 | 0 -0,46 | ±0,95 | - |
| 80 | 120 | - | - | - | ±2 | - | - | - | - | - |
| 120 | 140 | - | - | - | ±2,5 | - | - | - | - | - |

For Hollow Rods


Minimum wall thickness is 4 mm. Eccentricity : %10 (max.)

Outer Cold Drawn - Internal Extruded

Outer Class B - Hole Class A tolerance

Inner-Outer Extruded

Outer Class A - Hole Class A tolerance

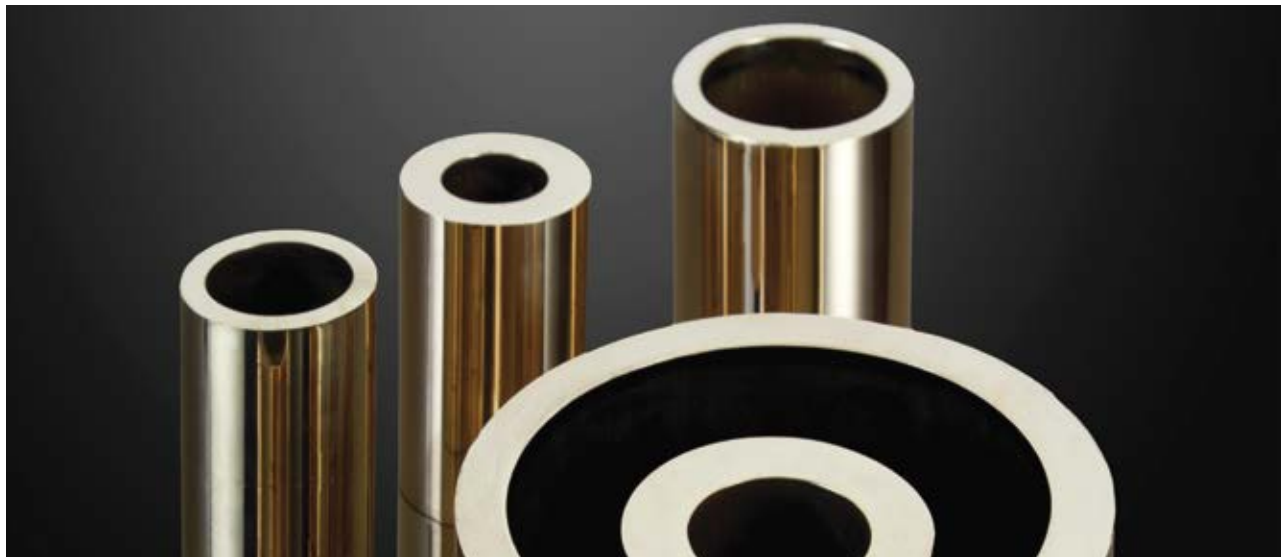

S713

RODS / HOLLOW RODS

CW713R - CuZn37Mn3Al2PbSi

| Product Code | EN Symbol | EN No | ASTM | | Cu | Zn | Pb | Sn | Fe | Ni | Al | Si | Mn | Others Total |
|--------------|------------------|--------|--------|---------|------|------|-----|-----|-----|-----|-----|-----|-----|--------------|
| S713 | CuZn37Mn3Al2PbSi | CW713R | C67420 | Min (%) | 57,0 | Rem. | 0,2 | - | - | - | 1,3 | 0,3 | 1,5 | - |
| | | | | Max (%) | 59,0 | Rem. | 0,8 | 0,3 | 1,0 | 1,0 | 2,3 | 1,3 | 3,0 | 0,3 |

Features And Applications

CW713R alloy has high mechanical properties, good resistance to wear under heavy loads stable, resistant to atmospheric agents. Also this alloy compliance with RoHS II and REACH directives.

Area of Usage

Bearings for high loads, sliding parts, valves, pistons and guides.

TECHNICAL SPECIFICATIONS

| | | | |
|-----------------------------|--------------------------|-----------------------|------------|
| Structure | β | Hot Forming | 600-700 °C |
| Machinability | % 50 | Soft Annealing | 500-650 °C |
| Density | 8,12 g/cm ³ | Soft Annealing Time | 1-3 hours |
| Electrical Conductivity | 7,8 MS/m, 13,4 %IACS | Stress Relieving | 250-400 °C |
| Thermal Conductivity | 63 W/(m·K) | Stress Relieving Time | 1-3 hours |
| Elasticity Module | 93 GPa | | |
| Coeff. of Thermal Expansion | 20,3 10 ⁻⁶ /K | | |
| Melting Point | 875-910 °C | | |



Range of Products

S713 alloy can be produced in our extrusion and cold drawing unit as rods, hollows and profiles suitable for both forging and machining. Please contact us for other technical informations.

INDICATIVE SHAPED ENDS DIMENSIONS

| Nominal Diameter or Width | | Type A – Chamfer Length (L) | | Type B – Point Length (L) | |
|---------------------------|---------------------|-----------------------------|----------|---------------------------|----------|
| Across-flats (mm) | | Min (mm) | Max (mm) | Min (mm) | Max (mm) |
| Over | Up to and including | | | | |
| 8 Inc. | 10 | 0,2 | 1,5 | 2 | 7 |
| 10 | 20 | 0,2 | 2 | 3 | 10 |
| 20 | 30 | 0,2 | 3 | 4 | 12 |

Unless otherwise specified by the buyer, the shape of the ends of products larger than 30 mm is up to the supplier.

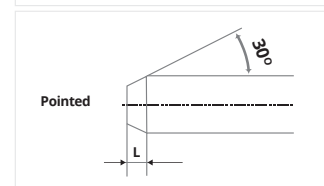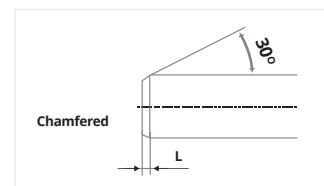

| Nominal Diameter or Width Across-flats (mm) | | Preferred (available) Lengths (mm) | Tolerance on Length (mm) |
|--|---------------------|---------------------------------------|-----------------------------|
| Over | Up to and including | | |
| 8 ^{Inc} | 30 | 3.000 - 4.000 | ±50 |
| 30 | 80 | 3.000 - 4.000 | ±100 |

Stress Relieving The polygonal rods and hollow rods are subjected to stress relieving treatment

Packaging 500 or 1000 kg bundle – 3/5 metal straps different bundle packagings, up to 10 mm dimension products are packed with wooden case

EN 12164 - Rods for Free Machining

| Material Condition | Nominal Diameter (mm) | | Width Across-flats (mm) | | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation | | | Hardness (HBW) | |
|-----------------------|-----------------------------|-------------------|-------------------------------|-------------------|---|--|-----|---------------------------|--------------------------|----------|-------------------|-----|
| | Over | Up to and inc. | Over | Up to and inc. | | Min | Max | A _{100mm} (%) | A _{11,3} (%) | A (%) | Min | Max |
| M | All | | All | | As manufactured | | | | | | | |
| R540 | 8 | 80 | 8 | 55 | 540 | 280 | - | - | 12 | 15 | - | - |
| H130 | 8 | 80 | 8 | 55 | - | - | - | - | - | - | 130 | 170 |
| R590 | 8 | 50 | 8 | 40 | 590 | 370 | - | - | 8 | 10 | - | - |
| H150 | 8 | 50 | 8 | 40 | - | - | - | - | - | - | 150 | 220 |

EN 12168 - Hollow Rods for Free Machining

| Material Condition | Wall Thickness (mm) | | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) | | Elongation A (%) Min | Hardness (HBW) | | Hardness (HV) | |
|-----------------------|------------------------|-------------------|---|--|-----|-------------------------------|-------------------|-----|------------------|-----|
| | Over | Up to and inc. | | Min | Max | | Min | Max | Min | Max |
| M | All | | As manufactured | | | | | | | |
| R540 | 10 | 30 | 540 | 280 | - | 15 | - | - | - | - |
| H130 | 10 | 30 | - | - | - | - | 130 | 170 | 140 | 180 |
| R590 | 5 | 10 | 590 | 320 | - | 10 | - | - | - | - |
| H150 | 5 | 10 | - | - | - | - | 150 | 190 | 160 | 200 |

EN 12165 - Wrought and Unwrought Forging Stocks

| Material Condition | Nominal Diameter (mm) | | Hardness (HBW) | |
|-----------------------|--------------------------|---------------------|-------------------|-----|
| | Over | Up to and including | Min | Max |
| M | All | | As manufactured | |
| H130 | 8 | 80 | 130 | 170 |

| STANDARD | | EN 12164 | | | EN 12165 | | EN 12168 | | | |
|-----------------|--------------|------------|-------------|-------------------|-----------|---------|---|------------|----------------------|---------------------|
| Dimension Range | | Round Rod | | Hexagonal, Square | Round Rod | | Round and Hexagonal Hollow Rod, Outer Dim. Tol. | | Hole Tolerance Round | Hole Tol. Hexagonal |
| Over | Up to & inc. | Class A | Class B | Rod | Class A | Class B | Class A | Class B | Class A | - |
| 8 | 10 | 0 -0,06 | 0 -0,036 | 0 -0,09 | ±0,25 | ±0,14 | - | - | - | - |
| 10 | 13 | 0 -0,07 | 0 -0,043 | 0 -0,11 | ±0,25 | ±0,14 | - | - | - | - |
| 13 | 18 | 0 -0,07 | 0 -0,043 | 0 -0,11 | ±0,25 | ±0,14 | - | - | ±0,35 | +0,70 -0 |
| 18 | 20 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | - | ±0,42 | +0,84 -0 |
| 20 | 23 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | - | ±0,42 | +0,84 -0 |
| 23 | 26 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | 0 -0,21 | ±0,42 | +0,84 -0 |
| 26 | 30 | 0 -0,08 | 0 -0,052 | 0 -0,13 | ±0,30 | ±0,17 | - | 0 -0,21 | ±0,42 | +0,84 -0 |
| 30 | 50 | 0 -0,16 | - | 0 -0,16 | ±0,60 | ±0,20 | - | 0 -0,25 | ±0,80 | +1,6 -0 |
| 50 | 55 | 0 -0,19 | - | 0 -0,19 | ±0,70 | ±0,37 | ±0,60 | 0 -0,46 | ±0,95 | - |
| 55 | 65 | 0 -0,19 | - | - | ±0,70 | ±0,37 | ±0,60 | 0 -0,46 | ±0,95 | - |
| 65 | 80 | 0 -0,19 | - | - | ±0,70 | ±0,37 | - | 0 -0,46 | ±0,95 | - |
| 80 | 120 | - | - | - | ±2 | - | - | - | - | - |
| 120 | 140 | - | - | - | ±2,5 | - | - | - | - | - |

For Hollow Rods

Minimum wall thickness is 4 mm. Eccentricity : %10 (max.)

Outer Cold Drawn - Internal Extruded

Outer Class B - Hole Class A tolerance

Inner-Outer Extruded

Outer Class A - Hole Class A tolerance



LOW PRESSURE CONTINUOUS CASTING INGOTS

CC757S - CuZn39Pb1Al-C

CC757S - CuZn39Pb2Al-C

| Product Code | EN Symbol | ASTM | | Cu | Zn | Pb | Sn | Fe | Ni | Al | Mn | Si |
|-------------------------------|---------------|--------|-------|------|------|-----|-----|-----|-----|-----|------|------|
| Low Pressure Ingots CC757S | CuZn39Pb2Al-C | C85700 | Min % | 58,0 | Rem. | 0,2 | - | - | - | 0,3 | - | - |
| | | | Max % | 63,0 | Rem. | 1,4 | 0,5 | 0,3 | 0,2 | 0,9 | 0,05 | 0,05 |

Each of the other elements < 0,02 %

Material Properties and Typical Applications

The Low Pressure Ingots, completely manufactured from raw material, has excellent microstructure and polishability.

The ingots are shipped in euro pallets between 1 and 2 tons.

ROHS II complies with the REACH directives. 4MS and UBA material restriction group: B, C, D

Different norm and alloy demands that come from our customers are examined and produced by the relevant units.

Areas of Usage

* Low Pressure ingots is used in the production of tap water depending on the metallurgical properties.

APPLICABLE STANDARDS

| | |
|-------------|---|
| EN-1982 | Standard for brass and copper alloys, ingots and casts. |
| DIN 50930-6 | Standard for brass materials used areas contacting drinking water. |
| UBA List | The list for brass materials used in drinking water published by German Federal Environment Agency. |
| 4MS | Committee regulating the national approvals for materials and products contacting drinking water that France, Germany, the Netherlands and United Kingdom are members of. |

| Casting Process and Designation | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) Min | Elongation A (%) Min | Hardness (HBW) Min |
|---------------------------------|--|--|-------------------------------|--------------------------|
| Permanent Mould - GM | 400 | 140 | 15 | 90 |
| Pressure Die Cast - GP | 310 | 270 | 1 | 120 |
| Sand - GS | 300 | 100 | 15 | 70 |

Note: These mechanical properties are valid for casting parts.

STANDARD MEASURES – WEIGHT

| Standard Meter (mm) | Standard Weight (kg) |
|------------------------|-------------------------|
| 64x64x380 | Average 12 |

DEZINCIFICATION-RESISTANT (DZR) CONTINUOUS CASTING INGOTS

CC770S - CuZn36Pb-C

CC770S - CuZn36Pb-C

| Product Code | EN Symbol | ASTM | | Cu | Zn | Pb | Sn | Fe | As | Ni | Al | Mn |
|---|------------|------|-------|------|------|-----|-----|-----|------|-----|-----|-----|
| Dzr Continuous Casting Ingots CC770S | CuZn36Pb-C | - | Min % | 62,0 | Rem. | 0,2 | - | - | 0,04 | - | 0,5 | - |
| | | | Max % | 64,0 | Rem. | 1,6 | 0,3 | 0,3 | 0,14 | 0,2 | 0,7 | 0,1 |

Each of the other elements < 0,02 %

Material Properties and Typical Applications

It is used in the manufacture of water faucets due to dezincification sills, metallographed structures and corrosion resistance.

DZR ingots, produced entirely from original raw material, has excellent polishability.

The ingots are shipped in euro pallets between 1 and 2 tons.

ROHS II complies with the REACH directives. 4MS and UBA material restriction group: B, C, D

Different norm and alloy demands that come from our customers are examined and produced by the relevant units.

Areas of Usage

It is usually used in the manufacture of water watches and water faucet.

APPLICABLE STANDARDS

| | |
|-------------|---|
| EN-1982 | Standard for brass and copper alloys, ingots and casts. |
| DIN 50930-6 | Standard for brass materials used areas contacting drinking water. |
| UBA List | The list for brass materials used in drinking water published by German Federal Environment Agency. |
| 4MS | Committee regulating the national approvals for materials and products contacting drinking water that France, Germany, the Netherlands and United Kingdom are members of. |

| Casting Process and Designation | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) Min | Elongation A (%) Min | Hardness (HBW) Min |
|---------------------------------|--|--|-------------------------------|--------------------------|
| Permanent Mould - GM | 280 | 110 | 10 | 70 |
| Pressure Die Cast - GP | 310 | 270 | 1 | 120 |

Note: These mechanical properties are valid for casting parts.

STANDARD MEASURES – WEIGHT

| Standard Meter (mm) | Standard Weight (kg) |
|------------------------|-------------------------|
| 64x64x380 | Average 12 |

UNLEADED CONTINUOUS CASTING INGOTS

CC773S - CuZn42Al-C

CC773S - CuZn42Al-C

| Product Code | EN Symbol | | Cu | Zn | Pb | Sn | Fe | Ni | Al | Mn | P | Si |
|---------------------------|------------|-------|------|------|-----|-----|-----|------|-----|------|------|------|
| Unleaded Ingots CC773S | CuZn42Al-C | Min % | 57,0 | Rem. | - | - | - | - | 0,1 | - | - | - |
| | | Max % | 59,0 | Rem. | 0,2 | 0,3 | 0,3 | 0,02 | 0,3 | 0,02 | 0,02 | 0,02 |

Each of the other elements < 0,02 %

Material Properties and Typical Applications

Unleaded ingots produced as continuous casting, from the unlead element in traditional drinking armature culverts. They ingots are by unlead the laws of water application. This is why drinking water is used. It is by suitable for use in places. Unleaded ingots produced entirely from raw material. Unleaded ingots, made entirely from original raw material, has excellent polishability.

The ingots are shipped in euro pallets between 1 and 2 tons.

ROHS II complies with the REACH directives. 4MS and UBA material restriction group: B, C, D

Different norm and alloy demands that come from our customers are examined and produced by the relevant units.

Areas of Usage

* It is usually used in the manufacture of water watches and water faucet.

APPLICABLE STANDARDS

| | |
|-------------|---|
| EN-1982 | Standard for brass and copper alloys, ingots and casts. |
| DIN 50930-6 | Standard for brass materials used areas contacting drinking water. |
| UBA List | The list for brass materials used in drinking water published by German Federal Environment Agency. |
| 4MS | Committee regulating the national approvals for materials and products contacting drinking water that France, Germany, the Netherlands and United Kingdom are members of. |

| Casting Process and Designation | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) Min | Elongation A (%) Min | Hardness (HBW) Min |
|---------------------------------|--|--|-------------------------------|--------------------------|
| Permanent Mould - GM | 300 | 120 | 15 | 80 |

Note: These mechanical properties are valid for casting parts.

STANDARD MEASURES - WEIGHT

| Standard Meter (mm) | Standard Weight (kg) |
|------------------------|-------------------------|
| 64x64x380 | Average 12 |

ECOBASS – ECOCAST
CONTINUOUS CASTING
(PATENTED)

CC768S - CuZn21Si3P-C

CC768S - CuZn21Si3P-C

| Product Code | EN Symbol | ASTM | | Cu | Zn | Pb | Sn | Fe | Ni | Al | Mn | P | Si |
|--------------------------------|--------------|--------|-------|------|------|-----|-----|-----|-----|------|------|------|-----|
| Ecocast Unleaded Ingots CC768S | CuZn21Si3P-C | C87850 | Min % | 75,0 | Rem. | - | - | - | - | - | - | 0,02 | 2,7 |
| | | | Max % | 77,0 | Rem. | 0,1 | 0,3 | 0,3 | 0,2 | 0,05 | 0,05 | 0,10 | 3,5 |

Each of the other elements < 0,02 %

Material Properties and Typical Applications

The ecocast ingots, which are produced as continuous castings, are unleaded ingots which is free from the damage of the lead element in traditional armature ingots. The EcoCast alloy, which is produced entirely from raw materials, has excellent pourable properties.

The ingots are shipped in euro pallets between 1 and 2 tons.

ROHS II complies with the REACH directives. 4MS and UBA material restriction group: B, C, D

Different norm and alloy demands that come from our customers are examined and produced by the relevant units.

Areas of Usage

* It is usually used in the manufacture of water watches and water faucet.

APPLICABLE STANDARDS

| | |
|-------------|---|
| EN-1982 | Standard for brass and copper alloys, ingots and casts. |
| DIN 50930-6 | Standard for brass materials used areas contacting drinking water. |
| UBA List | The list for brass materials used in drinking water published by German Federal Environment Agency. |
| 4MS | Committee regulating the national approvals for materials and products contacting drinking water that France, Germany, the Netherlands and United Kingdom are members of. |

| Casting Process and Designation | Tensile Strength R _m N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) Min | Elongation A (%) Min | Hardness (HBW) Min |
|---------------------------------|--|--|-------------------------------|--------------------------|
| Permanent Mould - GM | 460 | 180 | 20 | 100 |
| Sand - GS | 420 | 140 | 20 | 80 |
| Continuous - GC | 420 | 140 | 20 | 80 |

Note: These mechanical properties are valid for casting parts.

STANDARD MEASURES – WEIGHT

| Standard Meter (mm) | Standard Weight (kg) |
|------------------------|-------------------------|
| 64x64x380 | Average 12 |

FEDERALLOY IV - B2 – UNLEADED
CONTINUOUS CASTING INGOTS
(PATENTED)

C89540

FEDERALLOY IV - B2

| Product Code | ASTM | | Cu | Zn | Pb | Sn | Fe | Ni | Al | Bi | Se |
|---------------------------------------|--------|-------|------|------|------|-----|------|-----|------|-----|-----|
| Unleaded Ingots FEDERALLOY IV - B2 | C89540 | Min % | 58,0 | Rem. | - | - | - | - | 0,10 | 0,6 | - |
| | | Max % | 64,0 | Rem. | 0,10 | 1,2 | 0,50 | 1,0 | 0,60 | 1,2 | 0,1 |

Each of the other elements < 0,02 %

Material Properties and Typical Applications

Federalloy ingots, produced as continuous casting, is unleaded ashes which are free from the damage of the lead element in traditional armature ingots. Bismuth is used instead of lead. Fedaralloy ingots, which is produced entirely from raw material, has good crystal structure and excellent polishability. Like leaded equivalents, elongation and inclination guarantee quality testing. Better casting capability at low temperatures provides low cost to the end user.

The ingots are shipped in euro pallets between 1 and 2 tons.

Different norm and alloy demands that come from our customers are examined and produced by the relevant units.

Areas of Usage

- * Generally used in the manufacture of water watches and water faucets
- * USA and Canada are suitable alloys for use in drinking water lines for the market.

APPLICABLE STANDARDS

ASTM

(International American Society of Testing and Materials) A community that develops and publishes technical standards for a wide variety of materials, products and systems.

| Casting Process and Designation | Tensile Strength Rm N/mm ² (MPa) Min | 0,2 % Proof Strength N/mm ² (MPa) Min | Elongation A (%) Min | Hardness (HBW) Min |
|---------------------------------|--|--|-------------------------------|--------------------------|
| Permanent Mould - GM | 350 | 200 | 5 | - |

Note: These mechanical properties are valid for casting parts.

STANDARD MEASURES - WEIGHT

| Standard Meter (mm) | Standard Weight (kg) |
|------------------------|-------------------------|
| 64x64x380 | Average 12 |



Headquarter

Eđitim Mah. Adım Sok. Orjin İş Merkezi No: 10 -18 Kat: 3 Daire No: 39 - 49 34722
Hasanpaşa / Kadıköy / İstanbul / Turkey
T: +90 216 414 45 35 pbx | F: +90 216 414 45 40

Factory

Çerkezköy Organize Sanayi Bölgesi Gazi Osman Paşa Mah. 8.Cad. No: 3 59500
Çerkezköy / Tekirdađ / Turkey
T: +90 282 725 19 60 pbx | F: +90 282 725 19 70

sarbak