

sarbak



TECHNICAL DATA SHEET

CW603N - CuZn36Pb3

S603 - S603DW
RODS / HOLLOW RODS

Product Code	EN Symbol	EN No	ASTM		Cu	Zn	Pb	Sn	Fe	Ni	Al	Si	Others Total
S603	CuZn36Pb3	CW603N	C36000	Min (%)	60,0	Rem.	2,5	-	-	-	-	-	-
				Max (%)	62,0	Rem.	3,5	0,2	0,3	0,3	0,05	-	0,2
(*) S603DW	CuZn36Pb3-DW	CW603N-DW	C36000	Min (%)	60,0	Rem.	2,5	-	-	-	-	-	-
				Max (%)	62,0	Rem.	3,5	0,2	0,3	0,2	0,05	0,02	0,2

(*) Each of the other elements < 0,02 %

Features And Applications

CW603N is standard free machining alloy in USA market and named C36000. Also this alloy compliance with RoHS II and REACH directives. CW603N-DW alloy be used suitable for 4MS vs UBA list for drinking water applications.

4MS and UBA Hygienic list group for CW603N-DW alloy: C and D

Area of Usage

High speed machining parts, screws and nuts.

TECHNICAL SPECIFICATIONS

Structure	$\alpha+\beta$	Hot Forming	700-800 °C
Machinability	% 90	Soft Annealing	450-600 °C
Density	8,5 g/cm ³	Soft Annealing Time	1-3 hours
Electrical Conductivity	13 MS/m, 22 %IACS	Stress Relieving	200-300 °C
Thermal Conductivity	100 W/(m·K)	Max. Depth of Dezincification	1-3 hours
Elasticity Module	102 GPa		
Coeff. of Thermal Expansion	20,6 10 ⁻⁶ /K		
Melting Point	885-900 °C		


Range of Products

S603 and S603-DW alloys can be produced in our extrusion and cold drawing unit as rods, hollows and profiles suitable for both forging and machining. Please contact us for other technical informations.

INDICATIVE SHAPED ENDS DIMENSIONS

Nominal Diameter or Width		Type A - Chamfer Length(L)		Type B - Point Length(L)	
Across-flats (mm)		Min (mm)	Max (mm)	Min (mm)	Max (mm)
Over	Up to and including				
-	10	0,2	1,5	2	7
10	20	0,2	2	3	10
20	30	0,2	3	4	12

Unless otherwise specified by the buyer, the shape of the ends of products larger than 30 mm is up to the supplier.

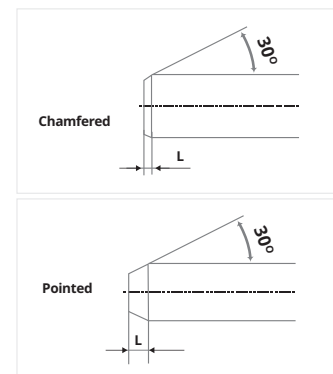

Nominal Diameter or Width Across-flats (mm)		Preferred (available) Lengths (mm)	Tolerance on Length (mm)
Over	Up to and including		
10 ^{inc.}	30	3.000 - 4.000	±50
30	65	3.000 - 4.000	±100

Stress Relieving The polygonal rods and hollow rods are subjected to stress relieving treatment

Packaging 500 or 1000 kg bundle – 3/5 metal straps different bundle packagings, up to 10 mm dimension products are packed with wooden case

EN 12164 - Rods for Free Machining

Material Condition	Nominal Diameter (mm)		Width Across-flats (mm)		Tensile Strength R _m N/mm ² (MPa) Min	0,2 % Proof Strength N/mm ² (MPa)		Elongation			Hardness (HBW)		
	Over	Up to and inc.	Over	Up to and inc.		Min	Max	A _{100mm} (%)	A _{11,3} (%)	A (%)	Min	Max	
M	All		All		As manufactured								
R340	10	65	10	55	340	-	280	-	-	20	-	-	
H070	10	65	10	55	-	-	-	-	-	-	70	120	
R400	10	25	10	20	400	200	-	4	8	12	-	-	
H100	10	25	10	20	-	-	-	-	-	-	100	140	
R480	10	14	10	10	480	350	-	3	5	8	-	-	
H125	10	14	10	10	-	-	-	-	-	-	125	-	

EN 12168 - Hollow Rods for Free Machining

Material Condition	Wall Thickness (mm)		Tensile Strength R _m N/mm ² (MPa) Min	0,2 % Proof Strength N/mm ² (MPa)		Elongation A (%) Min	Hardness (HBW)		Hardness (HV)	
	Over	Up to and inc.		Min	Max		Min	Max	Min	Max
M	All		As manufactured							
R340	4	20	340	-	280	20	-	-	-	-
H070	4	20	-	-	-	-	70	120	80	130
R400	4	10	400	200	-	12	-	-	-	-
H100	4	10	-	-	-	-	100	140	110	150
R480	4	7	480	350	-	8	-	-	-	-
H125	4	7	-	-	-	-	125	-	135	-


STANDARD		EN 12164			EN 12165		EN 12168					
Dimension Range		Round Rod		Hexagonal, Square	Round Rod		Round and Hexagonal Hollow Rod, Outer Dim. Tol.			Hole Tolerance Round		Hole Tol. Hexagonal
Over	Up to & inc.	Class A	Class B	Rod	Class A	Class B	Class A	Class B	Class C	Class A	Class B	-
-	10	0 -0,06	0 -0,036	0 -0,09	-	-	-	-	-	-	-	-
10	13	0 -0,07	0 -0,043	0 -0,11	-	-	-	-	-	-	-	-
13	18	0 -0,07	0 -0,043	0 -0,11	-	-	-	-	-	±0,35	-	+0,70 -0
18	20	0 -0,08	0 -0,052	0 -0,13	-	-	-	-	-	±0,42	-	+0,84 -0
20	23	0 -0,08	0 -0,052	0 -0,13	-	-	-	-	-	±0,42	±0,17	+0,84 -0
23	26	0 -0,08	0 -0,052	0 -0,13	-	-	-	0 -0,21	-	±0,42	±0,17	+0,84 -0
26	30	0 -0,08	0 -0,052	0 -0,13	-	-	-	0 -0,21	0 -0,13	±0,42	±0,17	+0,84 -0
30	50	0 -0,16	-	0 -0,16	-	-	-	0 -0,25	0 -0,16	±0,80	±0,20	+1,6 -0
50	55	0 -0,19	-	0 -0,19	-	-	-	0 -0,46	0 -0,30	±0,95	±0,37	-
55	65	0 -0,19	-	-	-	-	±0,60	0 -0,46	0 -0,30	±0,95	-	-
65	80	-	-	-	-	-	±0,60	0 -0,46	0 -0,30	±0,95	-	-

For Hollow Rods

Minimum wall thickness is 4 mm. Eccentricity : % 8 (max.)

" For hollows, maximum outer diameter is 78 mm and maximum producible weight 28 kg in 1 meter."
Outer Cold Drawn - Internal Extruded
 Outer Class B - Hole Class A tolerance

Inner-Outer Cold Drawn
 Outer Class C - Hole Class B tolerance

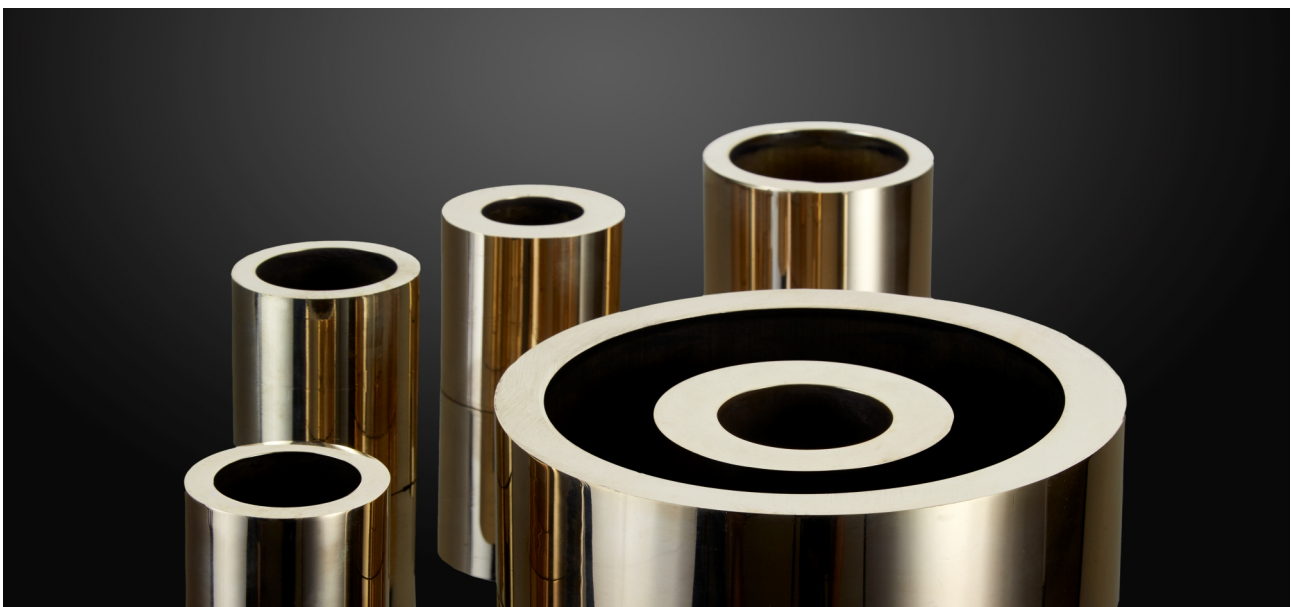Inner-Outer Extruded
 Outer Class A - Hole Class A tolerance




Headquarter

Eđitim Mah. Adım Sok. Orjin İş Merkezi No: 10 -18 Kat: 3 Daire No: 39 - 49 34722
Hasanpaşa / Kadıköy / İstanbul / Turkey
T: +90 216 414 45 35 pbx | F: +90 216 414 45 40

Factory

Çerkezköy Organize Sanayi Bölgesi Gazi Osman Paşa Mah. 8.Cad. No: 3 59500
Çerkezköy / Tekirdađ / Turkey
T: +90 282 725 19 60 pbx | F: +90 282 725 19 70